


VOLVO TEMP CYCLE TEST PART



DSC_0273

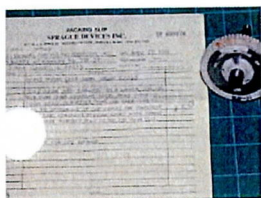

DSC_0274



DSC_0275




DSC_0276




DSC_0277




DSC_0278

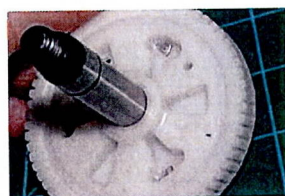

DSC_0279

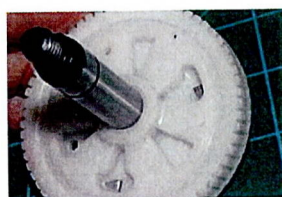

DSC_0280

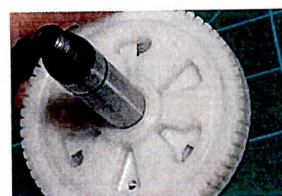

DSC_0281



DSC_0282



DSC_0283



DSC_0284



DSC_0285



DSC_0286



DSC_0287



DSC_0288

MACK WIPER MOTOR GEAR PARTS




DSC_0289



DSC_0290




DSC_0306

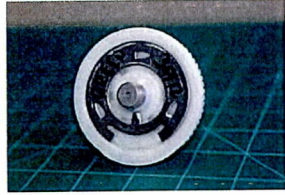


DSC_0307




DSC_0308

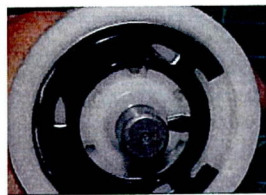

DSC_0309

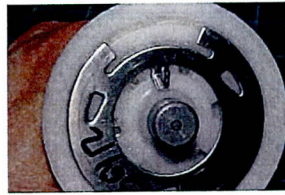


DSC_0310

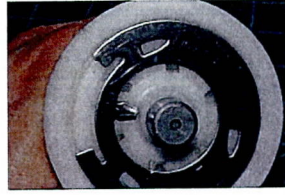

DSC_0311




DSC_0312

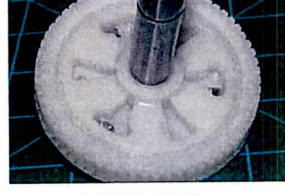


DSC_0313




DSC_0314

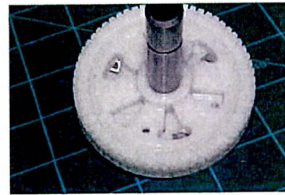


DSC_0315

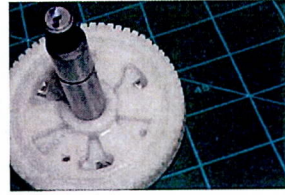

DSC_0316

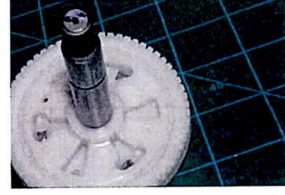


DSC_0317

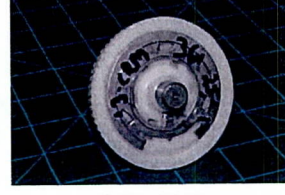


DSC_0318




DSC_0319

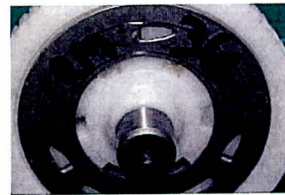


DSC_0320

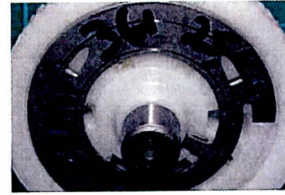


DSC_0321

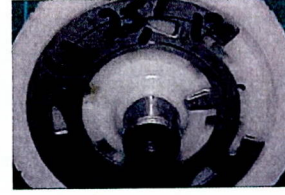


DSC_0322

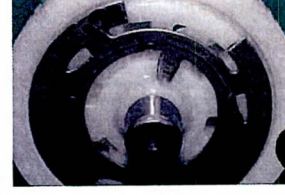


DSC_0323

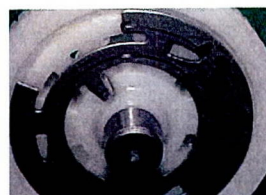

DSC_0324

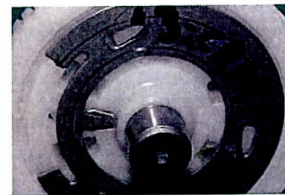

DSC_0325

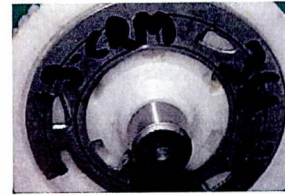


DSC_0326




DSC_0327




DSC_0328

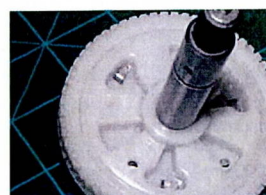


DSC_0329

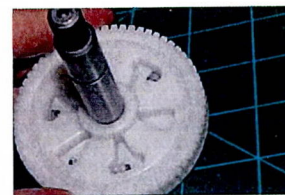

DSC_0330

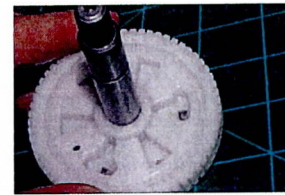


DSC_0331

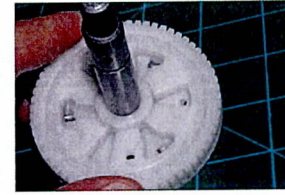

DSC_0332

AGED PARTS

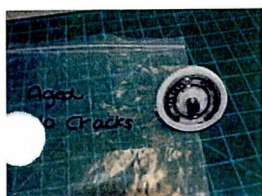

DSC_0333



DSC_0334



DSC_0335




DSC_0336



DSC_0337




DSC_0338

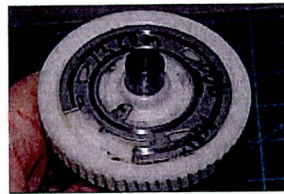


DSC_0339




DSC_0340

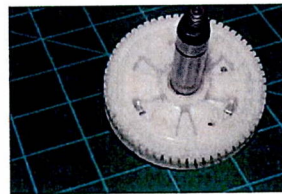


DSC_0341

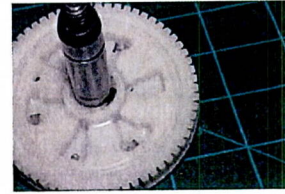


DSC_0342

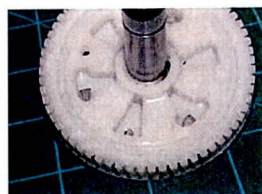

DSC_0343

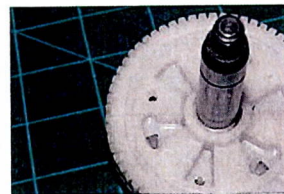

DSC_0344

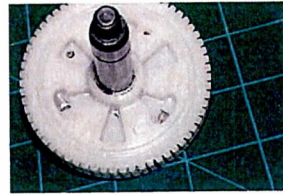

DSC_0345



DSC_0346



DSC_0347



DSC_0348



DSC_0349


WIPER MOTOR PARTS



DSC_0350



DSC_0351

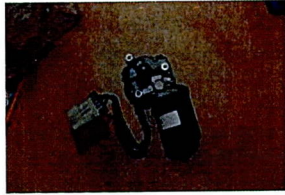

DSC_0352




DSC_0353




DSC_0354



DSC_0355

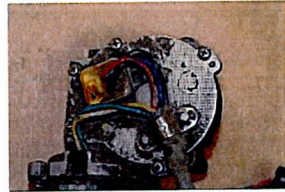


DSC_0356

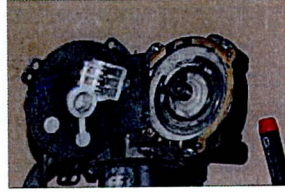

DSC_0357




DSC_0358

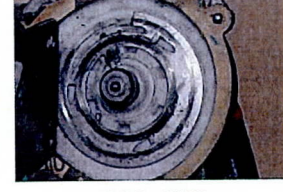


DSC_0359




DSC_0360

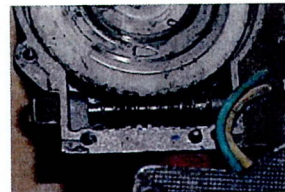


DSC_0361

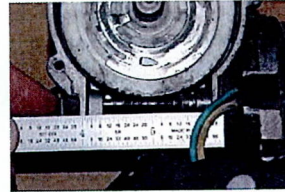


DSC_0362

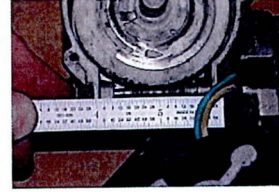


DSC_0363

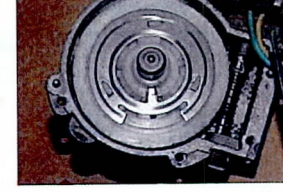


DSC_0364

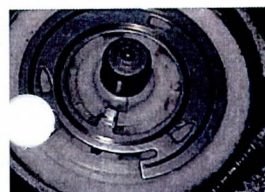


DSC_0365

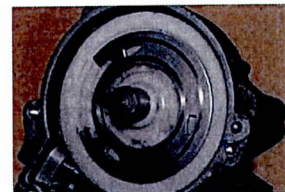


DSC_0366

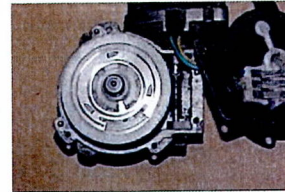

DSC_0367

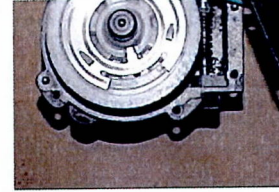

DSC_0368

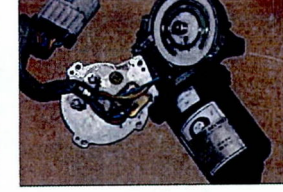


DSC_0369




DSC_0370




DSC_0371

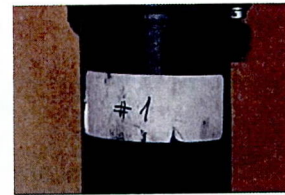


DSC_0372

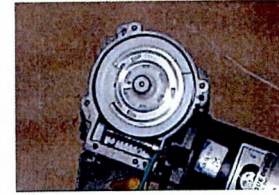


DSC_0373

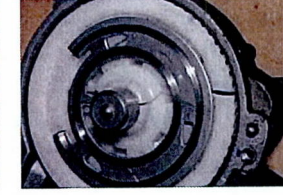


DSC_0374

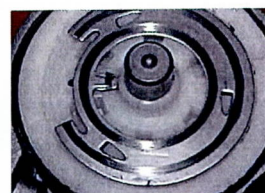


DSC_0375

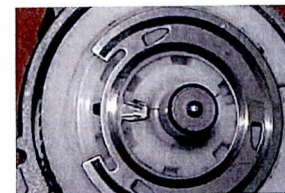

DSC_0376

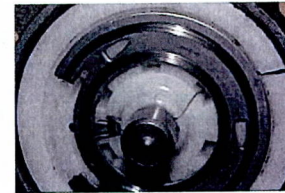


DSC_0377

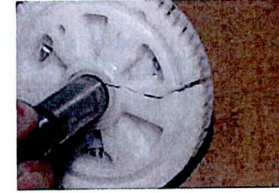


DSC_0378




DSC_0379

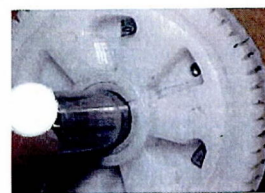


DSC_0380

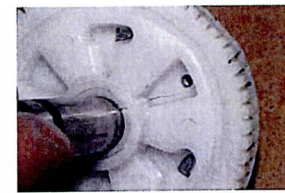

DSC_0381

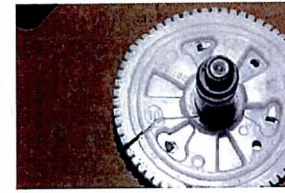


DSC_0382

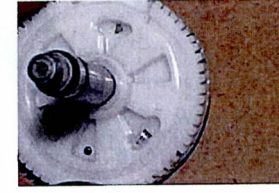


DSC_0383




DSC_0384

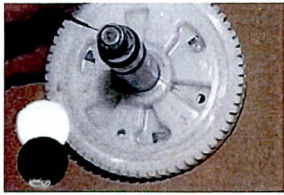


DSC_0385

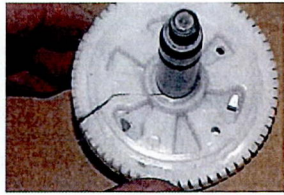


DSC_0386

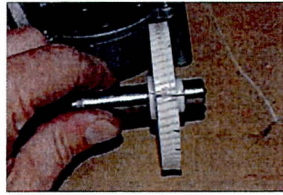

DSC_0387

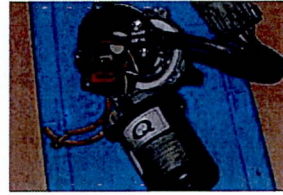

DSC_0388

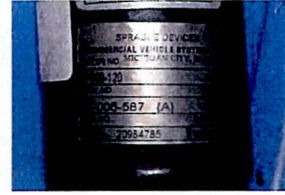

DSC_0389




DSC_0390




DSC_0391




DSC_0392

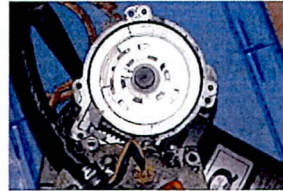


DSC_0393

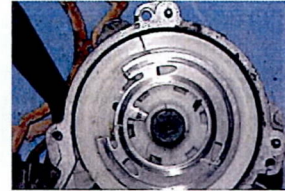


DSC_0394

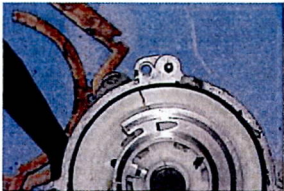


DSC_0395

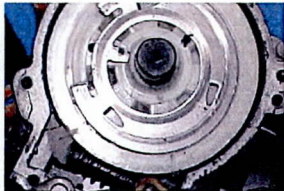


DSC_0396

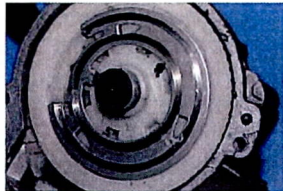

DSC_0397

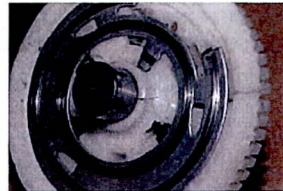

DSC_0398

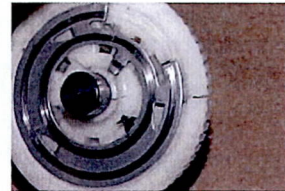


DSC_0399



DSC_0400




DSC_0401

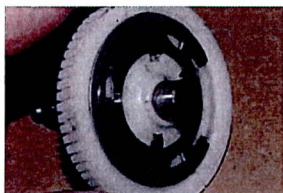

DSC_0402



DSC_0403

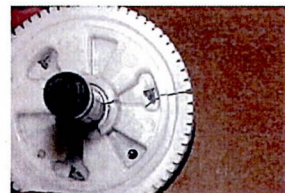

DSC_0404




DSC_0405



DSC_0406



DSC_0407

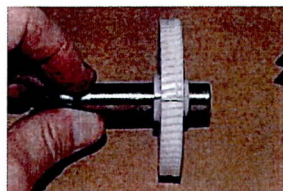


DSC_0408




DSC_0409




DSC_0410

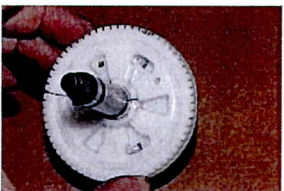

DSC_0411

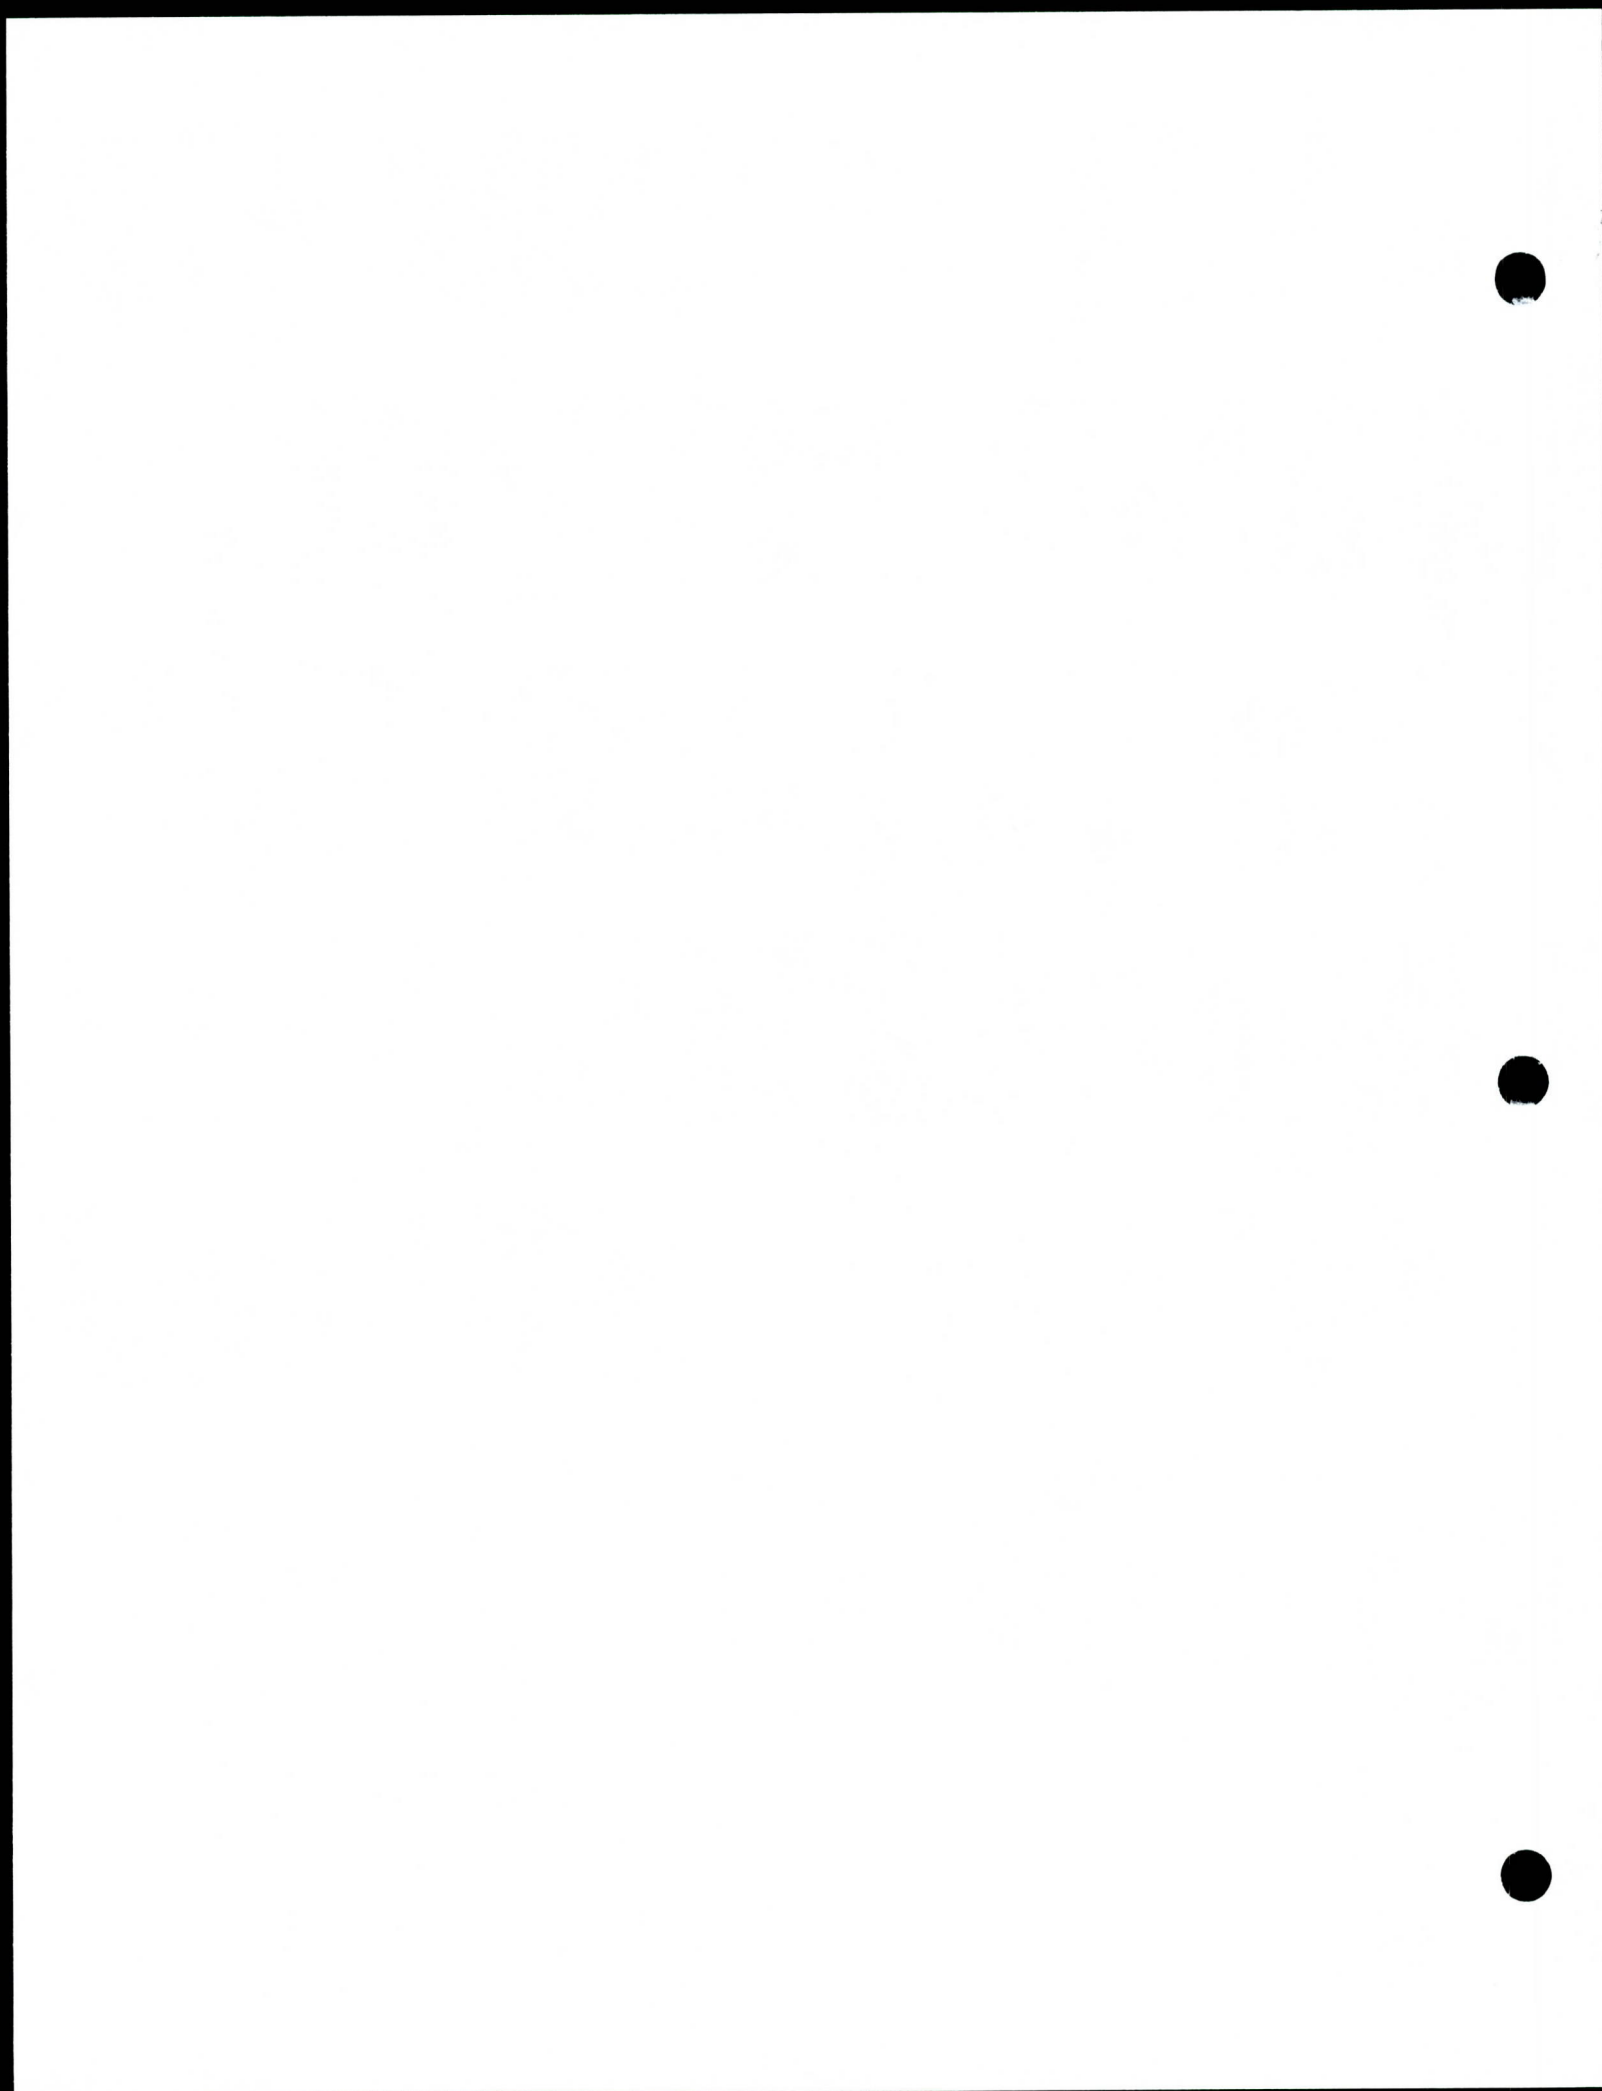


MICROSCOPY
PHOTOGRAPHS

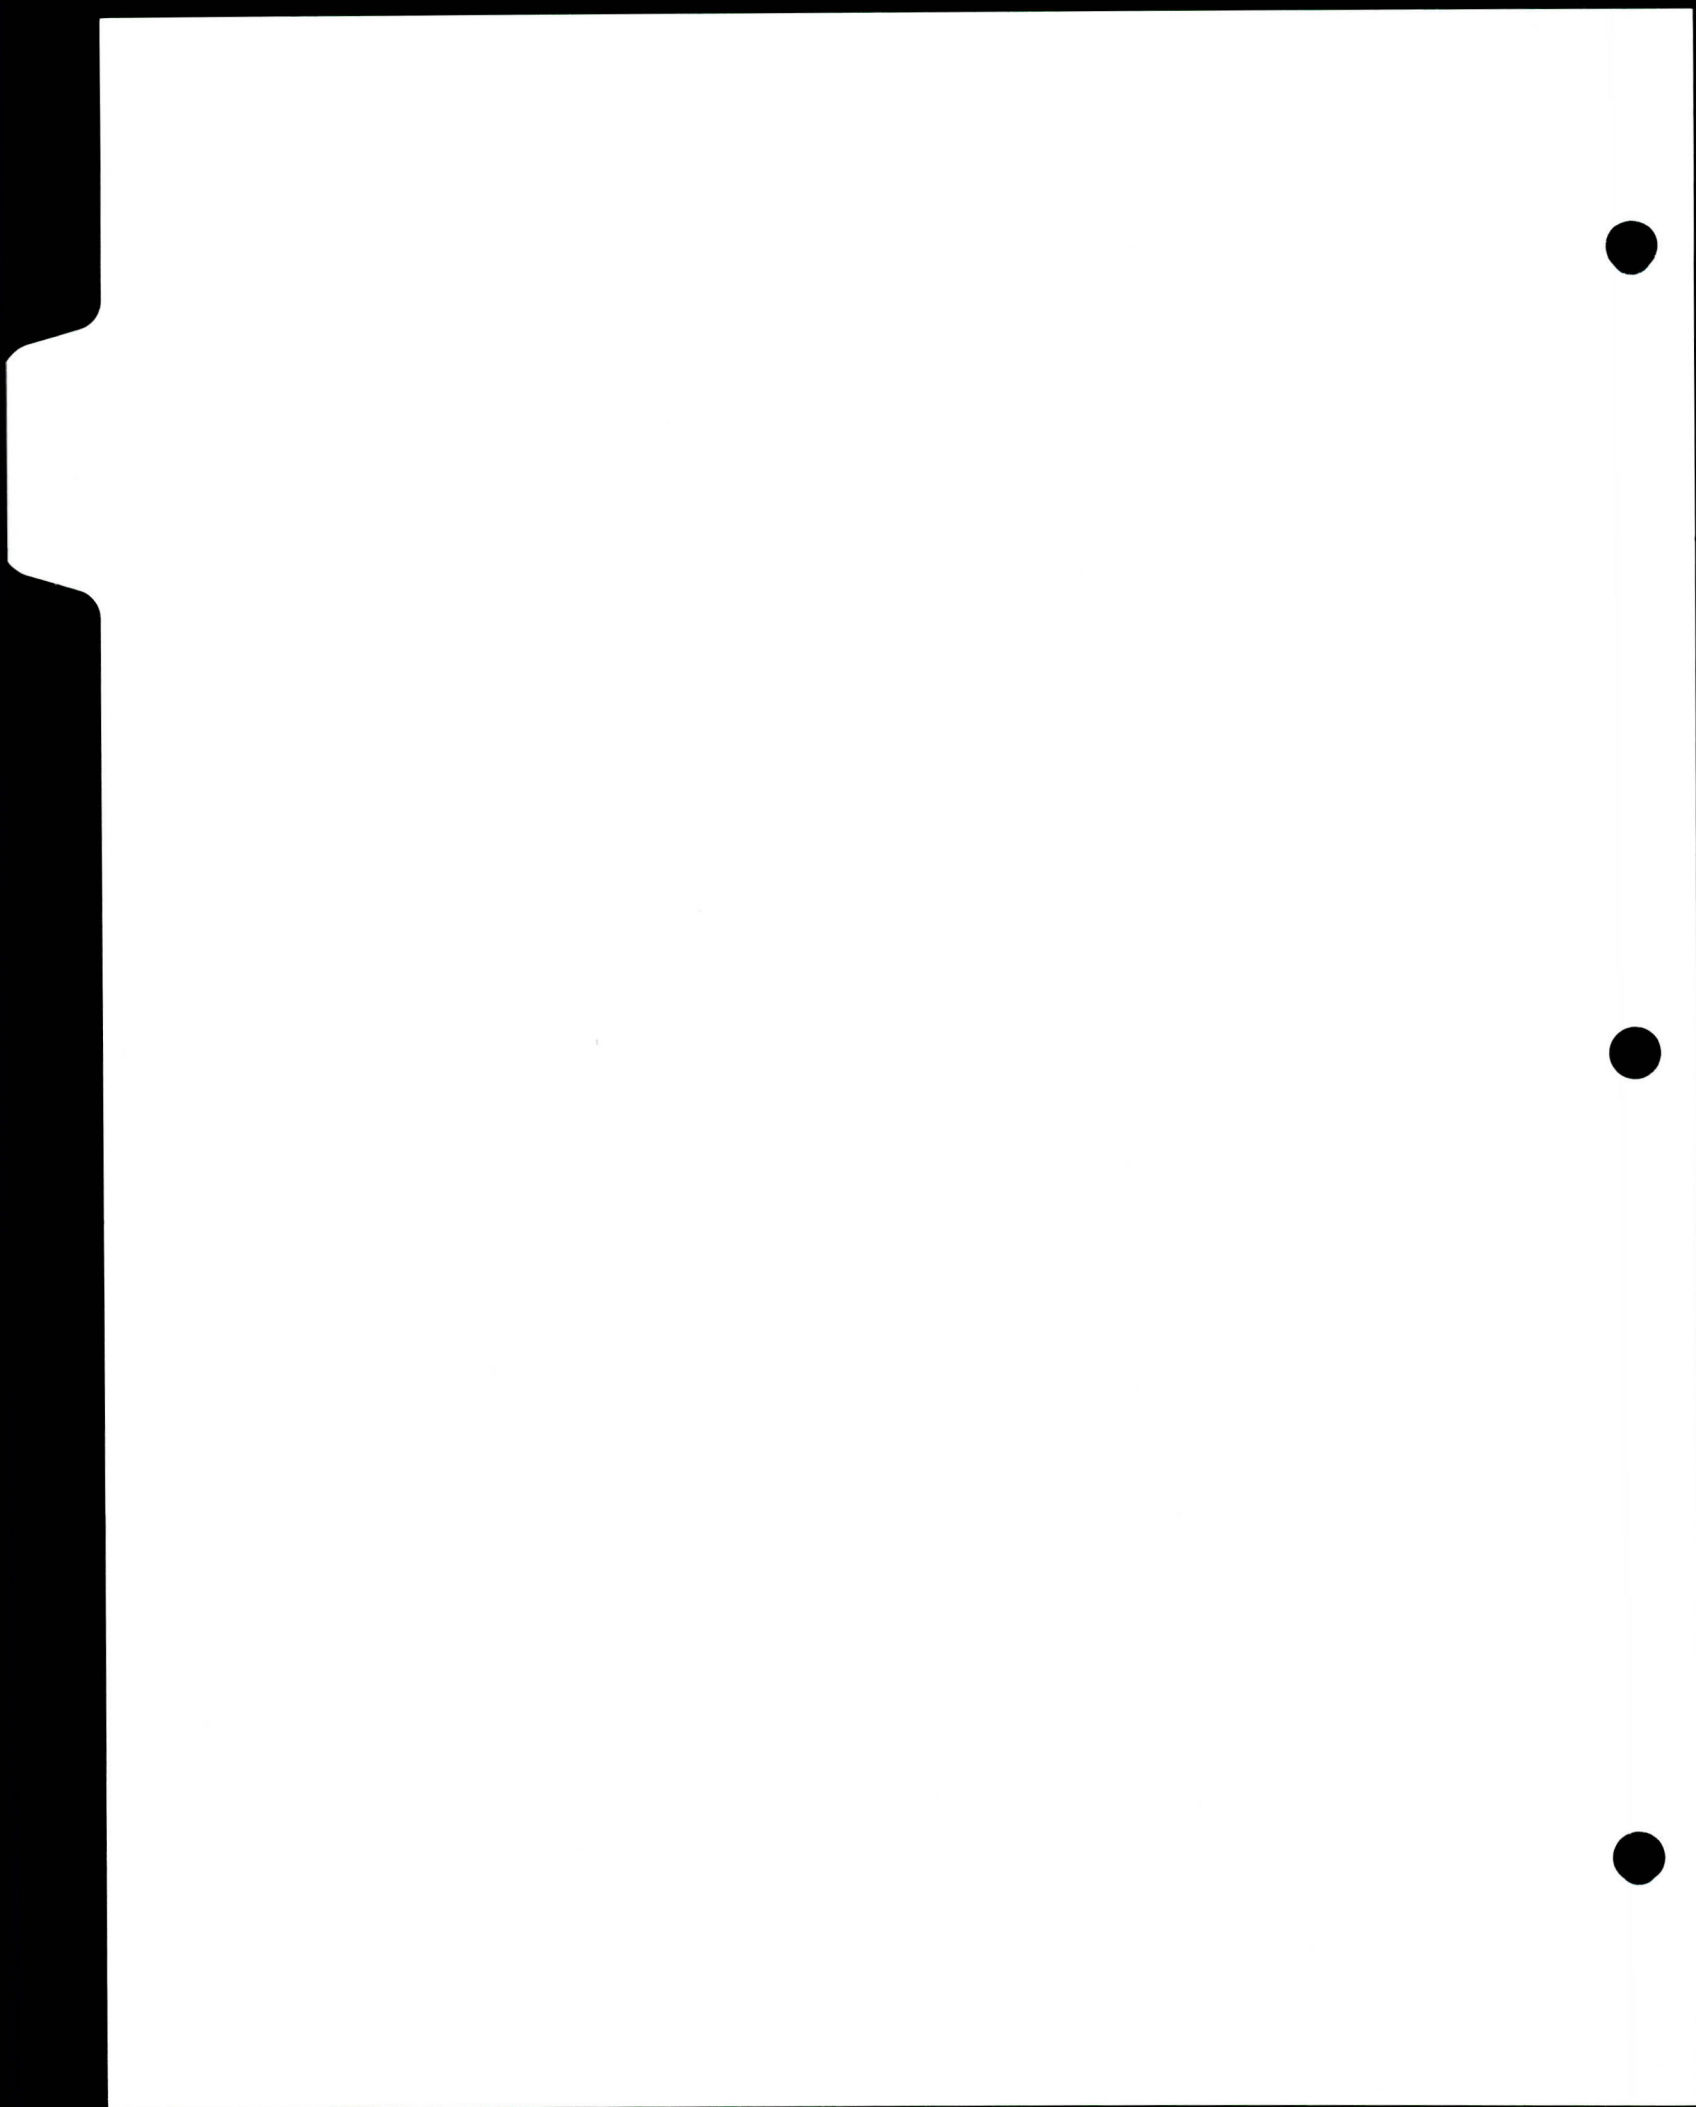





Voids in polymer created by poor polymer processing. Fracture of rim.

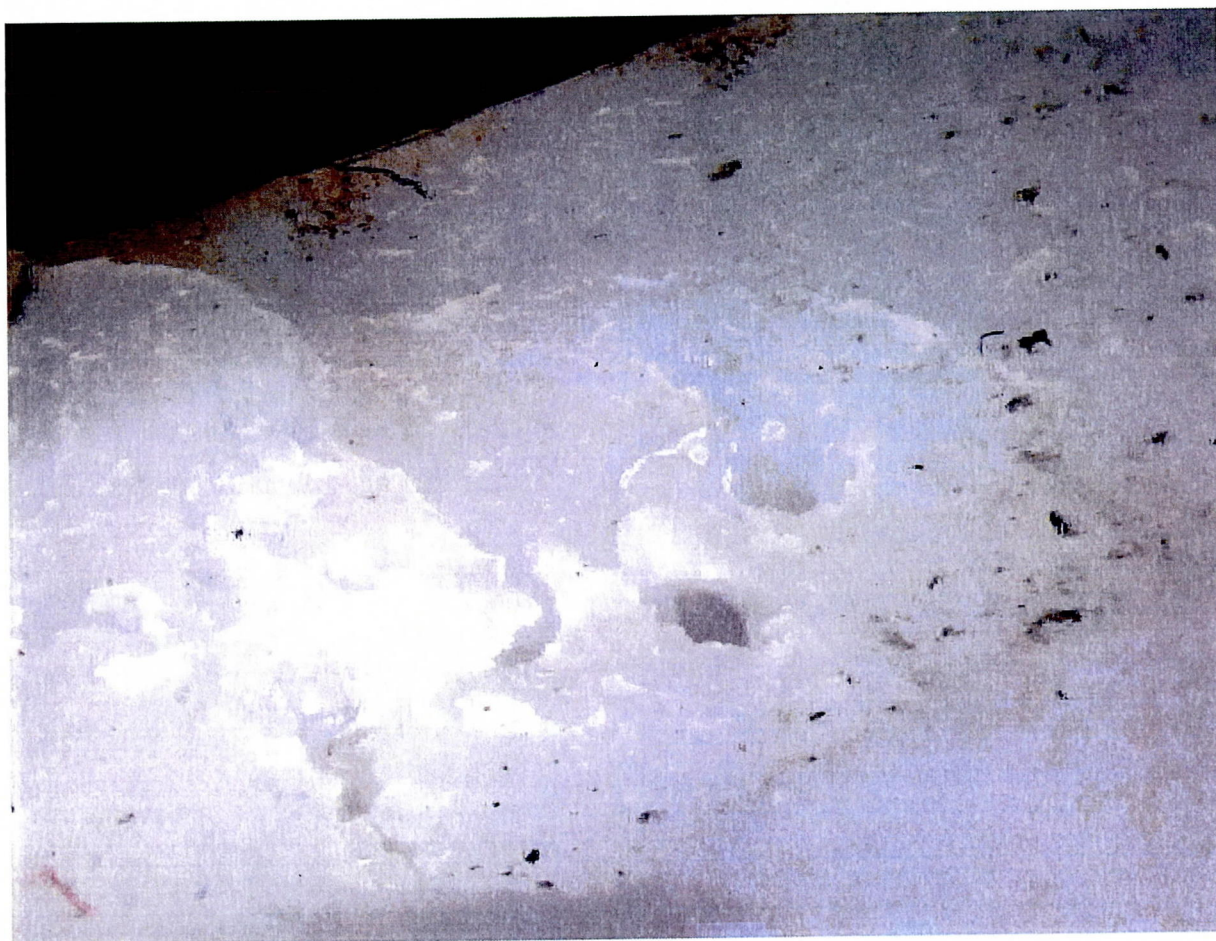


Voids in polymer, poor polymer flow/ weld.

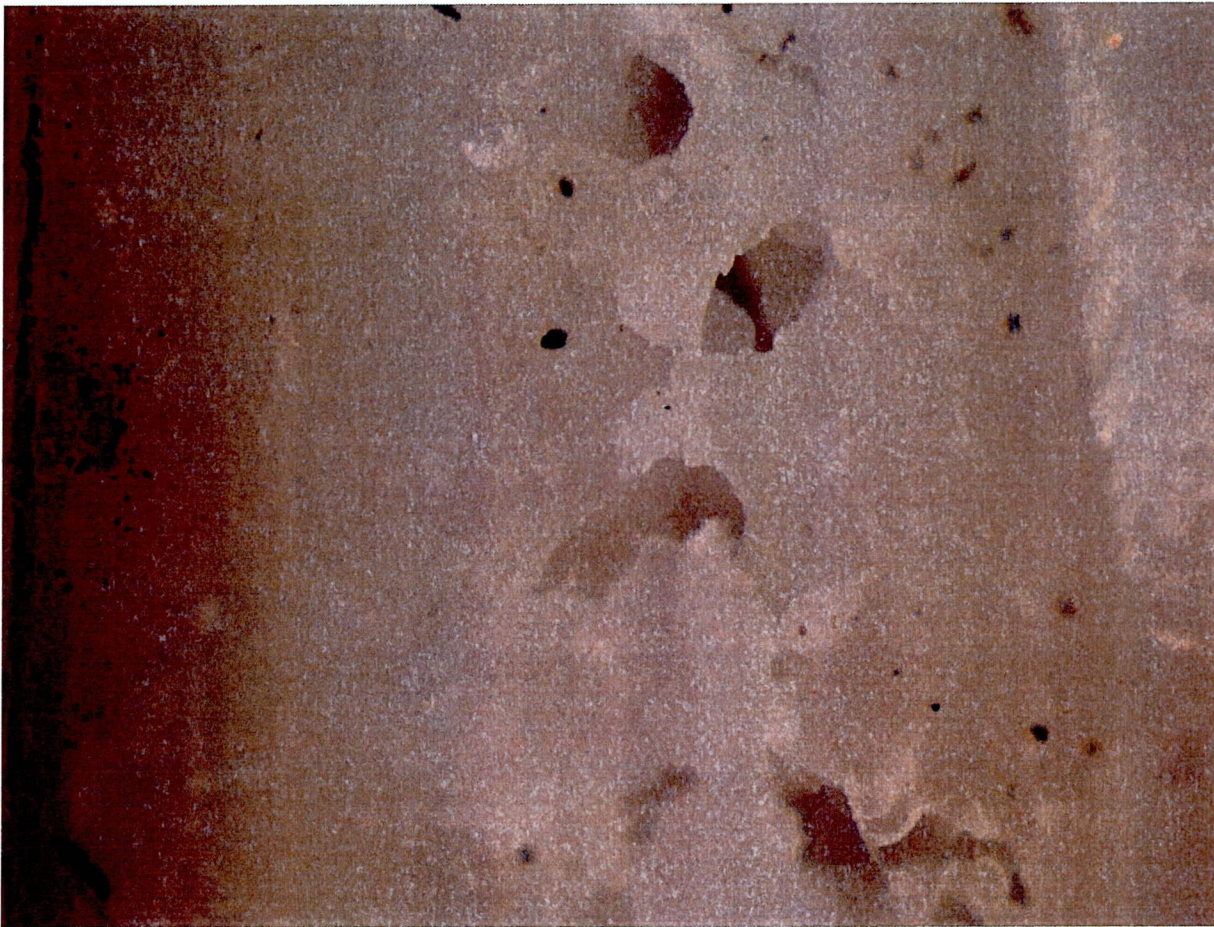


Voids in polymer.

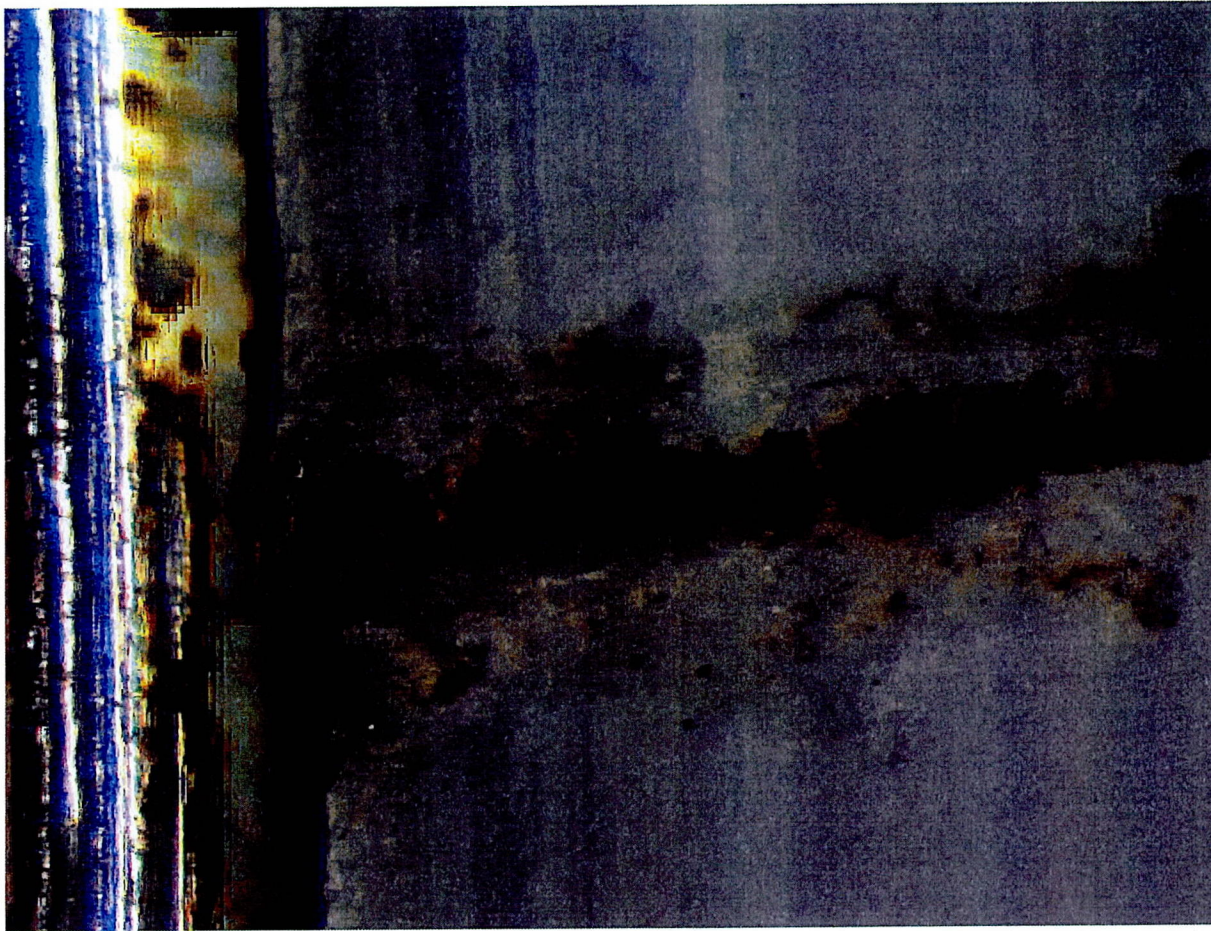


Ductile fracture. Pulled at weld lines.

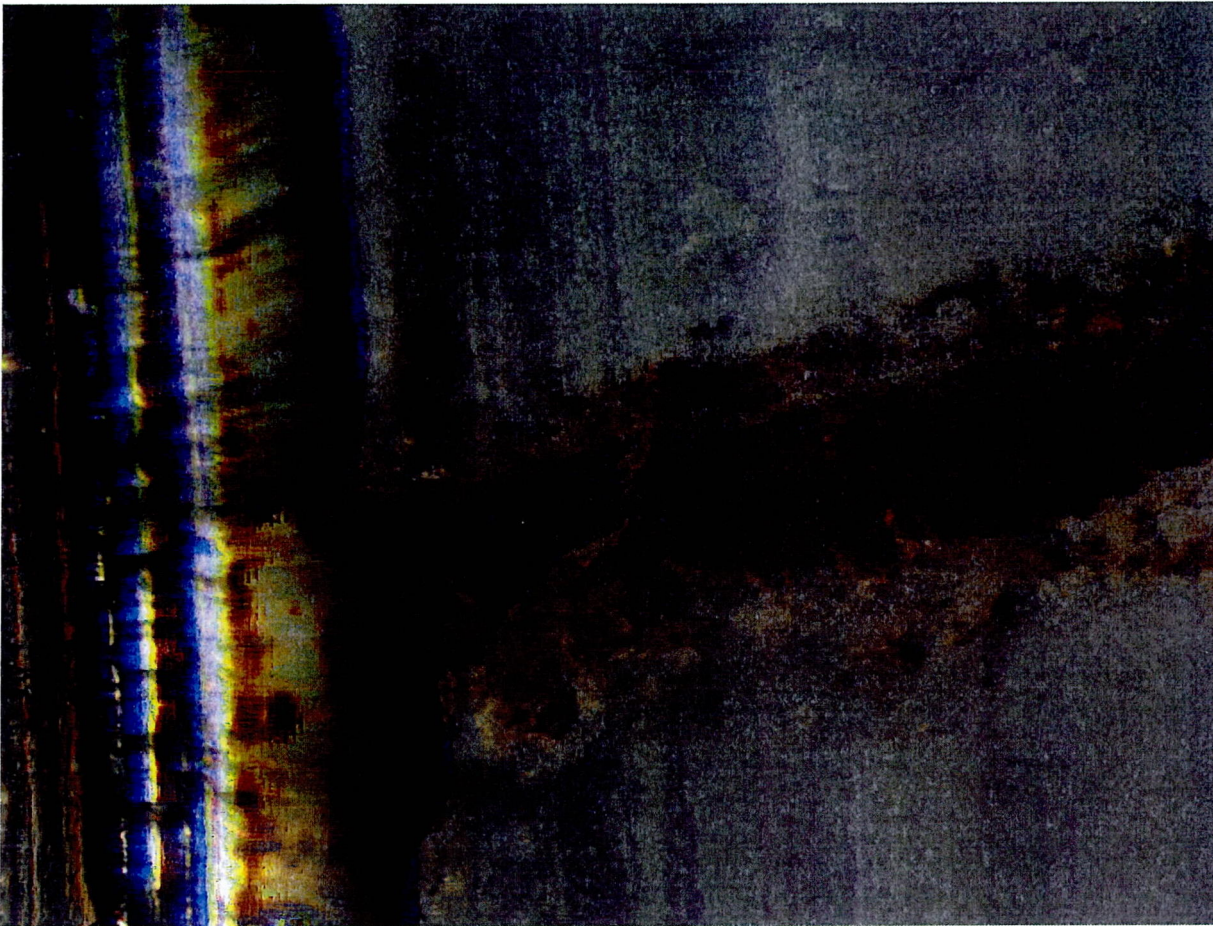


Ductile fracture at weld lines.

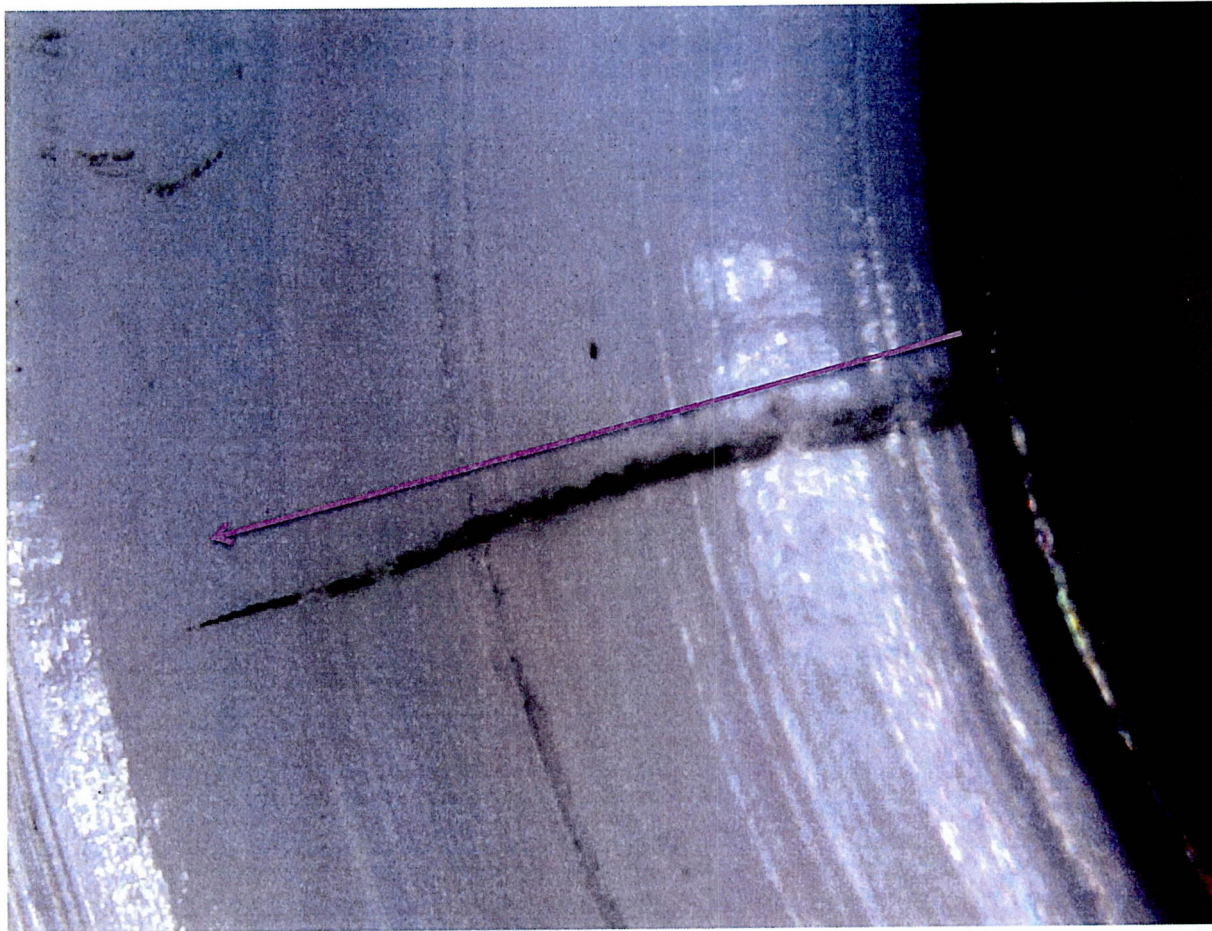

Radial fracture at insert.

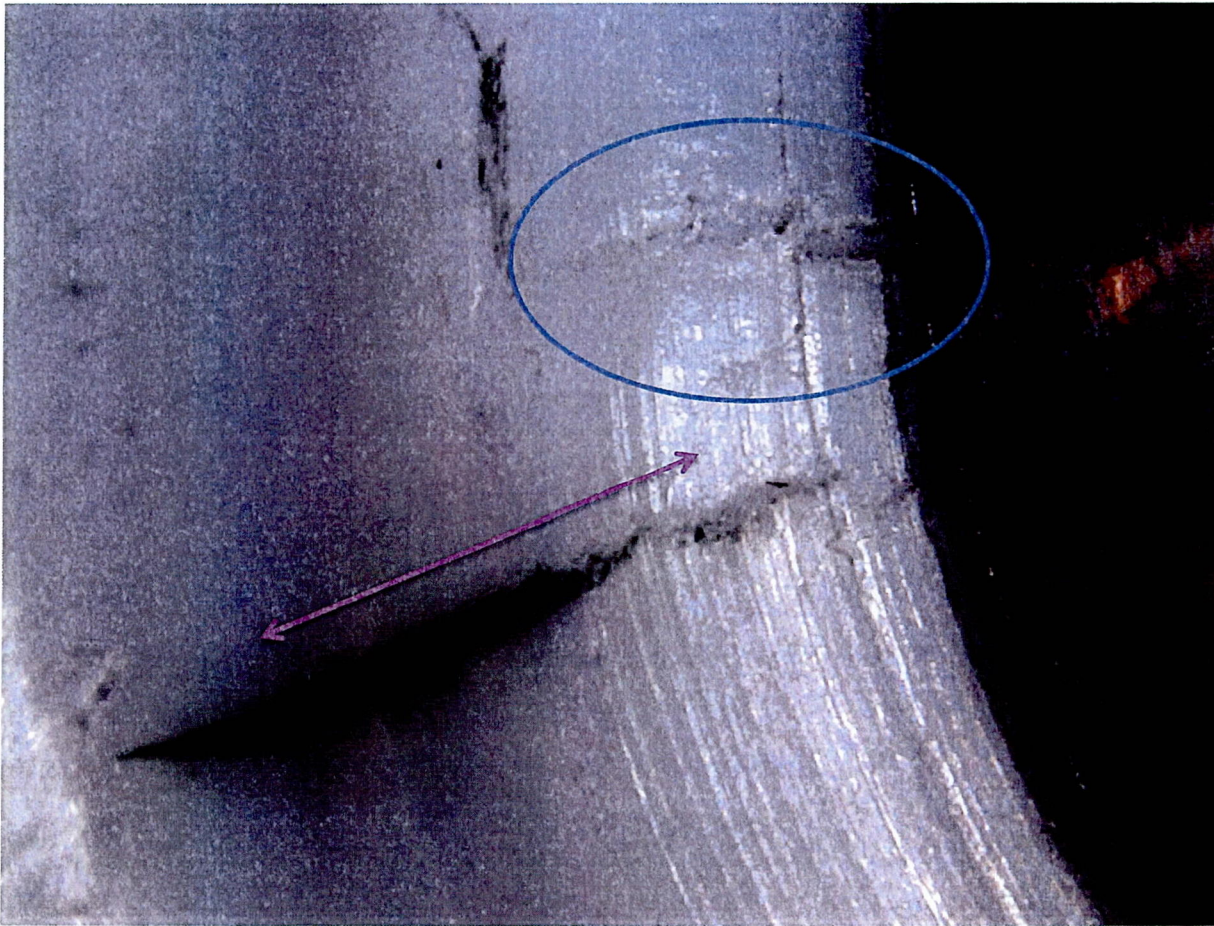

Radial fracture and stress lines at insert.

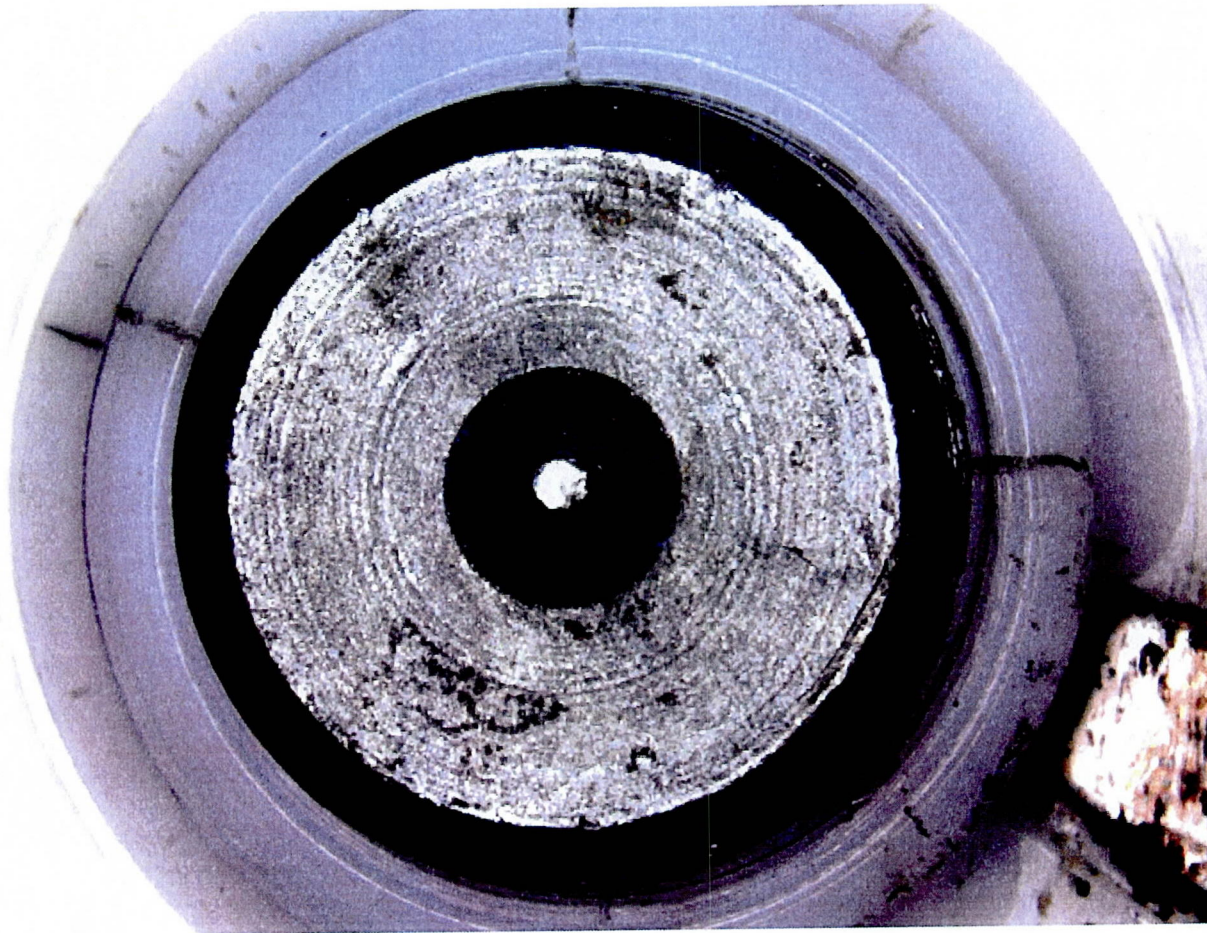

Fractures are consistently at 0, 60, 120, 180, 240, 300 degree locations. Often, on opposing (180 degree) sides. Indicative of hoop stress.




Cracks at insert groove.







Voids in polymer created by poor polymer processing. Fracture of rim.

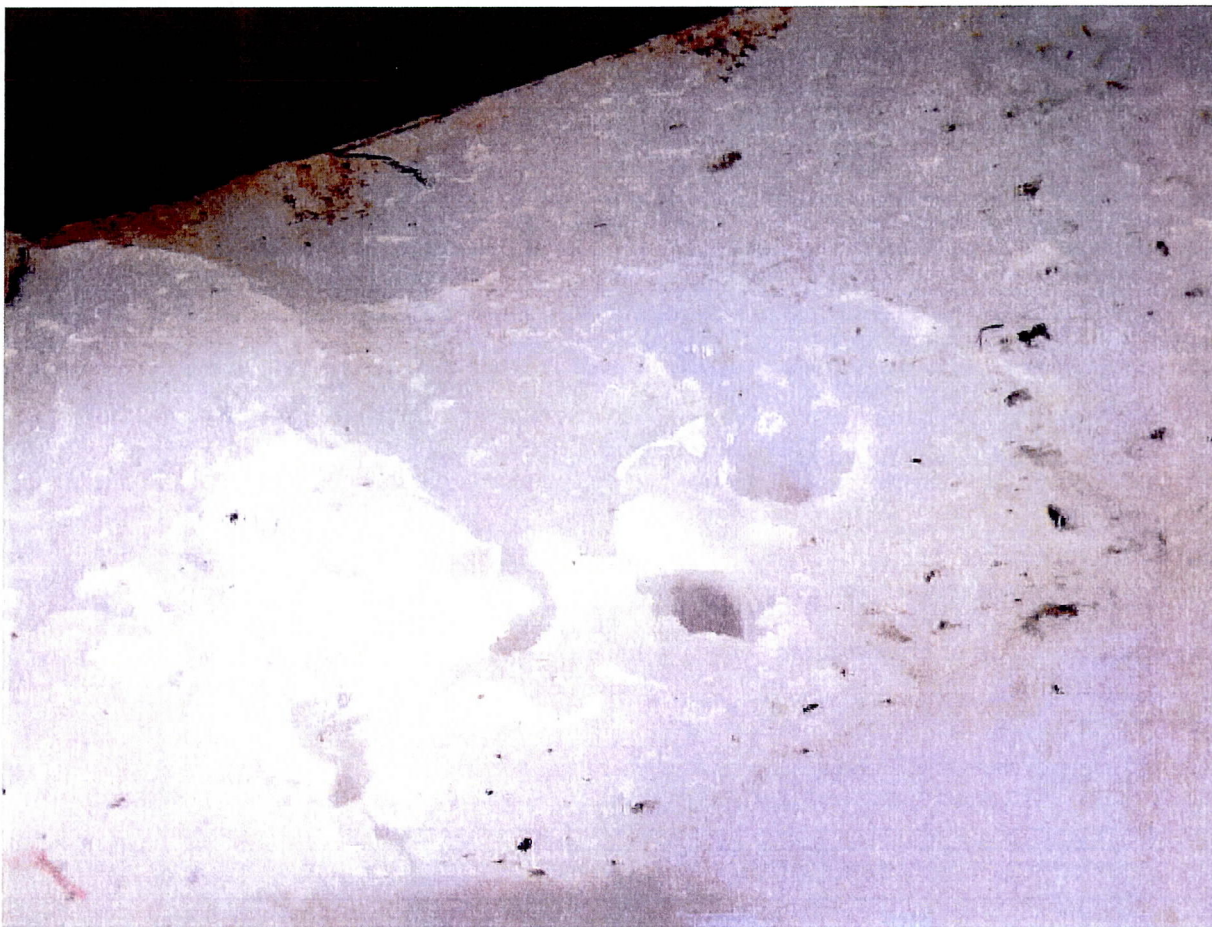


Voids in polymer, poor polymer flow/ weld.

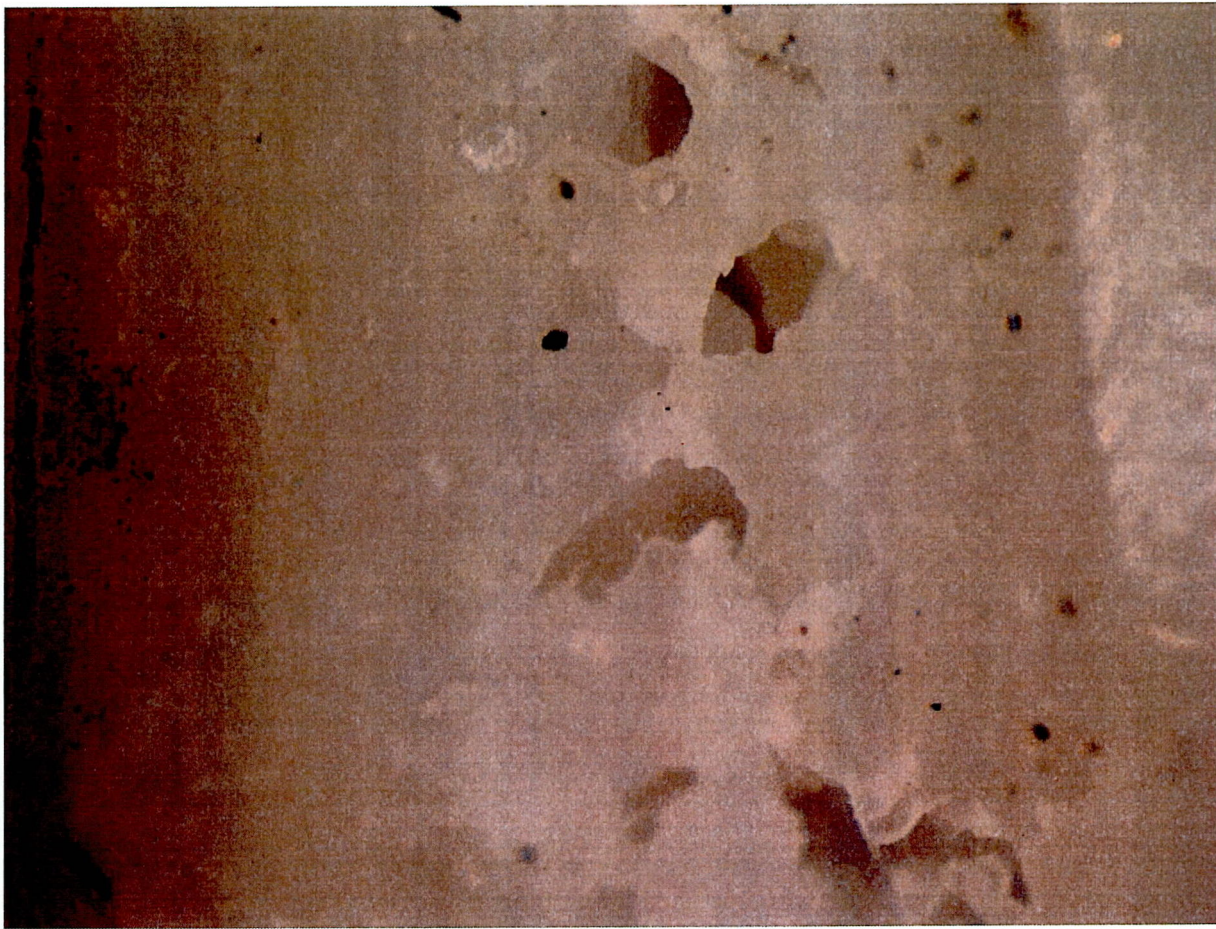


Voids in polymer.

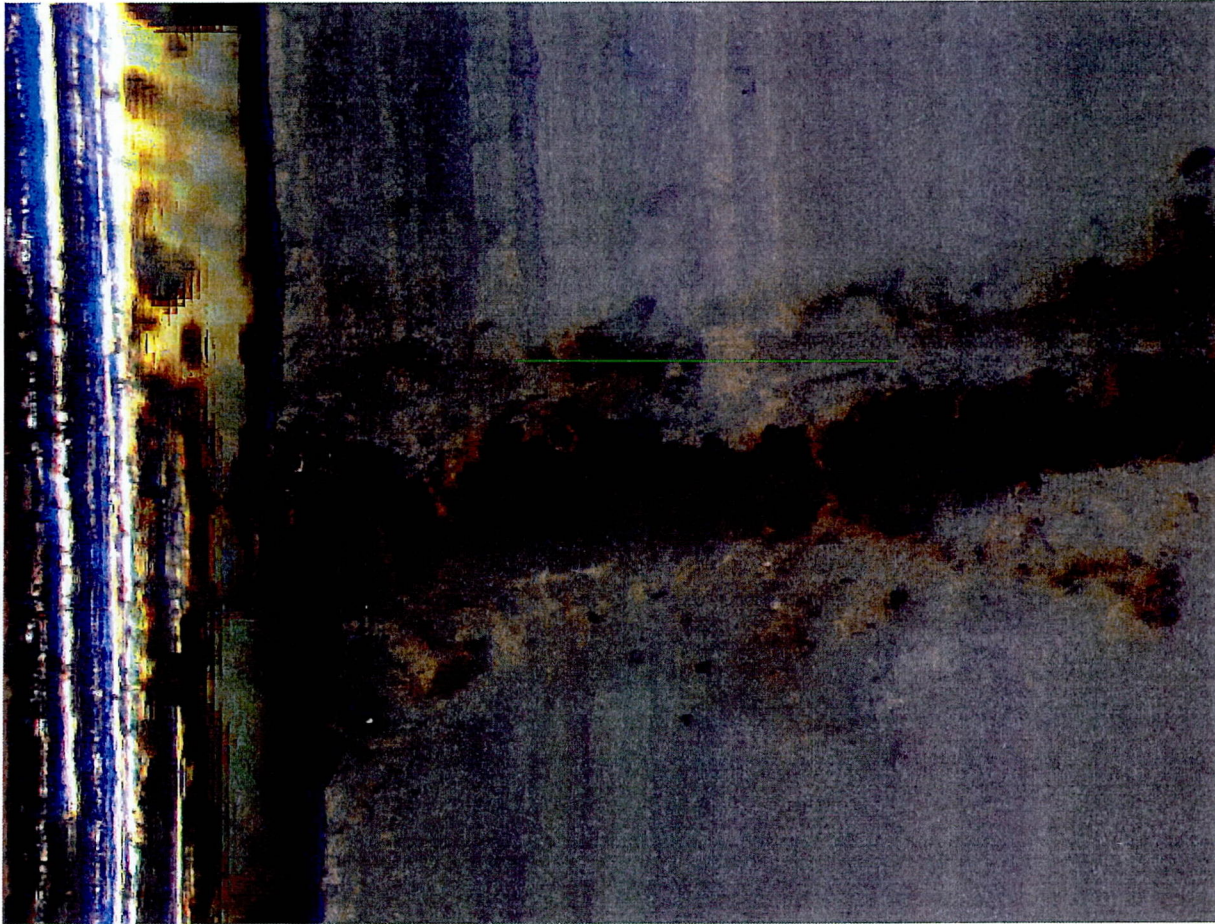


Ductile fracture. Pulled at weld lines.

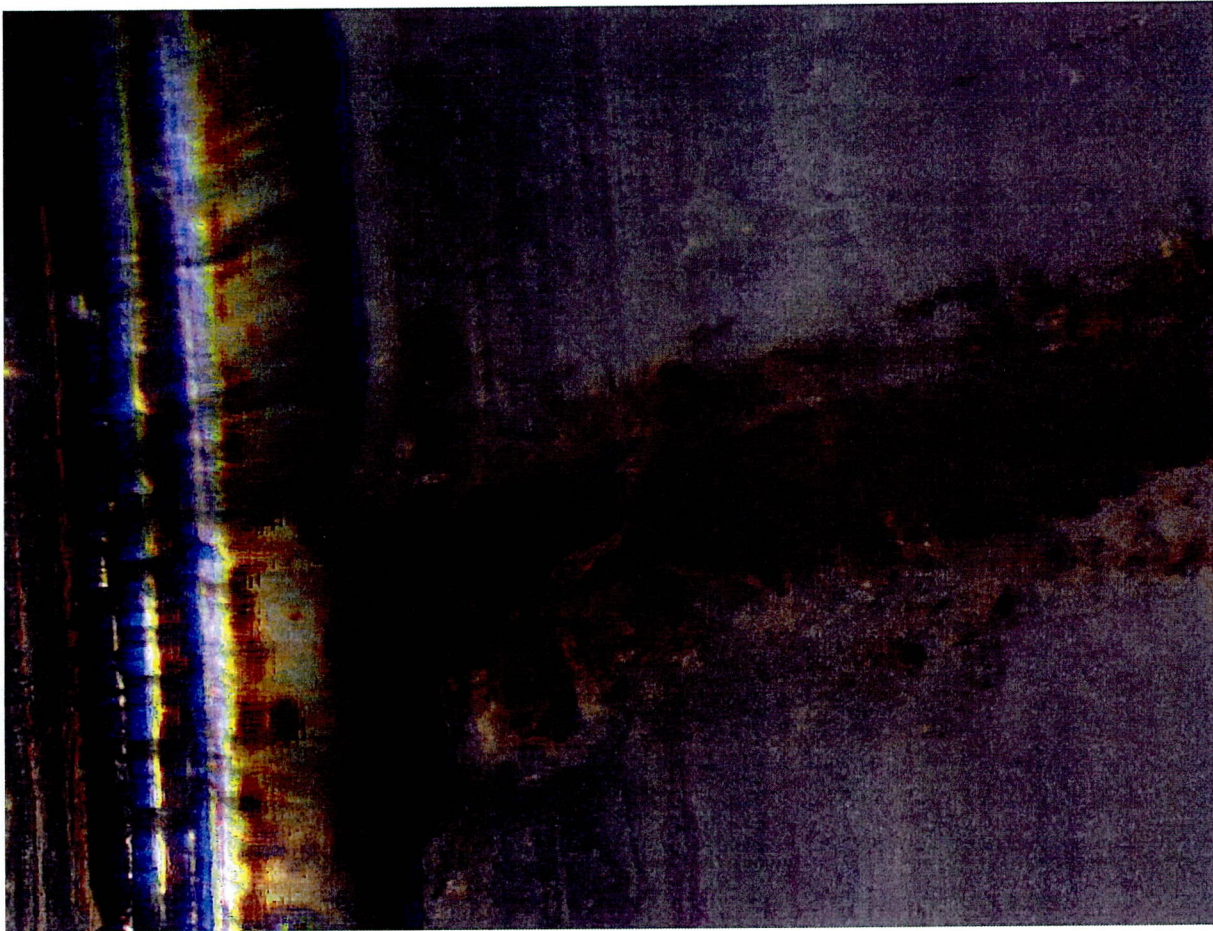


Ductile fracture at weld lines.

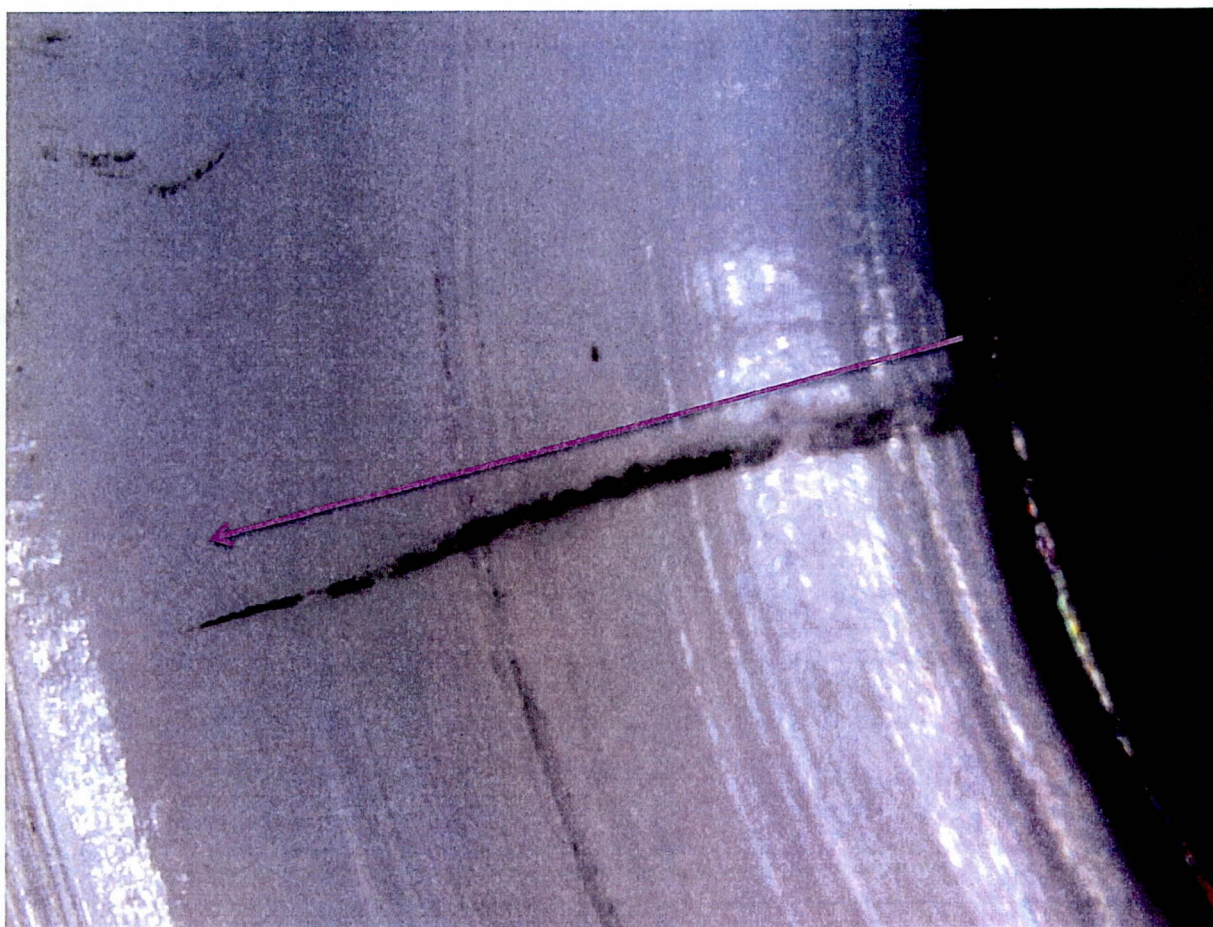

Radial fracture at insert.

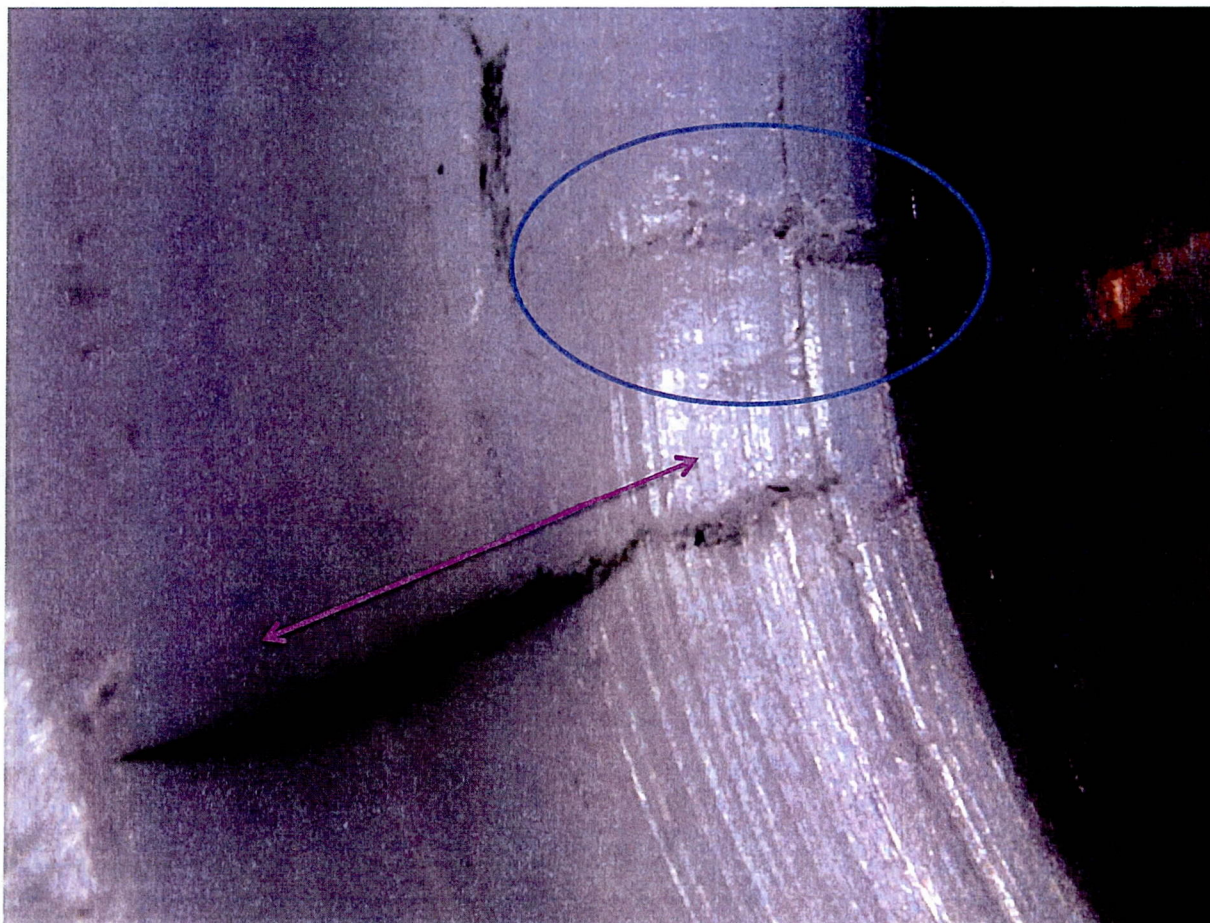

Radial fracture and stress lines at insert.

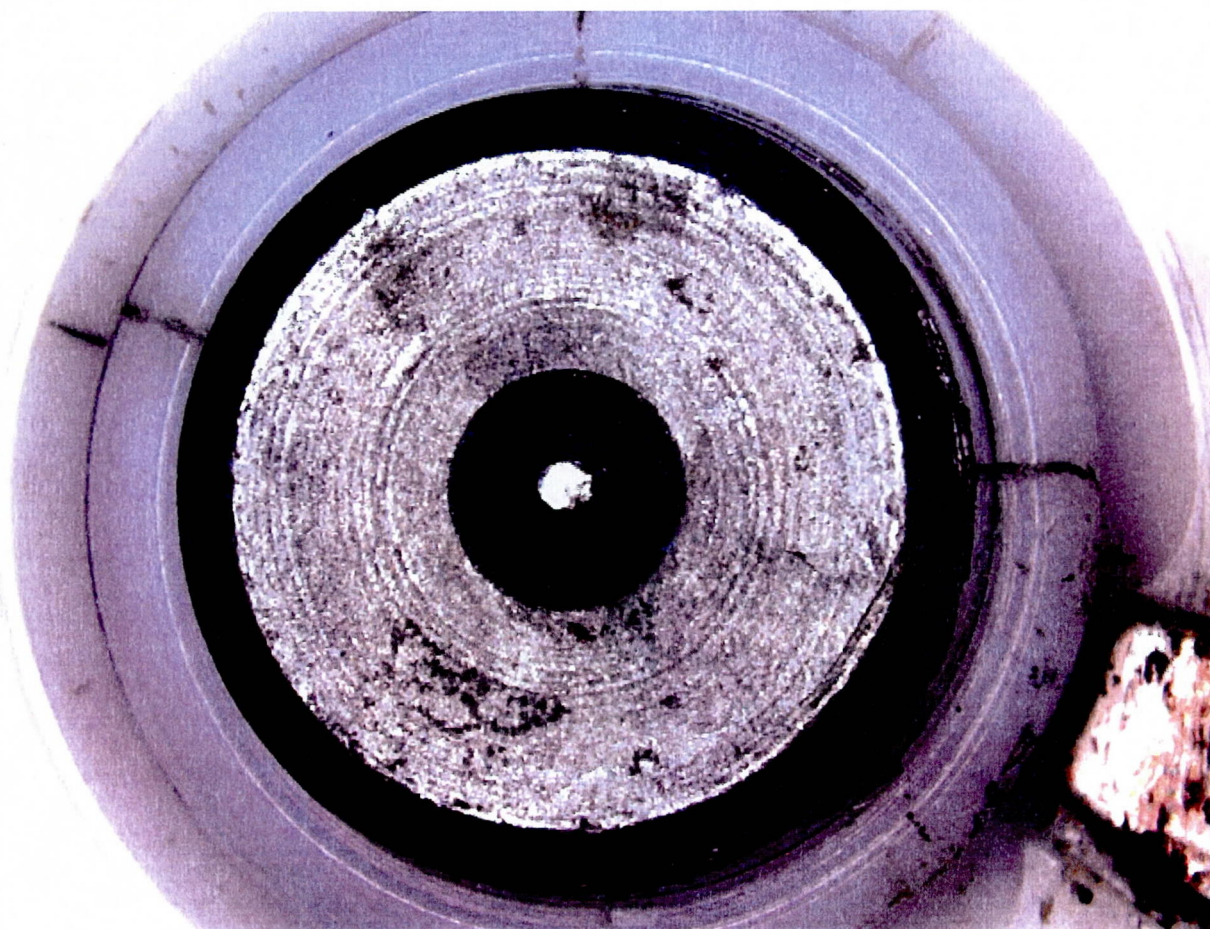

Fractures are consistently at 0, 60, 120, 180, 240, 300 degree locations. Often, on opposing (180 degree) sides. Indicative of hoop stress.




Cracks at insert groove.

POLYMERS

DuPont[™] Engineering Polymers

General Design Principles – Module I

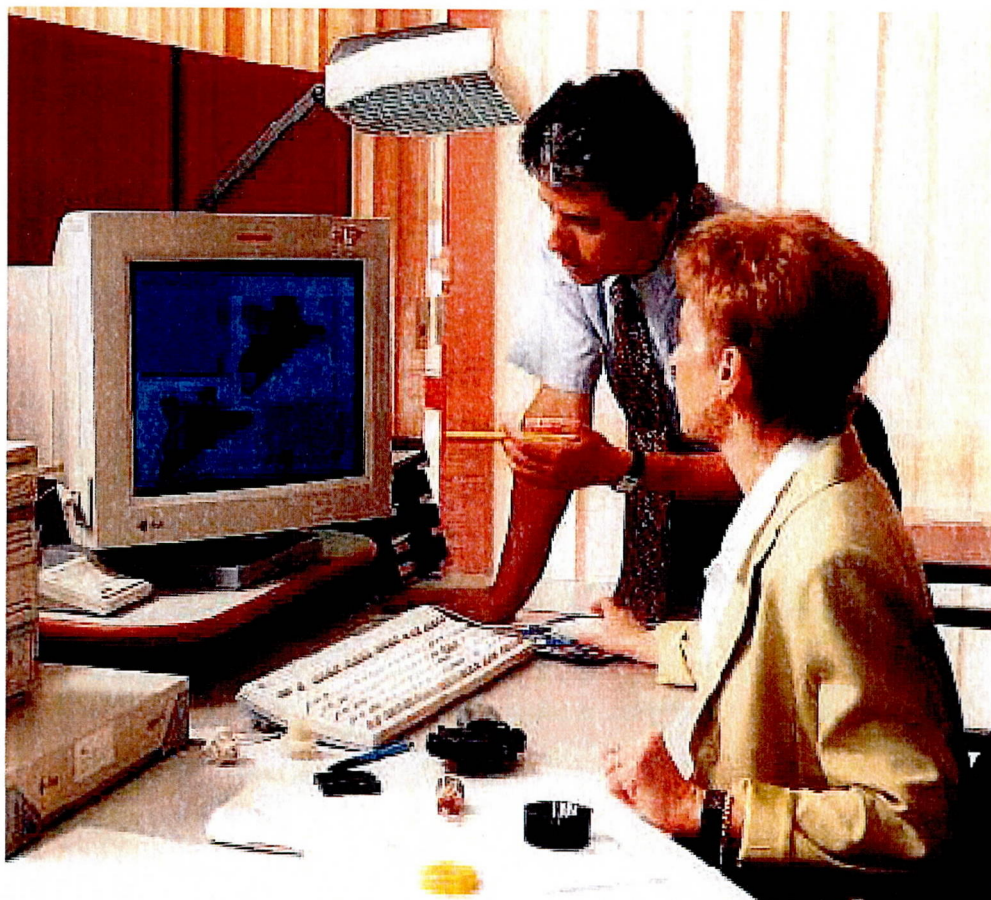

© DuPont registered trademarks of E.I. du Pont de Nemours and Company
DuPont and The miracles of science[™] are trademarks of E.I. du Pont de Nemours and Company

The miracles of science[™]

DuPont Engineering Polymers – General Design Principles

Table of Contents

1 General	Page	8 Gears (continued)	
Defining the End-Use Requirements	3	Bevel Gear Design	70
Design Check List	4	Fillet Radius	70
Prototyping the Design	5	Methods of Fastening	70
Computer Simulations	5	Combined Functions – Design Examples	71
Testing the Design	6	When to Use DELRIN® or ZYTEL®	73
Writing Meaningful Specifications	6	9 Assembly Techniques – Category I	
2 Injection Moulding		Mechanical Fasteners	75
The Process and Equipment	7	Plastic Threads	78
Trouble Shooting Guide for Moulding Problems	8	Press Fittings	81
3 Moulding Considerations		Snap-Fits	83
Uniform Walls	11	Hub Joints	87
Configurations	11	10 Assembly Techniques - Category II	
Draft and Knock-Out Pins	12	SPIN WELDING	91
Fillet and Radii	12	Practical Methods	91
Bosses	13	Pivot Welding	91
Ribbing	13	Inertia Welding	94
Holes and Coring	13	Machines for Inertia Welding	96
Threads	15	Jigs (Holding Devices)	98
Undercuts	16	Joint Profiles	101
Moulded-in Inserts	17	Calculations for Tools and Machines	102
Tolerances	18	Graphical Determination of Parameters	103
Shrinkage and Warpage	19	Quality Control of Welded Parts	104
4 Structural Design Formulae		Welding Double Joints	106
Short Term Loads	21	Welding Reinforced and Dissimilar Plastics	107
Modulus for Isotropic Materials	22	Spin Welding Soft Plastics and Elastomers	107
Orthotropic Material	23	ULTRASONIC WELDING	111
Other Loads	23	Ultrasonic Welding Process	111
Long Term Loads	24	Welding Equipment	112
Ribs and Strengthening Members	27	Part Design Considerations	115
Structural Design Formulae	33	Ultrasonic Welding Variables	119
5 Design Examples		Guide to Equipment Operation	120
Redesigning the Wheel	45	Welding Performance	121
Chair Seats Reevaluated	48	Other Ultrasonic Joining Techniques	123
Wheelbarrow Frame – a Potential Design	48	Safety	125
6 Springs and Living Hinges		VIBRATION WELDING	126
Design of Living Hinges	50	Basic Principles	126
7 Bearings		Definition of Motion Centre	126
Shaft Hardness and Finish	51	Arrangements for Producing Vibrations	127
Bearing Surface	51	Welding Conditions	128
Accuracy	52	Joint Design	129
Bearing Clearance	53	Test Results on Angular Welded Butt Joints	130
Lubrication	53	Joint Strength versus Welded Surface	130
Protection Against Dirt Penetration	53	Joint Strength versus Specific Welded Pressure	131
Thermal Conditions	54	Design Examples	131
Calculation of Bearings	54	Comparison with other Welding Techniques	132
Design Examples	56	Design for Vibration Welded Parts	133
Testing Guidelines	57	HOT PLATE WELDING	135
8 Gears		TRANSMISSION LASER WELDING	138
Gears Design	59	RIVETING	142
Designing for Stall Torque	61	11 Machining, Cutting, Finishing	
Gear Proportions	61	Safety Precautions	145
Accuracy and Tolerance Limits	63	Machining HYTREL®	145
Backlash and Centre Distances	64	Machining and Cutting of DELRIN®	147
Mating Material	65	Finishing of DELRIN®	148
Lubrication	66	Annealing of DELRIN®	148
Testing Machined Prototypes	66	Machining and Cutting of ZYTEL®	149
Prototype Testing	66	Finishing of ZYTEL®	151
Helical Gear Design	66	Annealing of ZYTEL®	152
Worm Gear Design	67		
Mating Material	70		

8 – Gears

Introduction

DELTRIN® acetal resins and ZYTEL® nylon resins are used in a wide variety of gear applications throughout the world. They offer the widest range of operating temperature and highest fatigue endurance of any thermoplastic gear material, accounting for their almost universal use in non-metallic gearing.

The primary driving force in the use of plastic vs. metal gears is the large economic advantage afforded by the injection moulding process. In addition, cams, bearings, ratchets, springs, gear shafts and other gears can be designed as integral parts in a single moulding, thus eliminating costly manufacturing and assembly operations. Tolerances for plastic gears are in some cases less critical than for metal gears because the inherent resiliency enables the teeth to conform to slight errors in pitch and profile. This same resilience offers the ability to dampen shock or impact loads. The use of ZYTEL® nylon resin as the tooth surface in engine timing chain sprockets is an outstanding example of this latter advantage. In this case, timing chain life is extended because nylon dampens somewhat the transmission of shock loads from fuel ignition. ZYTEL® nylon resin and DELTRIN® acetal resin have low coefficients of friction and good wear characteristics, offering the ability to operate with little or no lubrication. They can also operate in environments that would be adverse to metal gears. A summary of the advantages and limitations of plastic gears is given in Table 8.01.

Knowledge of the material performance characteristics and use of the gear design information to follow is important to successful gear applications in DELTRIN® acetal resin and ZYTEL® nylon resin.

Gear Design

The key step in gear design is the determination of the allowable tooth bending stress. Prototyping of gears is expensive and time consuming, so an error in the initial choice of the tooth bending stress can be costly.

For any given material, the allowable stress is dependent on a number of factors, including:

- Total lifetime cycle.
- Intermittent or continuous duty.
- Environment – temperature, humidity, solvents, chemicals, etc.
- Change in diameter and centre to centre distance with temperature and humidity.
- Pitch line velocity.
- Diametral pitch (size of teeth) and tooth form.
- Accuracy of tooth form, helix angle, pitch diameter, etc.
- Mating gear material including surface finish and hardness.
- Type of lubrication (frictional heat).

Selection of the proper stress level can best be made based on experience with successful gear applications of a similar nature. Fig. 8.01 plots a number of successful gear applications of DELTRIN® acetal resin and ZYTEL® nylon resin in terms of peripheral speed and tooth bending stress. Note that all of these applications are in room temperature, indoor environments. For similar applications operating at higher temperatures, the allowable stress should be corrected, see factor C_1 in Table 8.02. Since fatigue endurance is reduced somewhat as temperature increases, this effect must also be considered. Where very high temperatures are encountered, thermal ageing may become a factor.

Where suitable experience is not available, the allowable tooth stress must be based on careful consideration of all the factors previously outlined, and on available test data on the gear material of choice.

Table 8.01 Advantages and Limitations of Plastic Gears

Advantages	Limitations
Economy in injection moulding	Load carrying capacity
Combining of functions	Environmental temperature
No post-machining or burr removal	Higher thermal expansion coefficient
Weight reduction	Less dimensional stability
Operate with little or no lubrication	Accuracy of manufacture
Shock and Vibration damping	
Lower noise level	
Corrosion resistance	

A number of years ago, DuPont commissioned a series of extensive gear tests on gears of DELRIN® acetal resin and ZYTEL® nylon resin, which resulted in the information summarised in Tables 8.02 and 8.03. This data can be combined with environmental operating conditions to arrive at an allowable tooth bending stress.

Whether similar experience exists or not, it is essential that a prototype be built and the design carefully tested in the actual or simulated end-use conditions.

Table 8.02 Allowed Fatigue Strength for DELRIN® and ZYTEL® 101

$$\sigma_n = \sigma_1 [1 - C_n \log(n)] \text{ (MPa)}$$

where: σ_1 = fatigue strength for 10^6 cycles, see Table 8.03

$$C_n = 0,20 \text{ for ZYTEL® 101; } = 0,22 \text{ for DELRIN®}$$

n = number of cycles in million
(industrial purposes: $n \geq 1000$)

$$\sigma_{all} = c_1 c_2 c_3 \sigma_n \text{ (MPa)}$$

where: $c_1 = 1 - 0,6 (T - 20) / 80$

T = temperature in °C

c_2 = factor for shock-load

no shocks: $c_2 = 1,0$

heavy shocks: $c_2 = 0,5$

c_3 = factor for velocity = $1 / (1 + v)$

v = peripheral velocity; ≤ 5 (m/s)

$$v = \pi d \omega / 60000 \text{ (m/s)}$$

d = pitch diameter (mm)

ω = rotational speed (rpm)

Table 8.03 Fatigue Strength (σ_1) for DuPont gear materials for 10^6 cycles (MPa)

Material	Mating Material	Lubrication	
		Continuous	Initial
DELRIN® 100	Steel	48	27
DELRIN® 500	Steel	36	18
ZYTEL® 101	Steel	40	25
ZYTEL® 101	ZYTEL® 101		18

Once the admissible tooth bending stress has been determined, the designer can proceed with the selection of the other variables, for which an understanding of the basic terminology used in gear work is helpful. The terms most commonly used to describe gears are:

- *Pitch diameter* (d) is the diameter measured at the pitch circle.
- *Diametral pitch* (P_d) is the number of teeth per inch of pitch diameter, commonly used in USA.
- *Module* (M) is pitch diameter divided by number of teeth (z). Thus: $M = d/z$.

For standard gears:

- external diameter = $d + 2M$;
- tooth thickness = $0,5 \pi M$;
- tooth height = $2M + \text{clearance}$.
- *Pinion* is the smaller of a pair of meshing gears.
- *Gear* is the larger of a pair of meshing gears.
- *Ratio* is number of teeth gear/number of teeth pinion.

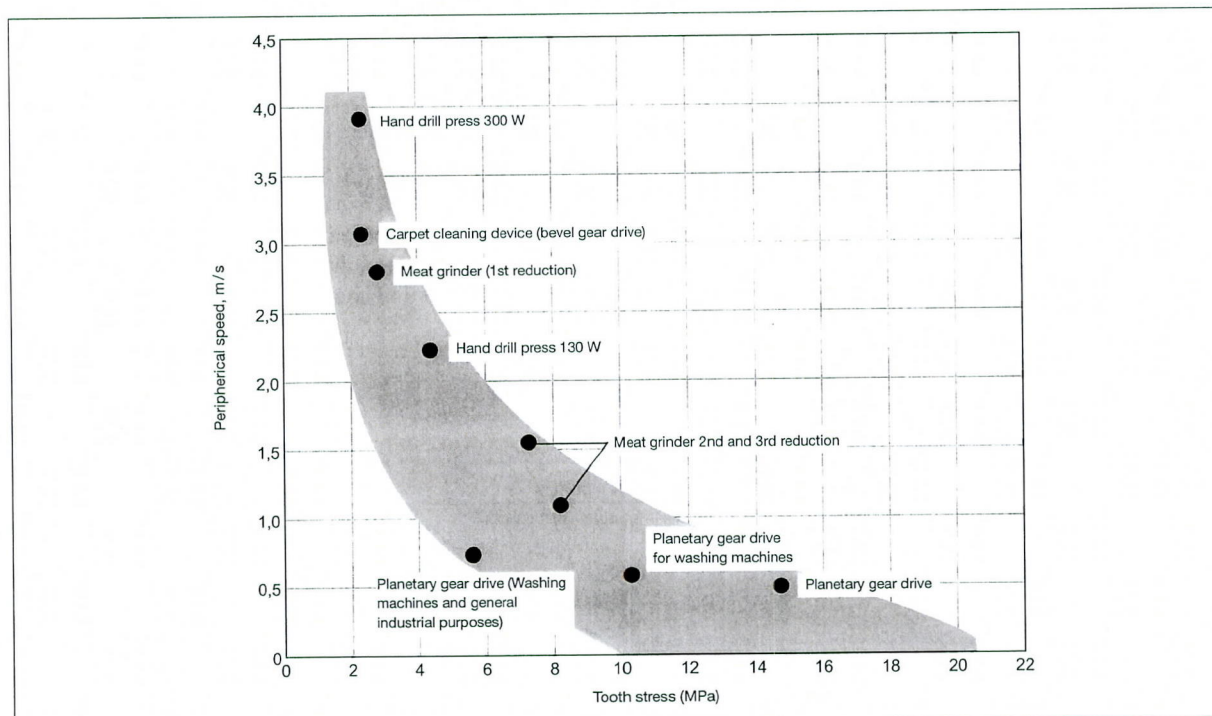


Fig. 8.01 Speed versus stress: Typical gear applications placed on curve

In a set of gears a torque is transferred by means of a peripheral force at the pitch diameter, with the following relation, (see also Fig 8.02):

$$F = 2000 T / d$$

F = peripheral (tangential) force	(N)
T = torque, $T = 9550 P/\omega$	(N·m)
d = pitch diameter	(mm)
P = transmitted power	(kW)
ω = rotational speed	(rpm)

In case both gear and pinion have a larger number of teeth, it is probable that multiple teeth are in contact while running. For smooth running, with as little production of vibration (noise) as possible, the number of teeth in contact should be independent of the rotation angle, and the take-over of the peripheral force by new sets of teeth in contact should also be smooth, for which reason gears are often made slightly helical.

For one set of (standard shaped) teeth in contact the following formula has been derived for the bending stress in the teeth of a spur gear:

$$\sigma = F / (y M f) \quad (\text{MPa})$$

y = tooth form factor, $y = 0,25 z^{0,25}$
 f = tooth width (mm)
 z = number of teeth

The computed bending stress should always be lower than the allowable bending stress according Table 8.02.

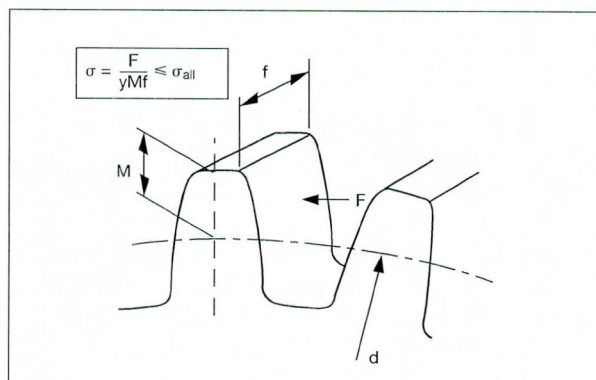


Fig. 8.02 Gear design

From a strictly functional and technical point of view, there is no reason to choose a larger tooth size than required. In the case of plastic gear design, the tooth size is often chosen smaller than necessary for the following reasons:

- Smaller teeth, for a given diameter, tend to spread the load over a larger number of teeth.
- Less critical moulding tolerances.
- Less sensitivity to thermal variations, post moulding shrinkage, and dimensional stability.
- Coarse module teeth are limited by higher sliding velocities and contact pressures

Designing for Stall Torque

There are many applications where the gear must be designed to withstand stall torque loading significantly higher than the normal running torque, and in some cases this stall torque may govern the gear design. To determine the stall torque a given gear design is capable of handling, use the yield strength of the material at expected operating temperature under stall conditions. Only a small safety factor ($S = 1,3 - 1,5$) needs to be applied if the material to be used is either ZYTEL® nylon resin or DELRIN® 100, as the resiliency of these materials allows the stall load to be distributed over several teeth.

Some applications, like window lift gears for cars, use a steel worm and a plastic helical gear (= worm gear), where the tooth thickness of the steel worm has been reduced in favour of the tooth thickness of the plastic gear. In this case the gear strength may be limited by the shear strength of the loaded teeth, as given by the equation:

$$F_{\max} = n f t \tau \quad (\text{N})$$

n = number of teeth in (full) contact
 f = tooth width (mm)
 t = tooth thickness (mm)
 τ = shear strength = $\sigma_y / (1,7 S)$ (MPa)
 σ_y = yield strength at design temperature (MPa)

Again, adequate testing of the moulded prototype is necessary.

Gear Proportions

Once the basic gear design parameters have been established, the gear design can be completed. It is very important at this stage to select gear proportions which will facilitate accurate mouldings with minimum tendency for post moulding warpage or stress relief.

An ideal design as far as moulding is concerned is shown in Fig. 8.03. For reasons of mechanical strength, it is suggested that the rim section be made 2 times tooth thickness "t".

The other sections depend both on functional requirements and gate location. If, for some reason, it is desirable to have a hub section "h" heavier than the web, then the part must be centre gated in order to fill all sections properly, and the web "w" would be 1,5 t. If the gate must be located

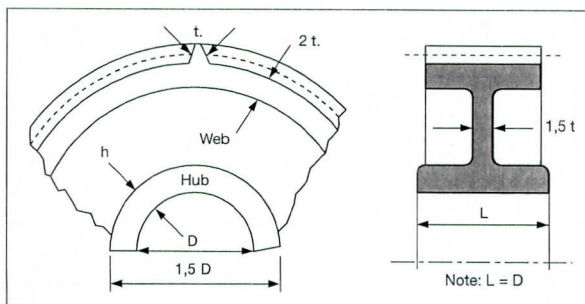


Fig. 8.03 Suggested gear proportions

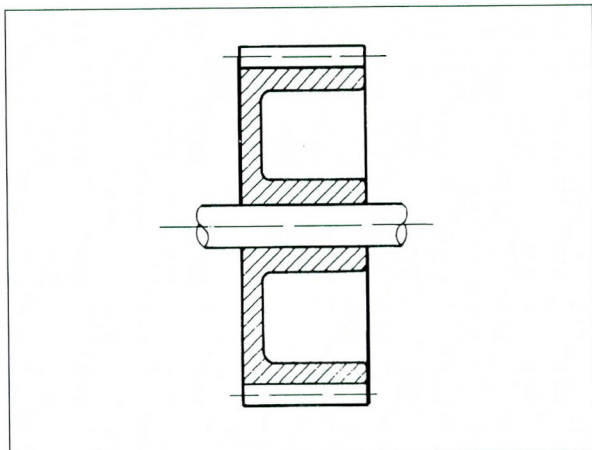


Fig. 8.04 Gear with off-centre web

in the rim or the web, then web thickness should equal hub thickness, as no section of a given thickness can be filled properly through a thinner one.

The maximum wall thickness of the hub should usually not exceed 6 mm. For minimum out-of-roundness, use centre gating.

On gears which are an integral part of a multifunctional component or which have to fulfill special requirements as shown in Fig. 8.20-8.25, it could be impossible to approach the ideal symmetrical shape as shown in Fig. 8.03, in which case the assembly must be designed to accept somewhat less accuracy in the gear dimensions.

The following additional examples illustrate a few more gear geometries which could lead to moulding and/or functional problems:

- Relatively wide gears which have the web on one side will be rather difficult to mould perfectly cylindrical, especially if the centre core is not properly temperature controlled. If the end use temperature is elevated, the pitch diameter furthest from the web will tend to be smaller than the pitch diameter at the web (Fig. 8.04).

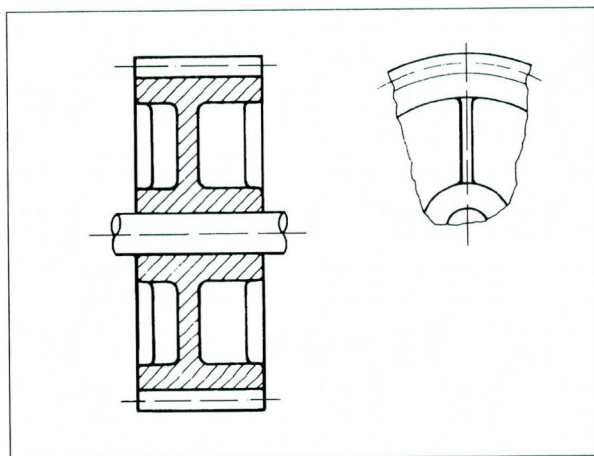


Fig. 8.05 Effect of radial ribs

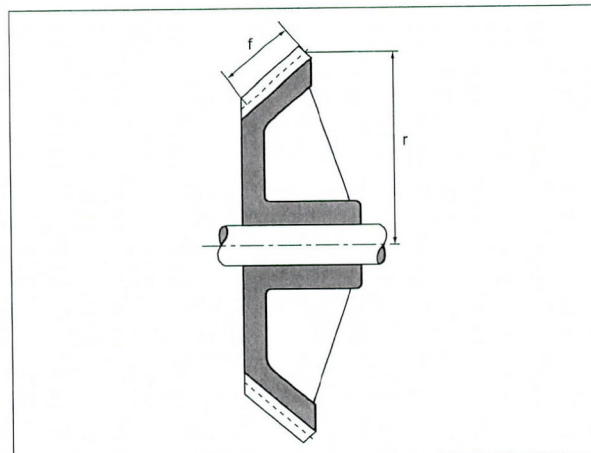


Fig. 8.06 Ribbed bevel gear

- Radial ribs which support the rim often reduce accuracy and should be provided only when strictly required due to heavy axial load. Helical gears are often designed this way, even when the resulting axial load is negligible (Fig. 8.05).
- On heavily loaded large bevel gears, thrust load on the tooth crown may become considerable and ribs cannot always be avoided. The basic principles for good rib design apply (Fig. 8.06).
- The same is valid for worm gear drives where the stall torque may produce severe thrust load requiring axial support.

For instance, it has been found on windshield wiper gears that ribbing may be necessary to prevent the worm gear from deflecting away from the worm under stall conditions (Fig. 8.07).

- It must also be understood that any large opening in the web, especially if located close to the teeth, will show up on a gear measuring device and may cause noise or accelerated wear on fast running gears (Fig. 8.08).

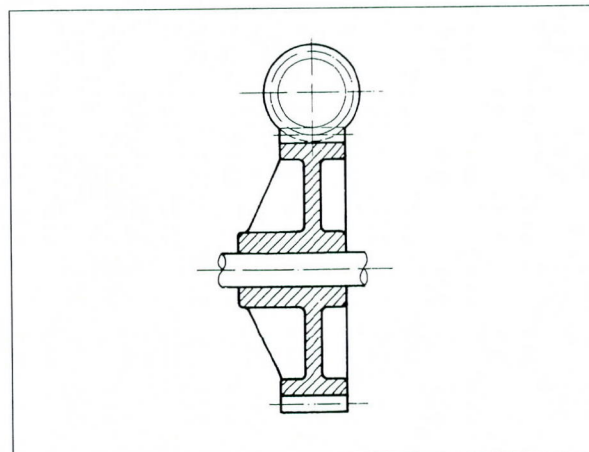


Fig. 8.07 Ribbed worm take-off gear

- Fig. 8.09 and 8.10 demonstrate how design and gating sometimes can determine whether a gear fails or performs satisfactorily. Both are almost identical windshield wiper gears moulded onto knurled shafts. The gear on Fig. 8.09 is centre gated and does not create a problem.
- The gear shown in Fig. 8.10 is filled through 3 pin-point gates in the web. In addition, the three holes provided for attaching a metal disc are placed close to the hub. As a result, the thicker hub section is poorly filled and the three weld lines create weak spots, unable to withstand the stresses created by the metal insert and the sharp edges of the knurled surface.

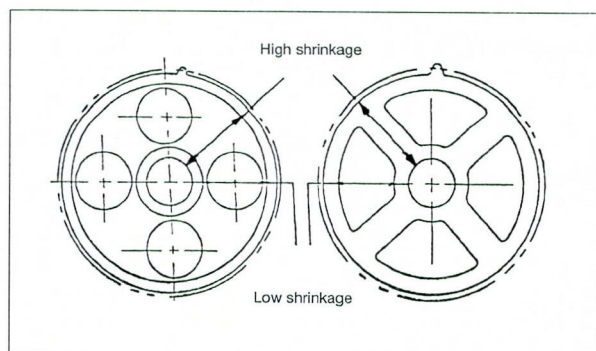


Fig. 8.08 Holes and ribs in moulded gears

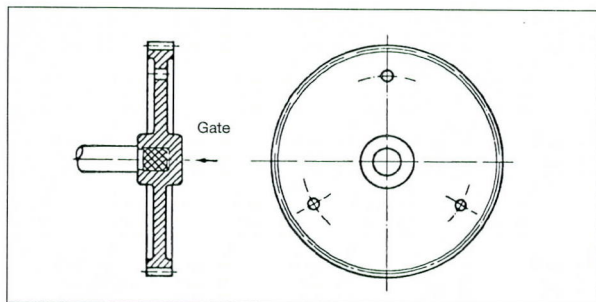


Fig. 8.09 Centre gated gear

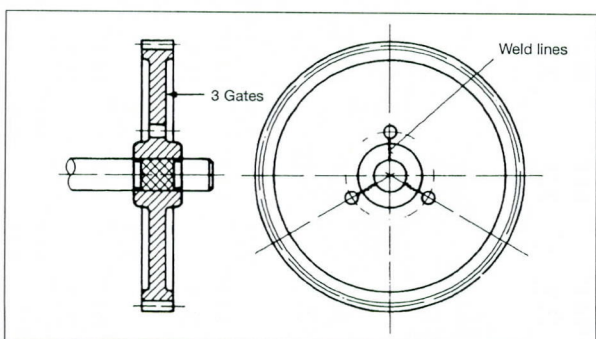


Fig. 8.10 Web gated gear

Accuracy and Tolerance Limits

As discussed previously, plastic gears, because of their resilience, can operate with broader tolerances than metal gears. This statement should not be taken too generally. Inaccurate tooth profiles, out-of-roundness and poor tooth surfaces on plastic gears may well account for noise, excessive wear and premature failure. On the other hand, it is useless to prescribe tolerances which are not really necessary or impossible to achieve on a high production basis.

The main problem in producing accurate gears in plastic is, of course, mould shrinkage. The cavity must be cut to allow not only for diametral shrinkage but also the effect of shrinkage on tooth profile on precision gears, this fact must be taken into account, requiring a skillful and experienced tool maker.

With the cavity made correctly to compensate for shrinkage, moulding conditions must be controlled to maintain accuracy. The total deviation from the theoretical tooth profile can be measured by special equipment such as used in the watch industry. An exaggerated tooth profile is shown in Fig. 8.11-a. It includes the measurement of surface marks from the cavity as well as irregularities caused by poor moulding conditions.

In practice, the most commonly used method for checking gear accuracy is a center distance measuring device as shown in Fig. 8.11-b.

The plastic gear meshes with a high precision metal master gear, producing a diagram of the center distance variations as shown in Fig. 8.11-c.

This diagram enables the designer to evaluate the accuracy of the gear and to classify it according to AGMA or DIN specifications.

AGMA specifications No. 390.03 classifies gears into 16 categories, of which class 16 has the highest precision and class 1 the lowest. Moulded gears usually lie between classes 6 and 10 where class 10 requires superior tool making and processing.

Similarly, DIN specification No. 3967 classifies gears into 12 categories, of which class 1 is the most precise and class 2 the least. Moulded gears range between classes 8 and 11 in the DIN categories.

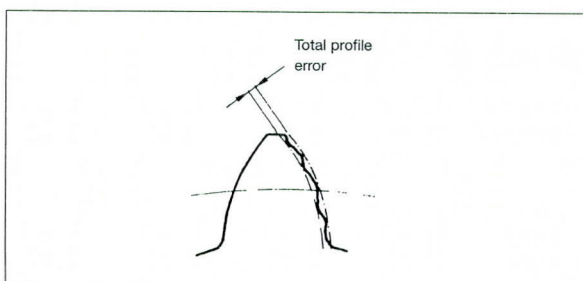


Fig. 8.11-a Measurement of tooth profile error

The total error as indicated in Fig. 8.11-c may be due in part to an inaccurate cavity, inadequate part gating or poor processing.

If several curves of a production run are superimposed, as in Fig. 8.11-d, the distance "T" between the highest and the lowest indicates the moulding tolerances.

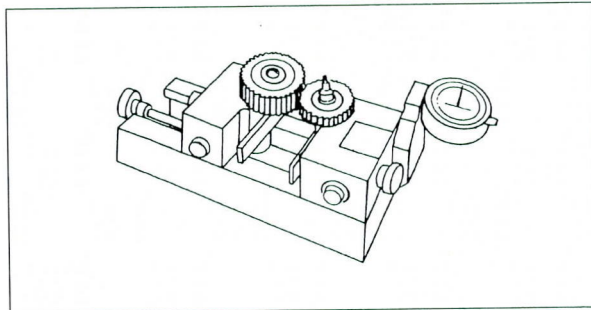


Fig. 8.11-b Center distance measuring instrument

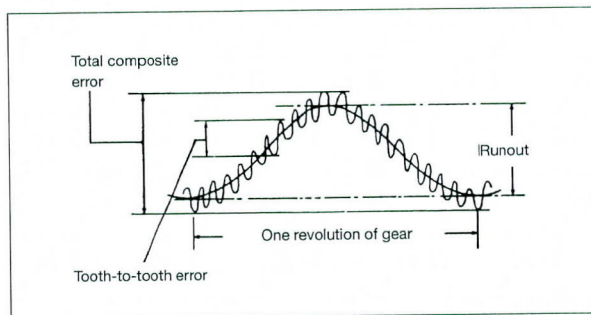


Fig. 8.11-c Center distance variation diagram

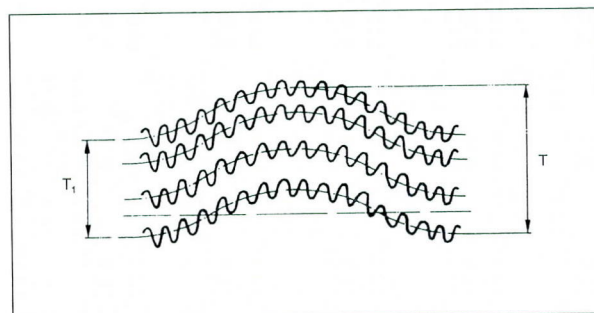


Fig. 8.11-d Moulding tolerances from center distance diagram

Backlash and Centre Distances

As shown in Fig. 8.11-e backlash is the tangential clearance between two meshing teeth. Fig. 8.12 provides a suggested range of backlash for a first approach.

It is essential to measure and adjust the correct backlash at operating temperature and under real working conditions. Many gears, even though correctly designed and moulded fail as a result of incorrect backlash at operating conditions.

In particular, the designer must be aware that backlash may be adequate after a device is assembled, but may change in time and under working conditions due to the following reasons:

- Thermal variations.
- Post moulding shrinkage.

If the gear box is moulded in a plastic material as well, the same considerations apply. Centre distance may vary and influence backlash, thus the dimensional stability characteristics of the housing material must be considered.

Increased backlash causes the gears to mesh outside the pitch diameter resulting in higher wear. Insufficient backlash may reduce service life or even cause seizing and rapid part destruction.

It is often easier to determine centre distance after having produced and measured the gears. It must be kept in mind that this procedure may produce more wear as the gears may no longer mesh exactly on the theoretical pitch circle.

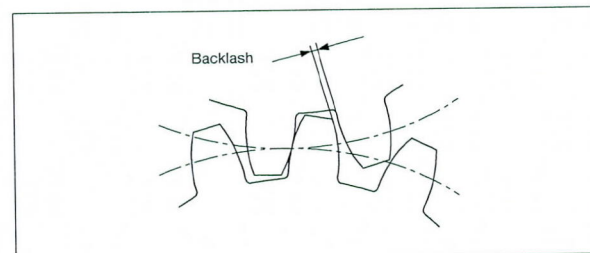


Fig. 8.11-e Measurement of backlash

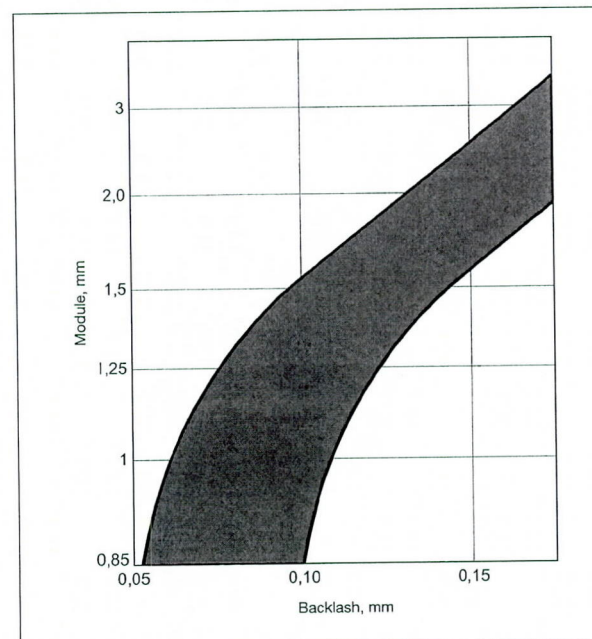


Fig. 8.12 Suggested backlash for gears of DELRIN® and ZYTEL®

Mating Material

The coefficient of friction and wear factor of DELRIN® acetal resin on DELRIN® acetal resin are not as good as DELRIN® acetal resin on hardened steel, see Table 7.01. Even so, a great number of commercial applications have entire gear trains made of DELRIN® acetal resin (especially appliances and small precision speed reducers for clocks, timers, and other mechanical devices).

- If two meshing gears are moulded in DELRIN® acetal resin, it does not improve wear to use different grades, as for instance, DELRIN® 100 and DELRIN® 900F or DELRIN® 500CL.
- In many cases wear can, however, be significantly improved by running DELRIN® acetal resin against ZYTEL® nylon resin. This combination is especially effective where long service life is expected, and shows considerable advantage when initial lubrication cannot be tolerated.
- In all cases, where two plastic gears run together, allowances must be made for heat dissipation. Heat dissipation depends on the overall design and requires special consideration when both materials are good thermal insulators.
- If plastic gears run against metals, heat dissipation is much better, and consequently a higher load can be transmitted. Very often, the first pinion of a gear train is cut directly into the fast running motor shaft. Heat transmitted through the shaft from the bearings and electric coils can raise the gear teeth temperature above that which might be expected. The designer should pay particular attention to adequate motor cooling.
- Gear combinations of plastic and metal may perform better and show less wear than plastic on plastic. This is, however, only true if the metal gear has a hardened surface.

Table 8.04 Suggested mating material choice for spur gears of DELRIN® acetal resin

Driving Gear	Meshing Gear	
DELRIN® 500	DELRIN® 500	General purposes, reasonable loads, speed and service life, such as clock and counter mechanisms.
DELRIN® 100	DELRIN® 100	Applications requiring high load, fatigue and impact resistance, such as: hand drill presses, some appliances, windshield wiper gears, washing machine drives (esp. reversing). Gears combined with ratchets, springs or couplings.
DELRIN® 500 soft metals	DELRIN® AF	Small mechanism gear drives requiring non slip-stick behaviour and less power loss (e.g., measuring instruments, miniaturized motor speed reducers). This combination does not necessarily give better performance as far as wear is concerned.
Hardened Steel (surface hardness approx 50 Rc)	DELRIN® 100	Excellent for high speed and load, long service life and low wear. Especially when used for the first reduction stage of fast running motors where the pinion is machined into the motor shaft (e.g., appliances, drill presses and other electric hand tools).
Soft steel, non-ferrous metals	DELRIN® 500CL	Combined with soft metals, DELRIN® 500CL gives considerably better results in wear than all other grades. In addition, it has little effect on the metal surfaces. Recommended for moderate load but long service life (e.g., high quality precision gear mechanisms).

Table 8.05 Suggested mating material choice for gears of ZYTEL® nylon resin

Driving Gear	Meshing Gear	
ZYTEL® 101L	ZYTEL® 101L	Very common usage in light to moderate load applications.
Hardened Steel	ZYTEL® 101L	Recommended for high speed, high load applications. Best sound and shock absorption. Longest wearing.
ZYTEL® 101L	DELRIN® 100, 500 and 900	Lowest friction and wear compared to either material running against steel 500, 900 or against itself. Highly recommended for moderate duty. Best where no lube is permissible. Either material can be the driver, however, the better dimensional stability of DELRIN® acetal resin makes it the logical choice for the larger gear.

Lubrication

Experience has shown that initial lubrication is effective for a limited time. Units disassembled after completion of their service life showed that all the grease was thrown on the housing walls; hence the gears ran completely dry. Initial lubrication does not allow a high load, it should be considered as an additional safety factor. *It should, however, always be provided as it helps greatly during the run-in period.*

On applications where lubricant cannot be tolerated, the combination of DELRIN® acetal resin and ZYTEL® nylon resin offers great advantages. Even under dry conditions such gear trains run smoothly and with little noise.

Where continuous lubrication of gears in DELRIN® acetal resin and ZYTEL® nylon resin is practical, and where surface pressure on the meshing teeth is not excessive, wear is negligible and service life is determined exclusively by fatigue resistance.

Testing Machined Prototypes

Though it would appear that the easiest way to determine whether a proposed gear will show the expected performance would be to test machined prototypes, results thus obtained must be interpreted with great care. A designer has no guarantee that a subsequently moulded gear will have the same performance characteristics. Therefore no final conclusion can be drawn from test results using machined gears. Making a trial mould is the only safe way to prototype a gear design. It allows not only meaningful tests but also the measurement of shrinkage, tooth profile, pitch diameter and overall accuracy.

It is highly recommended to check tooth quality on a profile projector which enables detection of deviation from the theoretical curve.

Prototype Testing

The importance of adequate testing of injection moulded prototype gears has been emphasized. Here are some guidelines:

- Accelerated tests at speeds higher than required of a given application are of no value.
- Increasing temperature above normal working temperature may cause rapid failure whereas under normal working conditions the gear may perform well. Test conditions should always be chosen to come as close as possible to the real running conditions.

The following examples further explain the need for meaningful end-use testing.

- Gears under a high load (e.g., in appliances) which operate only intermittently should not be tested in a continuous run, but in cycles which allow the whole device to cool down to room temperature between running periods.
- Infrequently operated, slow-running gears (such as window blinds) can be tested in a continuous run but at the same speed, providing temperature increase on the tooth surfaces remains negligible.
- Other applications like windshield wiper gears reach their maximum working temperature quickly, and operate most of their service life under these conditions. They should therefore be tested on a continuous-run base.

Valuable conclusions can often be drawn from the static torque at which a moulded gear fails. If breaking torque proves to be 8-10 times the operating load, it can usually be taken as an indication that the gear will provide a long service life in use. However, plastic gears often operate very close to the endurance limit, and the above relation should not be considered as valid in all cases.

In any event, backlash must be checked during all tests. Once a gear has failed, it is almost impossible to determine whether incorrect backlash was partially or entirely responsible.

Helical Gear Design

Whenever possible, helical gears should be used in preference to spur gears. Among other advantages they run more smoothly and have less tendency to squeak.

However, they require not only perfect tooth profiles but also exactly matching helix angles. This requirement is sometimes difficult to fulfill, especially if the plastic gear meshes with a metal gear.

Helical gears generate axial thrust which must be considered. It is advisable to use helix angles not greater than 15°. Compared to a spur gear having the same tooth size, a helical gear has slightly improved tooth strength. Since small helix angles are most commonly used, this fact can be neglected when determining the module and it should be considered as an additional safety factor only.

Worm Gear Design

Most machined worm gears are provided with a throated shape which provides a contact line of a certain length on the worm. Because this system cannot easily be applied on moulded plastic gears, a simple helical gear is normally used. Consequently, the load is transmitted on contact points which increases surface pressure, temperature and wear.

Various attempts have been made, aimed at improving wear and increasing power transmission, to change the contact points to contact lines. The following examples of practical applications demonstrate some possibilities along this line.

Fig. 8.13 shows a one-piece moulded worm gear in DELRIN® 100 meshing with a worm in ZYTEL® 101L for a hand-operated device. The undercut resulting from the throated shape amounts to about 4% and can therefore be ejected from the mould without problems. This principle of moulding and ejecting a one-piece worm gear is used in quite a number of applications even though it requires experience and skilled tool making. It is interesting to note that this particular worm with 7 leads cannot be moulded in a two-plate mould with the parting line on the centre.

The lead angle of 31° being greater than the pressure angle (20°), results in an undercut along the parting line. Therefore, the worm must be unscrewed from the mould.

Fig. 8.14 shows a windshield wiper gear produced in a different way. Because of the undercut of about 7% and the rigid structure, ejecting becomes impossible. The tool is therefore provided with 9 radial cores, each of which covers 6 teeth. This procedure produces an excellent worm gear but is limited to single cavity tools. Tooling cost is of course higher.

The worm gear in Fig. 8.15 is again for a windshield wiper drive and based on an intermediate solution. It is composed of a half-throated and a helical gear portion.

The tooth contact takes place on the curved section whereas the helical part merely improves the tooth strength and therefore the stall torque. Even though this solution is not ideal, it nevertheless offers a significant advantage over a simple helical worm gear.

A full throated worm gear is shown in Fig. 8.16 in the shape of a split worm gear. The two halves are designed in such a way that components in the same cavity can be fitted together, centered and the teeth perfectly aligned by means of lugs fitting into corresponding holes (see also Fig. 8.17). Thus, a single cavity provides a complete gear assembly which is held together by means of snap-fits, ultrasonic welding or rivets. As required by production, multi cavities can be added later. The gears can be made as wide as necessary limited only by proper meshing.

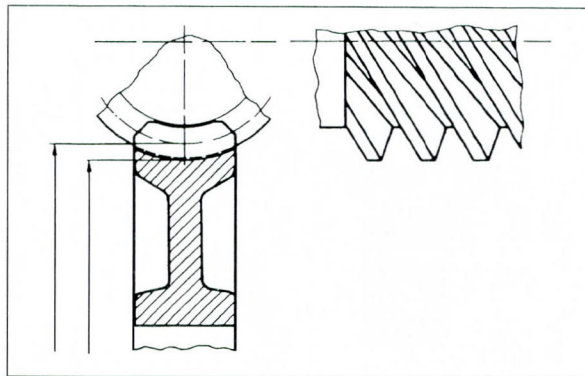


Fig. 8.13 One piece worm gear

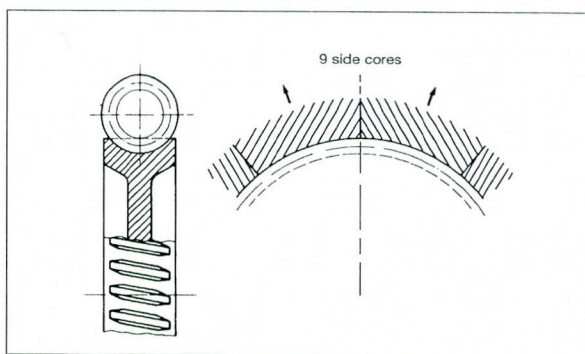


Fig. 8.14 Side-cored worm gear

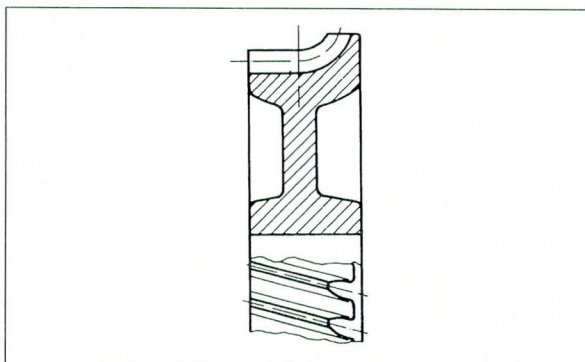


Fig. 8.15 Half throated worm gear

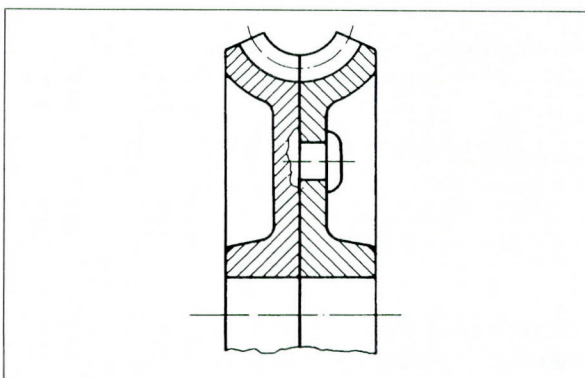


Fig. 8.16 Split worm gear

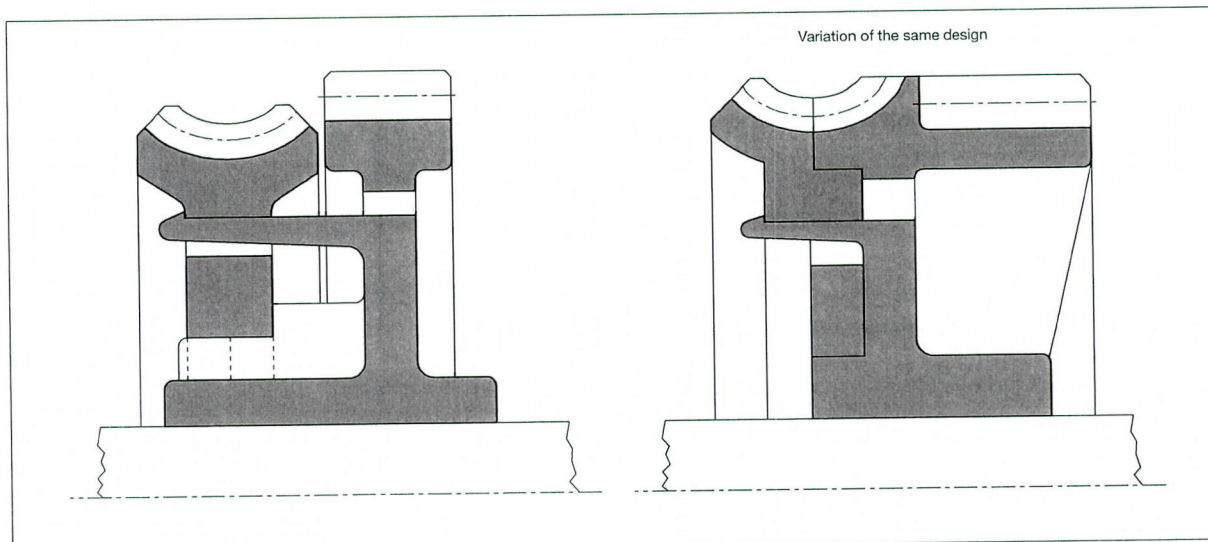


Fig. 8.17 Snap-fit split worm gear

This design comes closest to the classic machined metal full throated worm gear, and tooling costs are no higher than for the gear shown in Fig. 8.15. Split worm gears are especially recommended for larger worm diameters, where performance is improved considerably.

The advantage of throated over helical worm gears stems primarily from the load being spread over a larger area of the tooth, resulting in lower localized temperature and reduced bending stress. Tests with the split worm gear show it to be superior to a helical worm gear by a factor of 2-4.

An example of a snap-fit helical gear is shown in Fig. 8.17.

Certain limitations should be kept in mind in the design of these throated worm take-off gears when compared to simple helical gears, as follows:

- Higher tooling cost.
- Requirement of perfect centering of worm and worm gear. Even small displacements cause the load to be carried by only a portion of the tooth width, resulting in increased wear or rapid failure.
- The worm gear drive is more sensitive to discrepancies of the lead angles which must match perfectly.
- The worm and the gear must be assembled in a certain way. If for instance the worm is mounted first into the housing a throated gear can be introduced only in a radial direction, whereas a simple helical gear (or a gear as shown in Fig. 8.13) can be mounted sidewise.

Worm gear drives allow high speed reductions with only two elements. Consequently, they often are used in connection with fast running motors, with the worm cut directly or rolled into the metal shaft.

Since the requirements are quite different in various applications, the performance and limitations of worm gears in DELRIN® acetal resin and ZYTEL® nylon resin will depend upon the specific application.

For instance, a windshield wiper gear may run repeatedly for a considerable length of time and at high temperature. It can, in addition, be submitted to severe stalling torques if the windshield wiper blades are frozen. Since this happens at low temperatures, the gear diameter is smaller due to thermal contraction, causing the teeth to be loaded closer to the tip and thus increasing stress. Often it is this condition which controls the gear design.

On the contrary, an electric car window drive works under normal conditions only a few seconds at a time, with long intervals. Consequently, where is no time for a temperature rise and the gear can thus withstand higher loads. Since the total service life, compared to a wind-shield wiper, is very short, wear is rarely a problem. Many of these power window mechanisms will lock up substantial torque with the window closed. The gear must be strong enough that creep does not cause significant tooth distortion, particularly under closed car summer conditions.

In appliances, requirements are again quite different. The working time is usually indicated on the device and strictly limited to a few minutes at a time. This allows the use of smaller motors which are overloaded, heating up very fast and transmitting temperatures to the shaft and the worm. If the appliance is used as prescribed, temperature may not exceed a reasonable limit. If, however, the devices are used longer or at frequent intervals, temperature can reach a level at which high wear and premature failure can occur.

These examples demonstrate the necessity of carefully defining the expected working conditions, and of designing and dimensioning the worm and gear accordingly.

In addition to the limitations mentioned previously, other factors to be carefully considered are:

- Metal worms cut directly into motor shafts usually have very small diameters. Unless supported at both ends, overload and stalling torques cause them to bend, and lead to poor meshing.
- Under the same conditions, insufficiently supported plastic worm gears are deflected axially, with the same results.
- In cases where worms are cut into small-diameter motor shafts, tooth size is considerably limited. Actually, many worm gear drives, especially on appliances, work only satisfactorily as long as the initial lubrication is efficient. With regard to the relatively short total operating lifetime, performance may nevertheless be acceptable.

Even though initial lubrication has limited efficiency in time, it is highly recommended for all worm gear drives, since friction is the main problem. Moreover, whenever possible, proper steps should be taken to keep the lubricant on the teeth. It is also advisable to choose a grease which becomes sufficiently liquid at working temperature to flow and thus flow back onto the teeth. In cases where severe stalling torques are applied on the gear, bending stresses and shear strength must be checked as well. As noted previously, load is concentrated on a very small area of helical take-off gears which causes uneven stress distribution across the width. Consequently, the tooth face f used for determining stall torque stresses should not be more than approximately two times the tooth size. For a metric module of 1, $f = 4$ mm.

It is advisable that bending stresses should not exceed approximately 30 MPa at room temperature (accounting for a safety factor of $S = 1,5$).

Some manufacture machine worm take-off gears from moulded blanks. If there is a valid reason for making gears this way, it is important that the tooth spaces be moulded in the blank in order to prevent voids in the rim section. Many plastic worm gears fail due to tiny voids in the highly stressed root area of the teeth because the rim was moulded solid. (The same is valid for other types of gears.)

The majority of worm gear applications use single threaded worms with helical worm gears. The teeth of the helical gear are weaker than the threads of the worm, thus output will be limited by the torque capacity of the gear.

A liberal safety factor (3-5) should be applied to take into account the stress concentration due to theoretical point contact as well as the high rubbing velocity. With ZYTEL® nylon resin as the worm and DELRIN® acetal resin as the gear, heat dissipation is limiting, as both materials are not good conductors of heat. Thus, it is recommended rubbing velocities be less than 0,125 m/s. With a steel worm, heat dissipation is markedly improved, and rubbing velocities as high as 1,25 m/s can be tolerated with initial lubrication. With continuous lubrication or intermittent operation, speeds as high as 2,5 m/s are possible.

The equation used to determine rubbing velocity is:

$$v = \frac{0,001 \pi d \omega}{60 \cos(\alpha)} \quad (\text{m/s})$$

d = worm pitch diameter (mm)

ω = worm speed (rpm)

α = lead angle (Fig. 8.18)

Table 8.06 Worm gear mating material

Worm Material	Gear Material	Possible Applications
Soft steel (machined DELRIN® 500CL or rolled)	DELRIN® 500CL	Excellent wear behaviour; can be considered for small devices (e.g. appliances, counter, small high quality mechanical speed reducers).
Soft steel and hardened steel	DELRIN® 100	Less wear resistant, improved fatigue and impact strength, for high stalling torques (e.g. windshield wipers, car window mechanisms, heavily loaded appliances like meat grinders where impact load must be expected). Worms in hardened steel give far better wear results.
Non ferrous metals (brass, zinc-alloys)	DELRIN® 500CL	DELRIN® 500CL has proven to give superior wear results compared to all other DELRIN® acetal resin grades even though heat build-up is not better. (Used in speedometers, counters and other small devices).
ZYTEL® 101L (66 Nylon resin)	DELRIN® 500 DELRIN® 100	Excellent for hand-operated or intermittent use, low speed devices (e.g. window blinds; car window mechanisms; continuously running, small-speed reducers where load is negligible, such as speedometers, counters). Very good dry-running behaviour.
DELRIN® 500	DELRIN® 500	Should be avoided on the basis of unfavourable wear behaviour and high coefficient of friction. It is nevertheless used in many small slow-running mechanism where load is extremely low.

Mating Material

Generally speaking, all worm gear speed reducers are inefficient due to high sliding velocity, which converts a large percentage of the power into heat. Therefore, it is important to choose mating materials which have low wear and friction. Along this line, a worm in ZYTEL® 101 running against a gear in DELRIN® acetal resin is a good combination. Because heat dissipation is poor, this combination is limited to light duty applications. The can opener shown in Fig. 8.18 is a good example of a commercial design using this combination of materials.

The motor speed of 4000 rpm is reduced in the first stage with a pinion and an internal gear before driving the worm in ZYTEL® 101. Working cycles are, however, so short that no significant heat build-up can take place.

Bevel Gear Design

The formula for the calculation of the bending stress in a spur gear has to be corrected to the following:

$$\sigma = \{r / (r-f)\} F / (y M f)$$

$$r = \text{pitch radius } (r = 0,5 d_{\text{max}}, \text{ see Fig. 8.06})$$

$$f = \text{tooth width}$$

With plastic materials, support of the rim is very important and supporting ribs are almost always necessary.

Fillet Radius

Most gear materials are not sensitive, including DELRIN® acetal resin and ZYTEL® nylon resin. Thus, the importance of proper fillet radius cannot be over emphasized. Standard fillets have proved satisfactory in most applications. It has been found that the use of a full rounded fillet will increase the operating life of gears of DELRIN® acetal resin approximately 20% under continuously lubricated conditions. Full rounded fillets may also prove advantageous where shock or high impact loads are encountered.

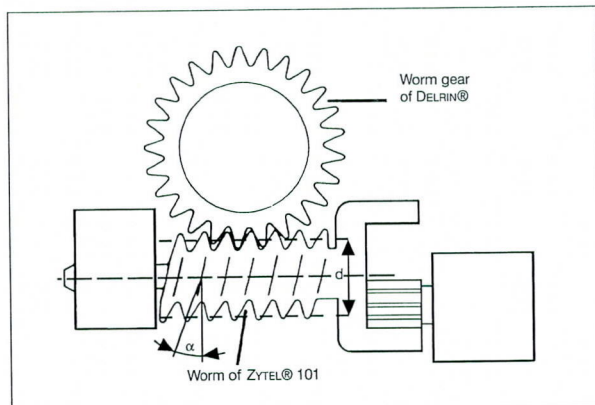


Fig. 8.18 Can opener with worm drive

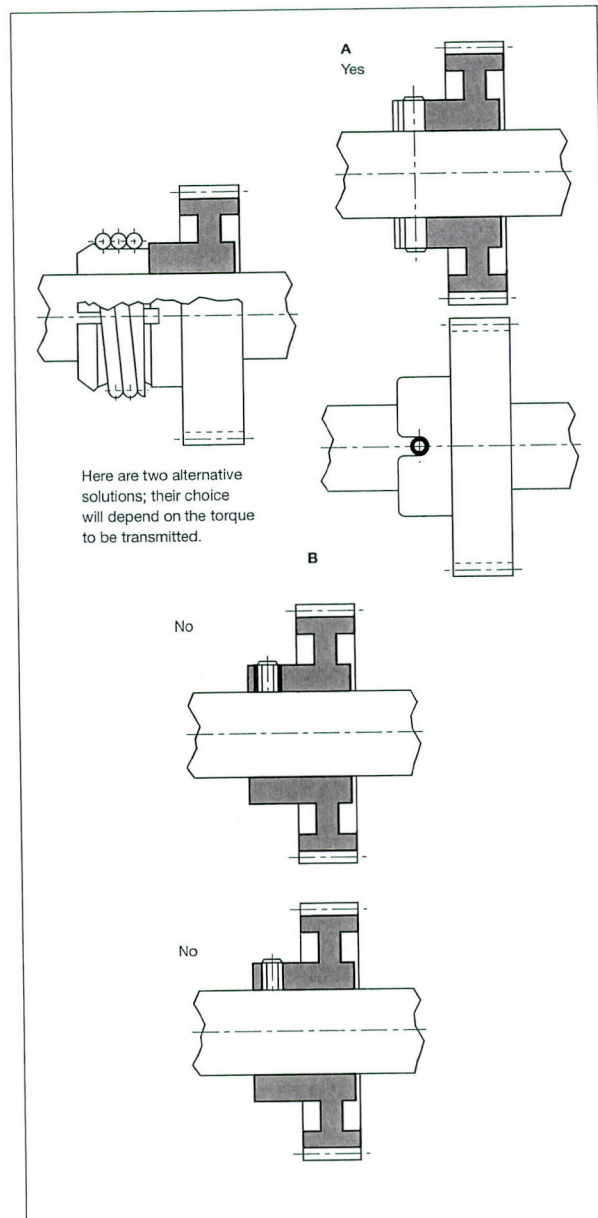


Fig. 8.19 Alternatives for grub screws

Methods of Fastening

The involute spline (Fig. 8.19 A) is by far the best method of fastening plastic gears to shafts.

Keys and set screws, although they have been used successfully, should be avoided as they require an unbalanced geometry in the hub. If set screws are used, they must bottom in a recess in the shaft. Interference fits can be used providing the torque requirements are low. Stress relaxation of the plastic material may result in slippage. Knurling the shaft can be helpful. Also grub screws (Fig. 8.19 B) should not be used to transmit even low torques. Plastic may break during assembly or creep in use.

The use of moulded-in inserts has been successful in gears of DELRIN® acetal resin and ZYTEL® nylon resin. The most common insert of this type is a knurled shaft.

Circumferential grooves in the knurled area can be used to prevent axial movement with helical, worm or bevel gears. Stamped and die cast metal inserts have also been used successfully. Engine timing sprockets mentioned previously use a die cast aluminium insert with incomplete teeth. ZYTEL® nylon resins is moulded over the insert to form the teeth. This is a good example of using the best properties of both materials to achieve a dimensionally stable, low cost, improved timing gear. Screw machine inserts have been used. It is important that materials with sufficiently high elongation be selected for use with moulded-in metal inserts so that the residual stress resulting from mould shrinkage will not result in stress cracking around the insert. Any of the ZYTEL® nylon resins are suitable in this regard. DELRIN® acetal resins have generally lower elongation than ZYTEL® nylon resins and have higher creep resistance, thus latent cracking can occur over moulded-in inserts with resins such as DELRIN® 500 and 900. However, DELRIN® 100ST has very high elongation and is recommended for use with moulded-in inserts. Inserts can be pressed or sonically inserted to reduce residual stress.

Stampings have been employed in the form of plates fastened to the web of the gear with screws or rivets, or by sonic staking.

With any fastening method, it is important to avoid stress risers. Fillets on the splines, inserts, etc., are extremely important.

Combined Functions – Design Examples

As mentioned previously, plastic gears offer large economic advantages over metal gears, and the greatest cost savings can come from combining an almost unlimited number of elements and functions in one single part.

Fig. 8.20–8.25 demonstrate a few design examples along this line:

- In this example (Fig. 8.20), a gear in DELRIN® acetal resin is provided with moulded-in springs acting on a ratchet wheel in ZYTEL® 101 nylon resin, which in turn is combined with another gear. There exist many various types of ratchets in DELRIN® acetal resin which function properly, providing the springs are not held in the loaded position for a long period of time.

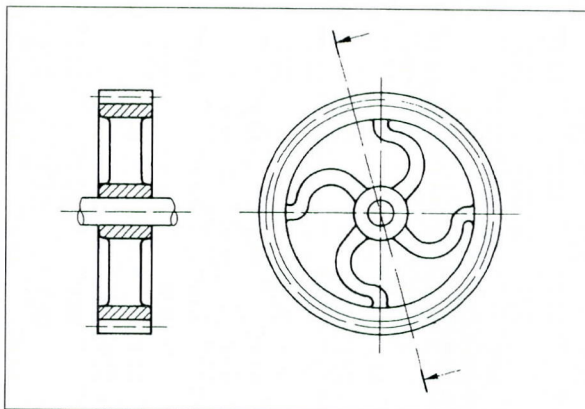


Fig. 8.21 Impact resistant web

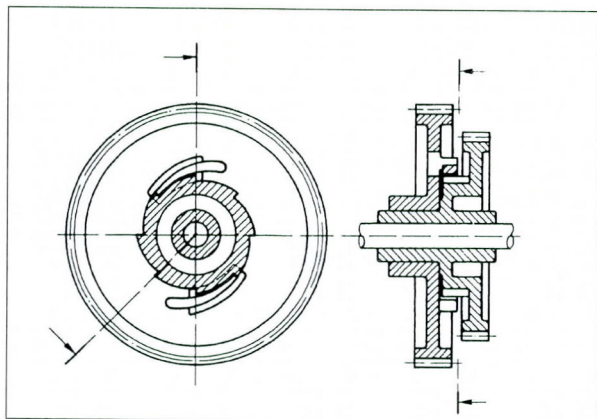


Fig. 8.20 Ratchet and gear combined

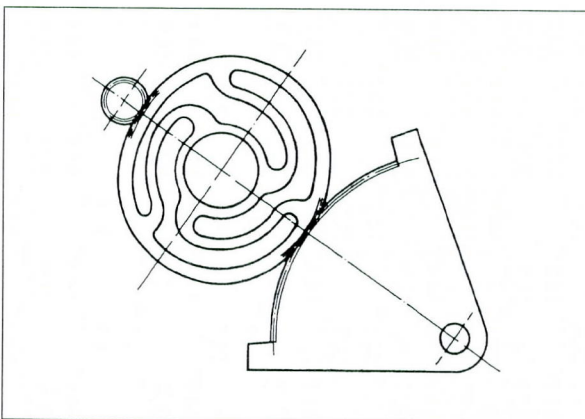


Fig. 8.22 Backlash-free gear

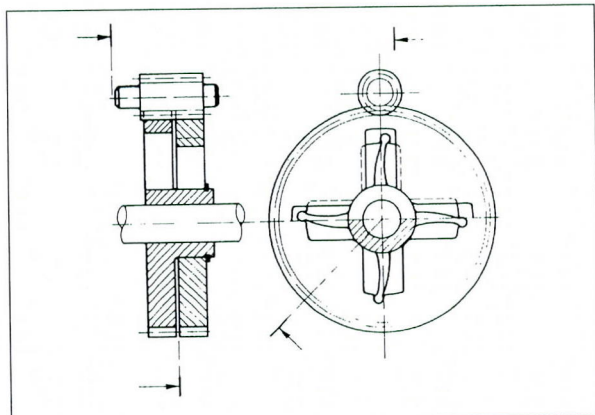


Fig. 8.23 Backlash-free gear

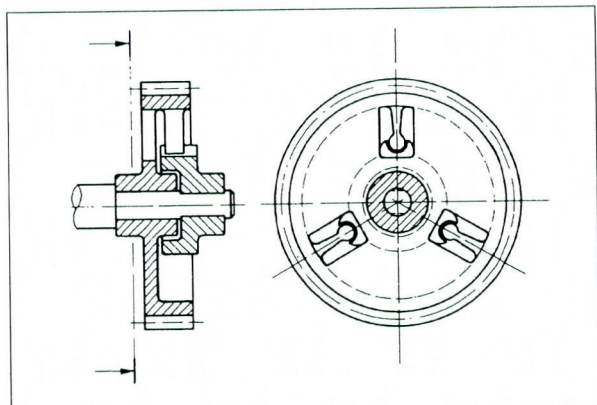


Fig. 8.24 Torque limiting gear

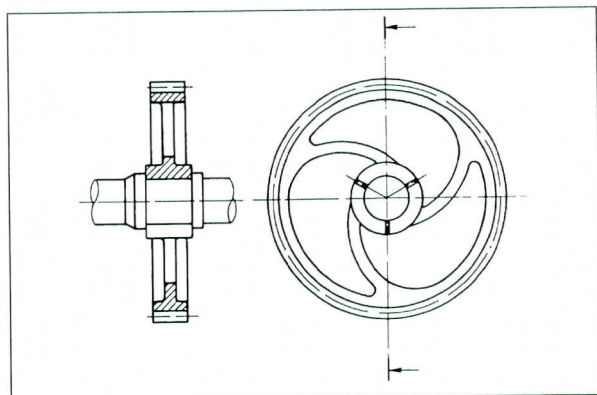


Fig. 8.25 Gear with sliding coupling

- In many cases, it is highly desirable to protect the teeth against impact load. This can be achieved, as is shown in Fig. 8.21, in connecting the hub and the rim by properly dimensioned flexible elements. Sometimes, this solution also is used on printing wheels in order to obtain consistent printing results without the need for precision tolerances.
- Fig. 8.22 is a backlash-free adjusting arrangement for an automobile clock. The motion is transmitted from the pinion to the segment by means of a flexible gear. When assembled, the gear is ovalized, thus applying a certain preload onto the pinion and the segment. As the transmitted torque is very small, stress relaxation does not jeopardize proper function. In addition, each time the mechanism is actuated, the oval gear moves into another position, thus increasing the preload and allowing the previously loaded section to recover. As an unusual additional feature, the segment is provided with two stops for limiting its movement. When a stop comes into contact with the gear, the pinion can be turned further without causing any damage to the system because the teeth slip over the flexing gear.
- Fig. 8.23 is another design suggestion for a backlash-free motion transmission between two gears. The main gear is equipped with moulded-in springs fitting into corresponding slots on the second gear. When assembled with the pinion, the two tooth crowns are slightly offset, causing the springs to be loaded and thus suppress any backlash. Here again, stress relaxation causes the force to decrease. The principle is adequate for only small torques such as those found on instrument dials or clock adjusting mechanisms.
- Torque limiting devices are quite often very useful for plastic gears in order to prevent tooth damage when overloading occurs (for instance on high torque transmissions like meat grinders, can-openers and hand drill presses). Fig. 8.24 shows one solution out of many other possible designs. It is essential that the springs do not remain accidentally in the loaded position. In the example shown, this is achieved by providing three pivoting springs.
- For specific requirements, it is also possible to combine gears with sliding couplings. The example shown in Fig. 8.25 is a gear in DELRIN® acetal resin snapped onto a shaft in ZYTEL® 101, in which the split hub acts as a coupling for a small dial setting device. If, as in this case, the required torque is very low, stress relaxation in the springs will not endanger perfect functioning for a sufficient length of service life. If, on the contrary, a constant torque must be transmitted for a long period of time, an additional metal spring around the hub would be required to keep the force constant.

When to use DELRIN® Acetal Resin or ZYTEL® Nylon Resin

ZYTEL® nylon resin and DELRIN® acetal resin are excellent gear materials, used extensively in a variety of applications. The choice of one over the other may at first seem unclear, but as one examines the specific requirements of the application, it becomes relatively easy. Although the two materials are similar in many ways, they have distinct property differences, and it is these differences upon which the selection is made. Some guidelines are as follows:

ZYTEL® Nylon Resin

- Highest end-use temperature
- Max. impact and shock absorption
- Insert moulding
- Max. abrasion resistance
- Better resistance to weak acids and bases
- Quieter running

DELRIN® Acetal Resin

- Best dimensional stability
- Integrally moulded springs
- Running against soft metals
- Low moisture absorption
- Best resistance to solvents
- Good stain resistance
- Stiffer and stronger in higher humidity environment

As previously pointed out, running DELRIN® acetal resin and ZYTEL® nylon resin against each other results in lower wear and friction than either material running against steel (not always true when high loads are encountered and heat dissipation is controlling). Some designers have used this combination in developing new, more efficient gear systems.

When properties of DELRIN® acetal resin are needed, DELRIN® 100 is the preferred gear material. As previously stated, DELRIN® 100 outperforms DELRIN® 500 by about 40%. DELRIN® 100 is the most viscous in the melt state, and cannot always be used in hard to fill moulds. DELRIN® 500 and 900 have been used successfully in many such cases.

When ZYTEL® nylon resin is the chosen material, ZYTEL® 101L is the most common material used. ZYTEL® 103HSL, a heat stabilized version of ZYTEL® 101L, should be specified if the service life and end use temperature are high.




Glass reinforced versions of either material should be avoided. The glass fibres are very abrasive and the wear rate of both the plastic gear and the mating gear will be high. Gears which operate for extremely short periods of time on an intermittent basis have been used with glass reinforcement to improve stiffness, strength or dimensional stability. Very careful testing is mandatory. The moulding conditions must be controlled carefully, not only for the usual purpose of maintaining gear accuracy, but also because glass reinforced resins will exhibit large differences in surface appearance with changes in moulding conditions, particularly mould temperature. It is possible to vary mould temperature without changing dimensions, by compensating through adjustments in other process variables. Thus, establish surface smoothness specifications to be sure the type of gear surface tested is reproduced in mass production.








DuPont Engineering Polymers

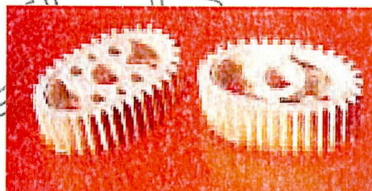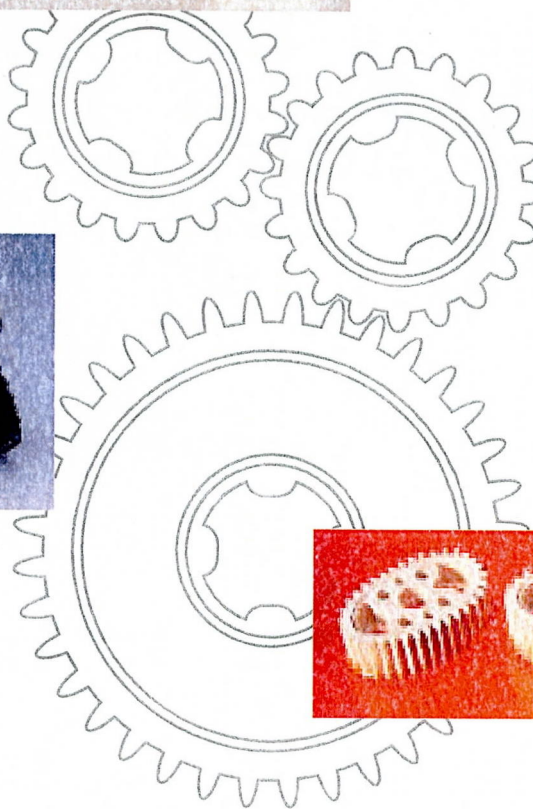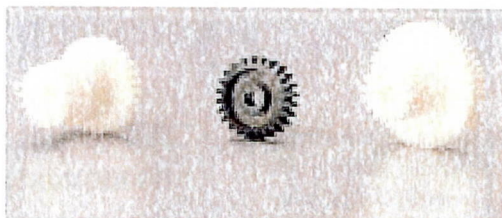

**Engineering polymers
for gears from DuPont.
More high-performance materials.
More skillful solutions.**

Pinpoint the performance you need with DuPont polymers.

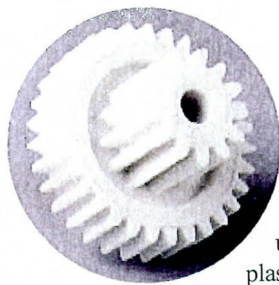


To satisfy the demand for lighter, faster, quieter, more durable, cost-effective products, innovative designs increasingly include the use of high-performance plastics. In applications

ranging from automotive components to office automation equipment, engineering polymers successfully replace metals—even in fine critical gears—and contribute superior performance. As design engineers worldwide discover the remarkable benefits of polymers for gears, they also discover that identifying the right product for the job can sometimes be a difficult proposition.

Delrin® acetal resin

Gear trains used in Lexmark's Optra laser printers have 11 gears molded from Delrin®. The gears drive the printer's toner drum, fuser rollers, and other media transport rollers or in ink transfer and fusion operations to an output tray. In the spur gears, Delrin® 500P offers dimensional stability, high strength, low friction and wear, and high molding productivity. In the helical gears, Delrin® 500CL satisfies additional requirements for low wear and friction at high PV conditions.

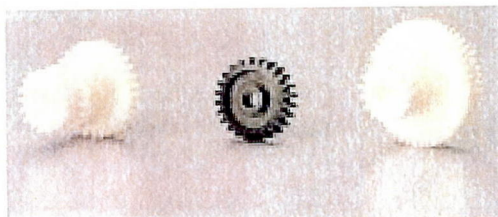


DuPont can help you hit the mark.

DuPont has been helping to solve tough gear design problems almost as long as we've been making polymers. In fact, the earliest plastic gears were made with the industry's first engineering polymer, DuPont Zytel® nylon resin.

DuPont Delrin® acetal resins and Zytel® nylon resins have been used in gears for more than 35 years in hundreds of diverse products, including windshield wipers, windowlifts, speedometers, rotary pumps, appliances, power tools, clocks, and copy machines.

No other supplier today offers more high-performance polymers for gears and more expertise—from design consultation to molding assistance—to streamline material selection. With the recent introduction of additional grades to many product families, DuPont offers a wider range of solutions than ever before.




DuPont polymers: The right choice, right from the start.

By involving DuPont early in the development process, along with an experienced team of gear molders and designers, DuPont can help you select the ideal product to meet your exact needs and help you enjoy the following benefits of plastics:

Lubricity. A low coefficient of friction provides gears of Delrin®, Zytel®, and other DuPont engineering polymers with a distinct performance advantage over metals in applications that do not permit external lubrication or where lubrication is limited to initial installation. DuPont offers a variety of internally lubricated polymer compositions to further improve wear resistance and reduce friction without the expense or assembly complication and inconvenience of external lubricants.

Shock Resistance. The intrinsic resilience of plastic gears provides superior damping of moderate shock or impact loads. Toughened grades of Delrin® and Zytel® are available for high-shock applications.

Noise Reduction. Pliable plastic gears offer smoother, quieter operation than metal gears. When designed with adequate clearance, plastic gear teeth will deflect slightly under loading. This deflection makes small differences in pitch and profile less critical, thus helping to reduce noise from meshing teeth. DuPont's toughened resins are more flexible and help to enhance this effect. For highly sliding meshes, like those found in worm or helical gear arrangements, potential plastic squeak can be prevented by selecting one of DuPont's many internally lubricated polymers.

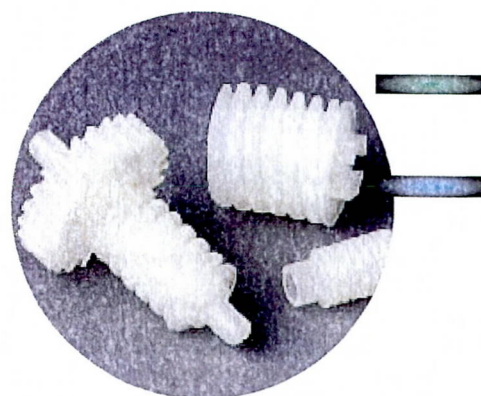

DuPont polymers at a glance.

-  **Delrin® acetal resin.** The most widely used DuPont resin for gears, Delrin® is a homopolymer that provides a superior combination of performance benefits: excellent mechanical properties—strength, toughness, fatigue endurance, and surface hardness—good lubricity, and resistance to wear, moisture, and chemicals. Many grades of Delrin® are designed specifically for demanding applications.
-  **Zytel® nylon resin.** The first engineering polymer for gears, Zytel® offers exceptional strength, toughness, temperature resistance, and excellent moldability. It can be modified in a number of ways to optimize performance, and is frequently used in conjunction with Delrin® to reduce gear noise and wear.
-  **Zytel® HTN high-temperature nylon resin.** Compared with other Zytel® nylons, Zytel® HTN exhibits enhanced moisture stability, increased chemical resistance, and better mechanical properties at elevated temperatures.
-  **Zytel® DMX nylon resin.** Zytel® DMX provides significantly improved dimensional stability and more consistent mechanical properties across varying humidity levels, as compared with traditional Zytel® nylons.
-  **Minlon® mineral-reinforced nylon resin.** Minlon® offers better strength and stiffness than unreinforced nylon. Compared with glass reinforced nylon, Minlon exhibits less potential for part warpage and is less costly.
-  **Hytrel® thermoplastic polyester elastomer.** Hytrel® provides extra tough teeth for gears subject to extreme shock or when mesh noise reduction is required. Often, just one gear made of Hytrel is enough to reduce noise in an entire gear train.
-  **Crastin® PBT thermoplastic polyester resin and Rynite® PET thermoplastic polyester resin.** Crastin® PBT and Rynite® PET are selected for strong, stiff gears in environments where a high degree of dimensional stability is required at high service temperatures.
-  **Zenite™ LCP liquid crystal polymer resin.** Zenite™ LCP may be the best solution in applications requiring any or all of the following: extremely thin or small gears, exact tool replications, ultra-high temperature resistance, superior chemical resistance, exceptional dimensional stability.
-  **VespeI® polyimide parts and shapes.** VespeI® tackles high-performance gear applications. DuPont offers finished gears of VespeI® manufactured to your specific requirements.

Zenite™ LCP liquid crystal polymer resin

Two mating oval gears molded from Zenite™ LCP precisely meter motor oil or other automotive fluids flowing through the hand-held EM5™ electronic meter made by Graco, Inc.

Zenite™ 6330, a 30% mineral reinforced formulation, fulfills Graco's demanding requirements for molding accuracy, exceptional dimensional stability, and resistance to attack by automotive lubricants, brake fluid, and antifreeze. The gears are installed with minimal clearance in the meter body. They are molded to high precision with zero draft.

Cost Efficiency. Gears made with DuPont polymers can be a cost-effective alternative to metal. The nature of molded plastic permits parts consolidation and therefore reduces costly manufacturing and assembly operations. Cams, bearings, ratchets, and gear shafts can be designed as an integral part of an injection molded plastic gear. Multiple gear clusters also may be molded as a unit, decreasing part count and significantly increasing costs savings.

Durability. In low-stress environments, plastic gears typically offer longer lasting performance than their metal counterparts. Unmodified Delrin® and Zytel® both exhibit excellent friction, wear, and mechanical properties which can be enhanced by modifications. Selection of modifications should be based on the expected failure mode, such as wear, fatigue, tooth shear, or bending. Unlike metal gears, plastic gears should


be designed to allow for tooth deflection, which is a result of the flexural modulus of the polymer. Gear life can be maximized by selecting a polymer, family and modification that balances friction and wear properties, strength, and fatigue resistance all at operating temperature.

Chemical Resistance. Compared with most metals, plastics offer superior resistance to the corrosive effects of a wide range of chemicals. Gears made of Delrin®, Zytel®, and other semi-crystalline DuPont polymers resist most oils and lubricants, solvents, and more.

Weight Reduction. Plastics have lower density than metals even when reinforced with glass and other materials. Gears made with DuPont polymers can significantly reduce inertia and total assembly weight.

What a few pages can do for you.

This brochure is designed to introduce you to DuPont's wide selection of polymers for gears and to offer some general material selection guidelines. We hope you'll use this information as just one part of a material selection process that includes technical support from DuPont.

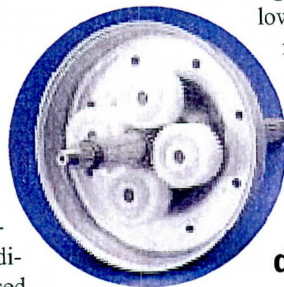

More products, more solutions.

In addition to our widely specified resins for gears—Delrin® and Zytel®—DuPont offers the broadest assortment of engineering polymers in the business. With so many high-performance products to

choose from, it would be difficult to list every available resin grade. Table I presents the DuPont polymer families for gears along with applicable modifications, reinforcements, and lubricants. Recently introduced compositions are highlighted.

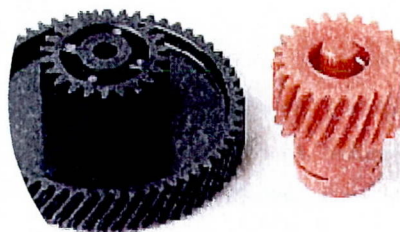


Table I
DuPont Engineering Polymers for Gears

Product Composition	Unmodified, General Purpose	Multiple Flow Grades	Enhanced Crystallinity/Nucleated	Toughened	Reinforced/Modified			Lubricated			Finished Gears
					Glass	Mineral	Kevlar™ Aramid	Teflon® Fluoro-carbon Resin	Internal Chemical	Silicone	
Product Family											
Delrin® acetal resin	■	■	▲	▲	▲		▲	▲	▲	▲	
Zytel® nylon resin	■	■	■	■	■		▲				
Zytel® HTN high-temperature nylon resin				▲	▲	▲					
Zytel® DMX nylon resin				▲	▲						
Minlon® mineral reinforced nylon resin				■	■	■					
Hytrel® thermoplastic polyester elastomer	■	■									
Crastin® PBT thermoplastic polyester resin	■	■		■	■	▲					
Rynite® PET thermoplastic polyester resin				■	■	■					
Zenite™ LCP liquid crystal polymer resin					■	■					
VespeI® polyimide parts and shapes ¹											▲

Key: ■—available grades
▲—new compositions since 1995.

¹VespeI® is the only polymer made into finished gears by DuPont. VespeI® is not available for purchase as molding resin.

Delrin® acetal resin

Cagiva of Italy uses Delrin® 500 for the gears in its motorcycle oil pumps.

Delrin® was selected for its excellent fatigue endurance, chemical resistance, and dimensional stability.

The gears made of Delrin® provide smooth operation, less noise, and reduced assembly costs.

Fine tuning the selection.

Once an appropriate resin family is selected for a particular application, resin properties can be enhanced through compositional modifications. Unmodified resin is the most economical, widely available choice. It is usually recommended for

general gearing; press-fit applications; and lubricated self-mating gears under low load conditions. Modifications are suggested only when necessary, as they will almost always increase cost.

Table II provides some of the principal benefits and limitations of common modifications compared with the unmodified resin.

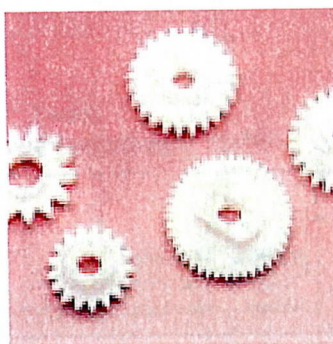


Table II
Principal Effects of Resin Modifications on Gear Properties

		Strength and Modulus	Impact Strength	Friction against Steel	Wear against Steel	Friction against Itself	Wear against Itself	Abrasive Wear	Slow-speed Squeak	Impact Noise	Resin Cost	KEY: Performance of modified composition compared with unmodified general-purpose resin. Limitation Performance Declines Benefit Performance Improves
Product Grade		Attributes										Typical Applications
Multiple Flow Grades	High Viscosity											High-shock gears; auto windowlift gears
	High Flow											Extremely fine gears; sprinkler gears
Enhanced Crystallinity/ Nucleated												High-volume production; printer gears
Toughened												High-shock gears; washer spin gears; applications requiring noise reduction
Reinforced	Glass											Lubricated power gears; garage door opener gears; door lock actuator gears
	Mineral											Low-cost, lubricated gears
	Kevlar™											Gears requiring modest increase in tooth strength without the abrasiveness of glass reinforcement
Lubricated	Teflon®											Unlubricated, high-load, high-speed helical gears mated with steel worm; high-performance, multifunctional gears and cams, first stage motor reduction gears
	Internal Chemical											Unlubricated gears requiring low wear; gears mated with soft metals (e.g., brass, aluminum)
	Silicone											Unlubricated plastic gear meshes requiring low wear and low friction, printer gears

Delrin® and Zytel®: Your first choice for gears.

Acetal and nylon resins account for the vast majority of plastic gears in use today. Most designers will want to begin materials evaluation by investigating DuPont Delrin® and Zytel® first.

Delrin® homopolymer acetal resins and the polyamide (PA) 66 grades of Zytel® nylon resins offer greater strength and modulus than competitive copolymer acetals and PA 6 nylons, respectively, especially at elevated temperatures. Compared with other polymers, both Delrin® and Zytel® offer multiple performance benefits that make them ideally suited to a wide range of gears. When comparing the two, you'll need to consider the following:

The advantages of Delrin®.



- Most frequently used polymer for gears
- Superior dimensional stability and low water absorption
- Superior strength, modulus, flexural fatigue endurance, and high surface hardness

- Lower coefficient of friction against steel
- Available in a variety of lubricated compositions for improved friction and wear performance

The advantages of Zytel®.

- Performs at higher service temperatures
- Resin of choice for worm gears
- Used as a dissimilar material against Delrin® to reduce gear wear and noise
- Lower surface hardness and modulus which reduces mesh noise against steel
- Better resistance to mild acids and bases
- Provides more forgiving, tougher gear teeth

The most commonly used compositions of Delrin® and Zytel® for gears are provided in Tables III and IV.

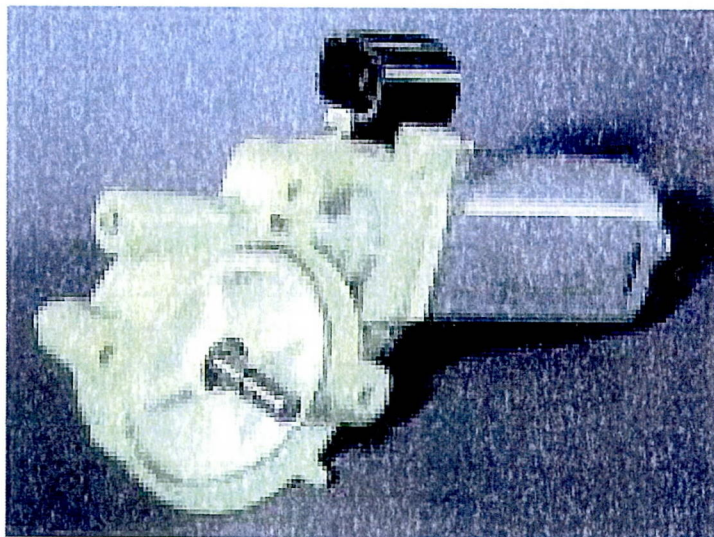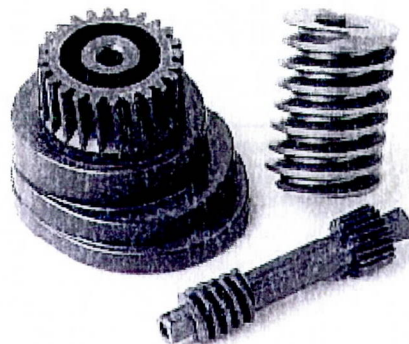

Delrin® acetal resin
and **Zytel® HTN** high-
temperature nylon resin

UTA Motor Systems' windowlift motors, installed in Ford Taurus and Mercury Sable automobiles, use gears made of Delrin® 100. Delrin® provides a combination of impact and moisture resistance, stiffness, and low coefficient of friction. The motor gear housing, injection molded from Zytel® HTN, marks a major shift away from traditional die-cast aluminum.

Table III
Delrin® Acetal Resins—Common Compositions for Gears

Product Composition		Product Grade	Description
Unmodified, General Purpose		Delrin® 100	High viscosity, maximum toughness
		Delrin® 100P	High viscosity, tough, improved mold release and thermal stabilizing system
		Delrin® 500	Medium viscosity
		Delrin® 500P	Medium viscosity, improved mold release and thermal stabilizing system
		Delrin® 900	Low viscosity, high flow
		Delrin® 900P	Low viscosity, high flow, improved mold release and thermal stabilizing system
		Delrin® 1700P	Ultra-low viscosity, maximum flow, improved mold release and thermal stabilizing system
Enhanced Crystallinity		Delrin® 111P	High viscosity, enhanced crystallinity, improved thermal stabilizing system
		Delrin® 511P	Medium viscosity, enhanced crystallinity, improved thermal stabilizing system
		Delrin® 911P	Low viscosity, enhanced crystallinity, improved thermal stabilizing system
Toughened		Delrin® 100ST	High viscosity, super tough
		Delrin® 500MT	Medium viscosity, medium toughened, improved thermal stabilizing system
		Delrin® 500T	Medium viscosity, toughened
Reinforced/ Modified	Glass	Delrin® 525GR	Medium viscosity, 25% glass reinforced, improved thermal stabilizing system
		Delrin® 510GR	Medium viscosity, 10% glass reinforced, improved thermal stabilizing system
	Kevlar™	Delrin® 100KM	High viscosity, modified with Kevlar™ aramid resin, improved thermal stabilizing system
Lubricated	Teflon®	Delrin® 100AF	High viscosity, tough, 20% Teflon® PTFE fibers, improved thermal stabilizing system
		Delrin® 500AF	Medium viscosity, 20% Teflon® PTFE fibers, improved thermal stabilizing system
		Delrin® 520MP	Medium viscosity, 20% Teflon® PTFE micropowder, improved thermal stabilizing system
		Delrin® 510MP	Medium viscosity, 10% Teflon® PTFE micropowder, improved thermal stabilizing system
		Delrin® 500TL	Medium viscosity, 1.5% Teflon® PTFE micropowder
	Internal Chemical	Delrin® 500AL	Medium viscosity, advanced lubricant system, improved thermal stabilizing system
		Delrin® 500CL	Medium viscosity, chemical lubricant
		Delrin® 900SP	Low viscosity, proprietary lubricant, improved thermal stabilizing system
	Silicone	Delrin® 500SC	20% Silicone concentrate, typically let down to 1% or 2%

Table IV
Zytel® Nylon Resins—Common Compositions for Gears

Product Composition		Product Grade	Description
Unmodified, General Purpose		Zytel® 101L	General purpose, lubricated ¹ PA 66
		Zytel® 103HSL	General purpose, heat stabilized, lubricated ¹ PA 66
		Zytel® 101F	General purpose, internally lubricated ¹ PA 66
		Zytel® 42A	High viscosity PA 66
		Zytel® 151L	General purpose, lubricated ¹ PA 612
		Zytel® 153HSL	General purpose, heat stabilized, lubricated ¹ PA 612
Nucleated		Zytel® 132F	Nucleated, internally lubricated ¹ PA 66
Toughened		Zytel® ST801	Super tough PA 66
		Zytel® 408L	Toughened, lubricated ¹ PA 66
Reinforced	Glass	Zytel® 70G33L	33% Glass reinforced PA 66
		Zytel® 77G33L	33% Glass reinforced PA 612
	Kevlar™	Zytel® 70K20HSL	PA 66 Reinforced with 20% Kevlar™ aramid resin

¹ Lubrication in these grades is used as a processing aid only. It is not intended to improve friction and wear properties.

The impressive performance of Delrin® and Zytel®.

To give you a sense of the performance characteristics of these highly functional polymers for gears, important mechanical properties and durability test results are provided. Of course, this information offers a selection guideline only. More property data is provided in the DuPont Design Guides for Delrin® and Zytel®.


Mechanical Properties.

A selection of mechanical properties is presented for some of the most commonly used Delrin® resins in Table V.

Delrin® acetal resin
and **Minlon®** mineral-reinforced nylon resin

The Chamberlain Group's ceiling-mounted garage door openers use an injection molded worm made of

Minlon® 10B40 and a worm gear molded from Delrin® 100. Delrin® and Minlon® provide the requisite mechanical strength and excellent compatibility for low friction and wear. The lubricated gears run quietly and perform flawlessly in tests involving

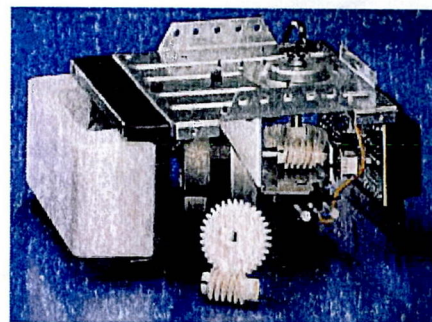

25,000 open/close cycles (the equivalent of 15 years of service). They also cost less than the glass-reinforced nylon and steel gears they replaced.


Table V
Mechanical Properties of Various Delrin® Acetal Resins

Product Description Properties	Unmodified, General Purpose			Enhanced Crystallinity	Toughened		Glass Reinforced	Lubricated		
	100P	500P	900P	511P	100ST	500T	525GR	Teflon®		Internal Chemical
Tensile Strength at Yield MPa (kpsi) ASTM D638	67 (9.7)	68 (9.9)	69 (10.0)	72 (10.4)	45 (6.5)	53 (7.7)	151 ¹ (21.9) ¹	54 (7.8)	61 (8.9)	66 (9.6)
Elongation at Yield, % ASTM D638	23	15	11	11	35	15	NA ²	12	10	10
Elongation at Break, % ASTM D638	80	40	25	33	>150	75	3	14	13	30
Flexural Modulus MPa (kpsi) ASTM D790	2,790 (410)	3,100 (450)	3,240 (470)	3,300 (480)	1,130 (160)	2,250 (330)	8,000 (1,160)	3,100 (450)	3,160 (460)	2,970 (430)
Izod Impact, notched J/m (ft-lb/in) ASTM D256	120 (2.3)	75 (1.4)	69 (1.3)	73 (1.4)	NB	128 (2.4)	96 (1.8)	32 (0.6)	27 (0.5)	58 (1.1)
Izod Impact, unnotched J/m (ft-lb/in) ASTM D256	NB ³	NB ³	1,630 (30.6)	NB ³	NB ³	NB ³	1,100 (20.6)	720 (13.5)	950 (17.8)	2,350 (44)

¹Values are tensile strength at break, since these materials do not yield.

²NA means not applicable.

³NB means no break occurs.

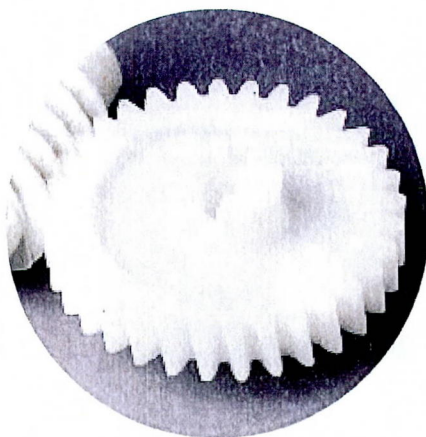

Compared with lower viscosity grades (the 500 and 900 series), the high-viscosity 100 series resins, such as Delrin® 100P, offer significantly greater elongation and impact strength with little change in flexural modulus or tensile strength. The toughened resins exhibit greater impact strength than Delrin® 100P with lower modulus and tensile strength. Glass reinforced Delrin® 525GR offers a significant increase in modulus and tensile strength with reduced elongation.

Property data for Zytel® resins is provided for dry as molded (DAM) and 50% relative humidity (RH) equilibrated samples in Table VI.

Immediately after molding, nylon parts contain less than 0.3% moisture, but gradually begin to absorb water from the

atmosphere and approach near equilibrium levels at 50% RH (PA 66: up to 2.5%; PA 612: up to 1.3%). The water content in nylon slowly cycles with seasonal variations in RH.

Toughening and glass reinforcement of Zytel® have effects on mechanical properties similar to those noted for the same modifications of Delrin®. The Zytel® PA 66 nylon resins have higher modulus and tensile strength than the comparable PA 612 resins when dry (DAM), but at 50% RH show similar properties.

Durability.

Friction and wear properties (tribological characteristics) are highly dependent on the configuration of the gear train, choice of gear materials, service requirements, and molding conditions.

Table VI
Mechanical Properties of Various Zytel® Nylon Resins
(Dry as Molded/Conditioned to 50% Relative Humidity)

Product Description	Unmodified, General Purpose		Toughened	Glass Reinforced	
	101L PA 66	151L PA 612		70G33L PA 66	77G33L PA 612
Properties					
Tensile Strength at Yield MPa (kpsi) ASTM D638	83/59 (12.0/8.5)	61/52 (8.8/7.4)	52/41 ¹ (7.5/6.0) ¹	186/124 ¹ (27/18) ¹	165/138 ¹ (24/20) ¹
Elongation at Yield, % ASTM D638	5/25	7/30	NA ²	NA ²	NA ²
Elongation at Break, % ASTM D638	60/≥300	60/250	60/210	3/4	3/4
Flexural Modulus MPa (kpsi) ASTM D790	2,830/1,210 (410/175)	2,030/1,240 (295/180)	1,690/860 (245/125)	8,970/6,200 (1300/900)	8,270/6,200 (1,200/900)
Izod Impact, notched J/m (ft-lb/in) ASTM D256	53/112 (1.0/2.1)	43/69 (0.8/1.3)	910/1,070 (17.0/20.0)	117/133 (2.2/2.5)	128/133 (2.4/2.5)
Izod Impact, unnotched J/m (ft-lb/in) ASTM D256	NB ³	NB ³	NB ³	1,330/1,490 (25/28)	1,330/1,330 (25/25)

¹Values are tensile strength at break, since these materials do not yield.

²NA means not applicable.

³NB means no break occurs.

Plastic gears may mate with gears of the same or a different plastic composition or with metals like brass, aluminum, or steel. Plastic gear wear is notably affected by the surface roughness of mating metal gears. Gear wear may be reduced by adding internal lubricants to the polymer. Gears molded with DuPont Teflon® fluorocarbon lubricated resins are especially effective in combating wear against steel.

The effect of molding on tribological characteristics can be demonstrated by increasing the mold temperature. Higher temperatures lead to higher levels of crystallinity, which in turn improves wear performance.

DuPont has conducted a number of studies to provide comparative information on the friction and wear characteristics of a variety of polymer resins. Given the complexity of friction and wear studies, it is necessary to verify performance by testing the chosen material in a prototype part under simulated operating conditions.

High Sliding Wear.

Gear wear will increase with contact pressure (load) and increased sliding velocity. Because worm gears generally have a high degree of sliding contact, as opposed to primarily rolling contact, wear should be investigated as a failure mode.

In one test, a modified ASTM D3702 thrust washer of Delrin® was rotated against two unlubricated countersurfaces at various loads and velocities in order to measure both break-in and equilibrium wear. Equilibrium wear is the constant wear rate experienced after initial break-in wear has occurred. The results of this test were used to develop three-dimensional plots of equilibrium specific wear rate ($\dot{W}_s$)—as defined by DIN method 50324—versus pressure $\times$ velocity (PV) and velocity (V). In an effort to provide practical design guidance, the data is presented at potential operating PV ranges, as opposed to describing a PV limit. This test is most applicable to worm or helical gears.

Two examples of these three-dimensional plots are provided in Figures 1 and 2 for Delrin® 520MP against steel and Delrin® 500AL against itself. The plots show that

wear is dependent on operating pressure and velocity. Lubricated grades like Delrin® 520MP and 500AL are less dependent on these parameters than nonlubricated compositions.

To help simplify the data from three-dimensional plots, comparisons are presented in Tables VII and VIII for various Delrin® resins against steel and against themselves at two PV conditions.



Delrin® acetal resin

Delrin® 100 is used in mixer gears

manufactured by E.G.S. of Germany.

Delrin® was selected because of

its good impact strength, low coefficient of friction, and high stiffness. The switch to Delrin® means improved productivity, a low reject rate, and cost reductions as the result of parts consolidation.

Figure 1. Delrin® 520MP Against Steel: Equilibrium-Specific Wear Rate



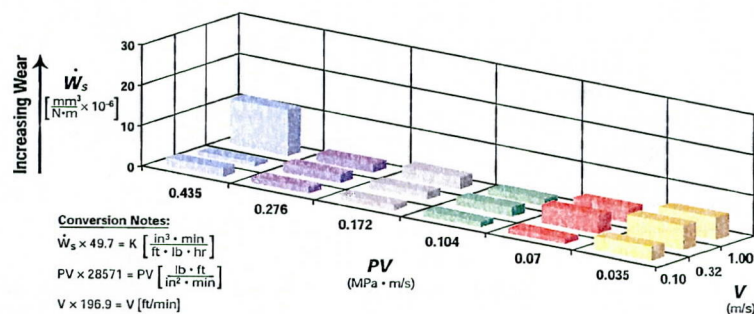


Figure 2. Delrin® 500AL Against Itself: Equilibrium-Specific Wear Rate

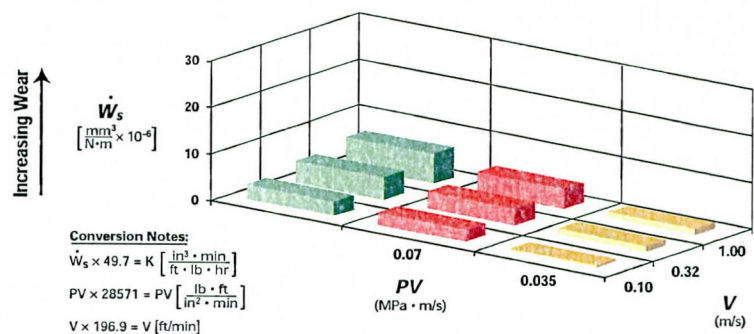

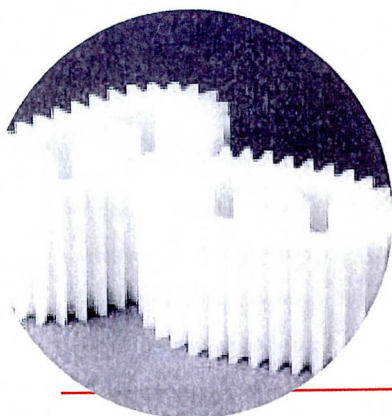

In Table VII, the break-in and equilibrium wear of Delrin® against steel at both PV conditions show that Delrin® 500P is slightly better than Delrin® 500. All of the lubricated compositions in this table are significantly better than Delrin® 500 and 500P. Delrin® 500AF offers the lowest wear and coefficient of friction

(COF) values. Delrin® 500AF, 520MP, and 510MP are all very low in break-in wear.

Wear of plastic against plastic is generally much greater than wear of plastic against steel; therefore, the results represented in Table VIII are for significantly lower PV conditions. The data for

Table VII
Specific Wear Rate and Coefficient of Friction—Delrin® Against Steel

Product Composition		Product Grade	Break-in Wear	Equilibrium Wear			
			PV=0.104	PV=0.104 (P=0.33 MPa V=0.32 m/s)		PV=0.172 (P=0.55 MPa V=0.32 m/s)	
			Wear, $\dot{W}_s$	Wear, $\dot{W}_s$	Dyn. COF	Wear, $\dot{W}_s$	Dyn. COF
Unmodified, General Purpose		Delrin® 500	22.5	15.5	0.39	26.0	0.43
		Delrin® 500P	13.5	8.5	0.37	5.4	0.34
Toughened		Delrin® 500T	10.5	10.0	0.54	4.0	0.47
Lubricated	Teflon®	Delrin® 500AF	2.1	1.4	0.19	0.7	0.16
		Delrin® 520MP	2.0	2.2	0.17	1.9	0.18
		Delrin® 510MP	2.6	1.8	0.20	1.3	0.20
		Delrin® 500TL	8.1	1.6	0.27	2.0	0.21
	Internal Chemical	Delrin® 500AL	5.2	3.8	0.23	1.5	0.18
		Delrin® 500CL	6.0	2.0	0.20	3.6	0.21

Metric Units—Specific Wear Rate $\dot{W}_s = \frac{\text{mm}^3}{\text{N} \cdot \text{m}} \times 10^{-6}$

Conversion Notes: $P(\text{MPa}) \times 145 = P(\text{lb/in}^2)$
 $V(\text{m/s}) \times 196.9 = V(\text{ft/min})$

Table VIII
Specific Wear Rate and Coefficient of Friction—Delrin® Against Itself
(Wear of Washer Test Surface Only)

Product Composition		Product Grade	Break-in Wear	Equilibrium Wear			
			PV=0.035	PV=0.035 (P=0.11 MPa V=0.32 m/s)		PV=0.070 (P=0.22 MPa V=0.32 m/s)	
			Wear, $\dot{W}_s$	Wear, $\dot{W}_s$	Dyn. COF	Wear, $\dot{W}_s$	Dyn. COF
Unmodified, General Purpose		Delrin® 500	>600	26.0	0.42	885	0.50
		Delrin® 500P	>600	16.1	0.44	503	0.48
Lubricated	Teflon®	Delrin® 520MP	3.21	0.08	0.29	0.44	0.20
		Delrin® 500TL	78.7	7.04	0.34	11.7	0.30
	Internal Chemical	Delrin® 500AL	6.43	1.23	0.30	3.72	0.23
		Delrin® 900SP	1.55	1.15	0.33	2.96	0.23
	Silicone	Delrin® 500P with with 1% Silicone	24.8	7.85	0.33	19.7	0.20
		Delrin® 500P with with 2% Silicone	2.01	0.52	0.30	0.60	0.18

Metric Units—Specific Wear Rate $\dot{W}_s = \frac{\text{mm}^3}{\text{N} \cdot \text{m}} \times 10^{-6}$

Conversion Notes: $P(\text{MPa}) \times 145 = P(\text{lb/in}^2)$
 $V(\text{m/s}) \times 196.9 = V(\text{ft/min})$

Delrin® resins against themselves demonstrates that Delrin® 500 and 500P resins have the greatest wear of the compositions tested. The other compositions, which include special internal lubrication systems, are all significantly better than the unmodified resins, and 2% silicone in Delrin® 500P is markedly better than 1%. Although the differences among Delrin® 500P with 2% silicone, 520MP, 500AL, and 900SP are slight, Delrin® 900SP exhibits the lowest break-in wear. Delrin 520MP shows the lowest equilibrium wear under these conditions.

Low Sliding Wear.

DuPont measured tooth wear in spur gears, each made of a different Delrin® resin. The gears were driven by a steel pinion at equivalent torque and speed. In Figure 3, compositions containing Teflon® (Delrin® 500AF, 520MP, and 510MP) show the least wear, followed by chemically lubricated Delrin® 500AL and the resins without any internal additive or lubricant, Delrin® 500T and 500P.

In the same test, sensitivity to load of the three Delrin® resins containing Teflon® was also measured. Each resin was compared at two different initial contact stress levels. As shown in Figure 4, greater initial contact stress causes more wear.

Figure 3. Unlubricated Wear of Gear Teeth—Delrin® Against Steel


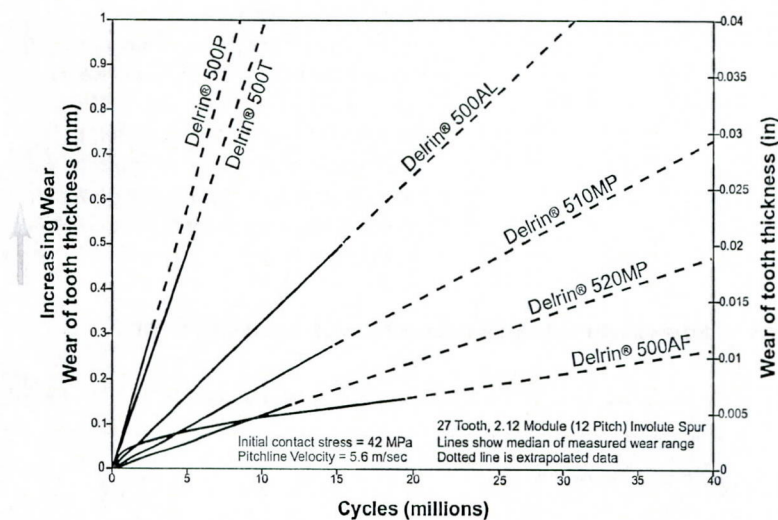


Figure 4. Sensitivity to Load—Delrin® Against Steel



Zytel® nylon resin


In small appliance engines manufactured by Briggs & Stratton, the cam gear and lobes are insert molded around a steel camshaft using Zytel® 103HSL. Chosen for its high-temperature toughness and oil resistance, Zytel® reduces noise at the cam/lifter interface and provides greater cost efficiency.

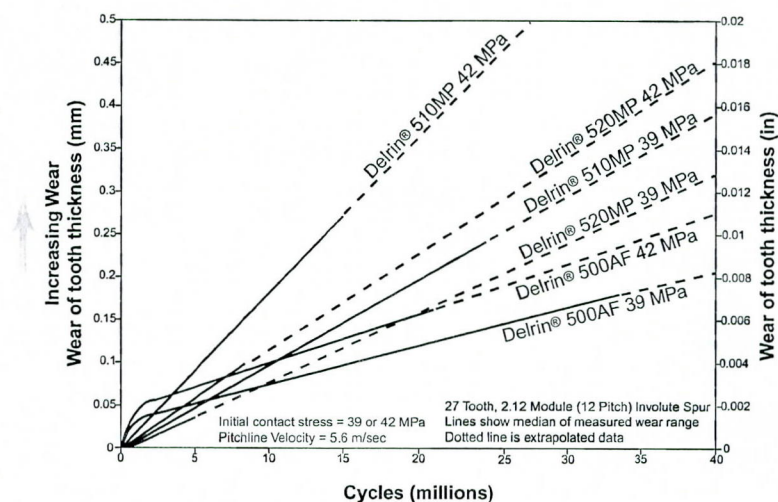

Fatigue.


Tooth fatigue from repeated bending stress is another important failure mode for continuously or initially lubricated gears. A simple approximation of this stress may be calculated using a form of the Lewis equation. This approach assumes that only one tooth of each gear is in contact near the pitch point and carries the entire load.

Figure 5. Maximum Bending Stress for Continuously Lubricated Gear Teeth

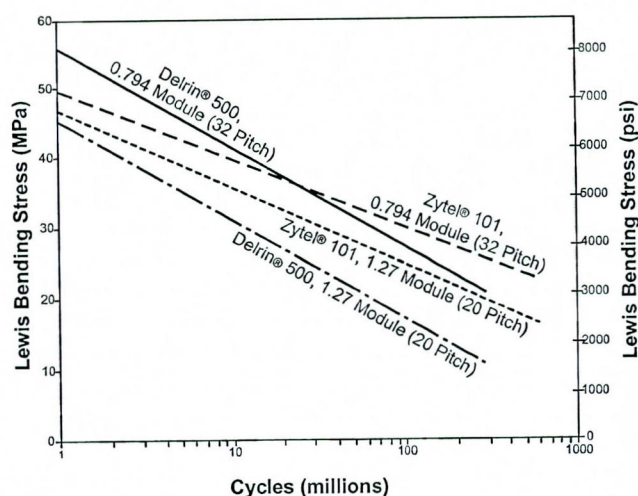

Delrin® acetal resin

Zanussi IMD of Italy uses Delrin® 500 in its gears for vending machine grinders. Delrin® was selected because of its dimensional stability at higher temperatures and lower noise. The gears made of Delrin® are quieter than the metal parts they replaced.

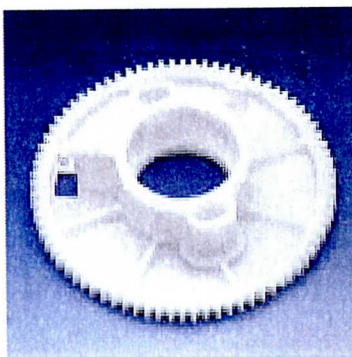

$$S_b = \frac{2 T}{f Y M D_p}$$

where S_b = Bending stress

T = Gear torque


f = Gear face width

Y = Lewis form factor for plastic gears, loaded near the pitch point

M = Module (pitch diameter in millimeters (mm) ÷ number of gear teeth)

D_p = Pitch diameter

In one gear-life test, tooth bending stress was calculated on continuously lubricated gears using this formula to plot cycles (gear revolutions) to failure. The plotted bending stress presented in Figure 5 has been reduced by 25% to provide an acceptable safety margin. Lines are presented for 20- and 32-pitch gears of both Delrin® 500 and Zytel® 101.

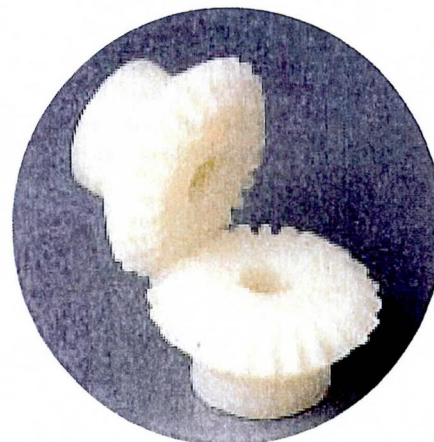

Make DuPont part of an ideal solution.

When you involve DuPont early in the process as part of your gear design team, you have access to a wealth of resources:


- An unmatched selection of high-performance engineering polymers to meet your precise gearing requirements
- Unsurpassed technical support from design through molding
- A global network of interlinked technical service laboratories, equipped to handle virtually all standard and many nonstandard testing procedures
- More than 50 years of experience and innovation in engineering polymers
- Polymers research and development laboratories, located worldwide, to provide continuous product improvement
- Polymers manufacturing in more than two dozen locations on four continents

For technical assistance, additional product or property data, or for more information about using property data to design gears, please call DuPont at 1-800-441-0575 or contact the location nearest you. We can be reached online at <http://www.dupont.com/enggpolymer/americas>. No supplier is better prepared to help you zero in on the best solution to your next gear design problem.

Zytel® nylon resin

Black and Decker's cordless

PowerDriver screwdrivers have a planetary gear transmission with two stages, each using three gears of Zytel® 101L. The gears run against metal sun gears and a zinc ring gear. Zytel® offers quiet operation, excellent durability, and precision molding. It replaces metal in the second-stage gears at a lower cost.

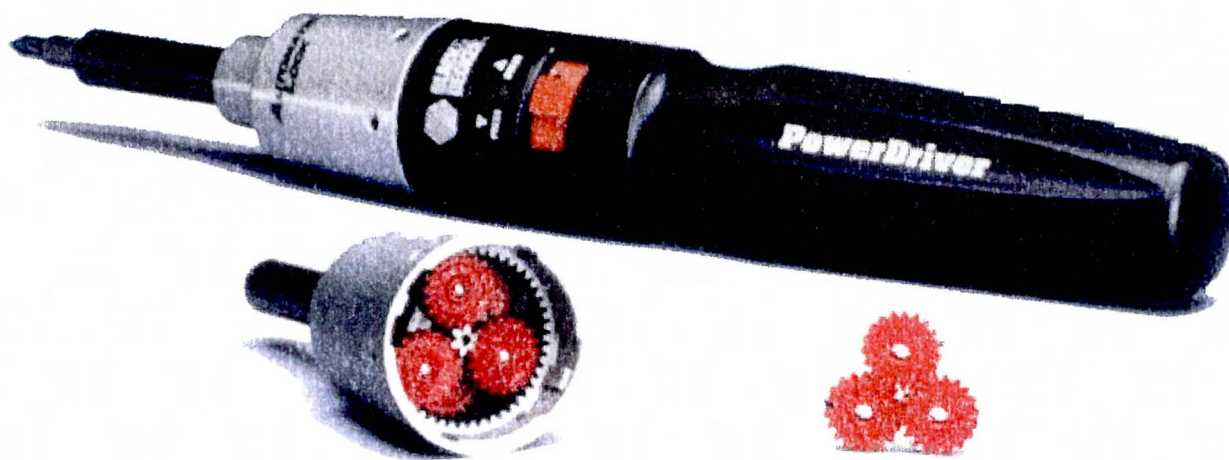

Gear photo insets throughout provided by Winzeler Gear, Inc.

**For more information on
DuPont Engineering Polymers
for gears, call:**

1-800-441-0575

<http://www.dupont.com/enggpolymer>

U.S.A.

DuPont Engineering Polymers
Chestnut Run Plaza 713
P.O. Box 80713
Wilmington, DE 19880-0713
(302) 999-4592

Automotive

DuPont Engineering Polymers
Automotive Products
950 Stephenson Highway
Troy, MI 48007-7013
(248) 583-8000

Asia Pacific

DuPont Asia Pacific Ltd.
P.O. Box TST 98851
Tsim Sha Tsui
Kowloon, Hong Kong
852-3-734-5345

Canada

DuPont Canada, Inc.
DuPont Engineering Polymers
P.O. Box 2200
Streetsville, Mississauga
Ontario, Canada L5M 2H3
(905) 821-5953

Europe

DuPont de Nemours Int'l S.A.
2, chemin du Pavillon
P.O. Box 50
CH-1218 Le Grand-Saconnex
Geneva, Switzerland
Telephone: ##41 22 7175111
Telefax: ##41 22 7175200

Japan

DuPont Kabushiki Kaisha
Arco Tower
8-1, Shimomeguro 1-chome
Meguro-ku, Tokyo 153
Japan
(011) 81-3-5434-6100

Mexico

DuPont S.A. de C.V.
Homero 206
Col. Chapultepec Morales
11570 Mexico D.F.
(011 525) 250-8000

South America

DuPont America do Sul
Al. Itapecuru, 506
Alphaville—CEP: 06454-080
Barueri—Sao Paulo, Brasil
Tel.: (055-11) 421-8531/8647
Fax.: (055-11) 421-8513
Telex: (055-11) 71414 PONT BR

DuPont Argentina S.A.
Avda. Mitre y Calle 5
(1884) Berazategui-Bs.As.
Tel.: (541) 319-4484/85/86
Fax.: (541) 319-4417

The data listed here fall within the normal range of properties, but they should not be used to establish specification limits nor used alone as the basis of design. The DuPont Company assumes no obligations or liability for any advice furnished or for any results obtained with respect to this information. All such advice is given and accepted at the buyer's risk. The disclosure of information herein is not a license to operate under, or a recommendation to infringe, any patent of DuPont or others. DuPont warrants that the use or sale of any material that is described herein and is offered for sale by DuPont does not infringe any patent covering the material itself, but does not warrant against infringement by reason of the use thereof in combination with other materials or in the operation of any process.

CAUTION: Do not use in medical applications involving permanent implantation in the human body. For other medical applications, see "DuPont Medical Caution Statement," H-50102.



STRESS
CALCULATIONS



THERMAL DEFORMATION : $\Delta L = \alpha L_0 (T_2 - T_1)$
 THERMAL STRAIN $\epsilon_{TH} = \frac{\Delta L}{L_0} = \alpha (\Delta T)$
 THERMAL STRESS $\sigma_{TH} = E \epsilon_{TH}$


- MATERIALS :
- STEEL ARM - $\alpha = 13 \times 10^{-6} \frac{1}{K}$ COEF. OF THERMAL EXPANSION
 $E = 30 \times 10^6$ PSI MODULUS OF ELASTICITY
 - DELRIN 500 - $\alpha = 13 \times 10^{-5} \frac{1}{K}$ COEF. OF THERM. EXP.
 $E = 3.3$ GPa MOD. OF ELAS.
 $YS = 69$ MPa YIELD STRENGTH
 - DELRIN 100 - $\alpha = 13 \times 10^{-5} \frac{1}{K}$ COEF. OF TH. EXP
 $E = 3.1$ GPa MODULUS OF ELAS.
 $YS = 69$ MPa YIELD STRENGTH

$\Delta T = -40^\circ C \rightarrow 100^\circ C = 140^\circ$

$L_0 = \text{CIRCUMFERENCE OF SHAFT} + \text{ID OF DELRIN GEAR}$
 $= 2\pi r = 2(\pi)(6\text{mm}) = 37.7\text{mm}$

$\Delta L_{\text{SHAFT}} = \alpha L_0 (\Delta T) = (13 \times 10^{-6} \frac{1}{K})(37.7\text{mm})(140^\circ)$
 $= 0.069\text{mm}$

$\Delta L_{\text{GEAR}} = \alpha L_0 (\Delta T) = (13 \times 10^{-5} \frac{1}{K})(37.7\text{mm})(140^\circ)$
 $= 0.686\text{mm}$



WHEN TEMP INCREASES THE STEEL ARM WILL GET LARGER BY .069mm FOR THE EXTREME TEMP CHANGE. AT THE SAME TIME THE ID ON THE DELRIN GEAR IS GETTING SMALLER, BY 0.686mm, AS THE DELRIN EXPANDS FROM TEMPS THE ID GETS SMALLER.

$\epsilon = \frac{\Delta L}{L} = \frac{(0.069 + 0.686)}{37.7} = .02$

$\sigma_{TH} = E \cdot \epsilon_{TH} = (300\text{MPa})(.02) = 6\text{MPa} \leftrightarrow YS = 69\text{MPa}$

$\sigma_{TH} = E \cdot \epsilon = (3100\text{MPa})(.02) = 62\text{MPa}$