

FLA COE
FLB COE
> FLD Conventional
Business Class
FLC 112 Conventional

> Century Class Conventional
> Argosy
> Cargo
> Columbia
> 122SD and Coronado

> Business Class M2
> Cascadia
> 108SD/114SD
> New Cascadia

**Freightliner
Service Bulletin**

Description of Revisions: *This bulletin replaces the version dated May 5, 2017. Delfleet One™ has been added for aftermarket use.*

Important Information

The following information addresses the assessment of blemishes and repairs in Freightliner vehicles paint finishes. The following standards, which outline requirements for paint-finish quality and blemish repairs, are used by Freightliner personnel to ensure consistency and quality in paint finishes on all vehicles.

Tools

Tools used to measure paint finish can be expensive. However, Axalta (formerly DuPont), PPG and Sherwin-Williams distributors and field representatives have paint-finish measuring tools and the knowledge to use them. Contact Axalta (formerly DuPont), PPG and Sherwin-Williams personnel for assistance and tools through your Daimler Trucks North America (DTNA) Field Service Representative.

Visual Inspection Distance

All paint inspections must be performed at a distance of approximately 3 feet (1 meter) from the vehicle. The light intensity in the inspection area must meet a minimum of 100 foot-candles (1076 meter-candles).

Warranty

Repairs made to correct paint defects **WILL NOT** be paid under warranty, unless the defect violates these paint finish standards. Since determination whether a paint defect violates the paint finish standards is subjective, Freightliner Field Service or Warranty Department representatives should be consulted before questionable paint repairs are undertaken. Requirements and procedures for filing paint claims are outlined in the Freightliner Warranty Manual.

NOTE: Certain areas of the vehicle either are not painted, or are not painted to a standard. Therefore, claims for repairing the paint on these surfaces are not warrantable. The areas include:

- The underside of the hood, including the inside of the wheel wells;
- the underside of the roof-mounted air fairing;
- the underside of the exterior sun visor;
- the inside of the side-mounted air fairings;
- the inside of the bumper.

Quality Assurance Appearance Requirements

These standards describe the painted surface appearance requirements for a vehicle cab and chassis to meet the quality expected in a Freightliner vehicle.

Appearance Zones

All vehicles are divided into various appearance zones, with specific requirements for each zone. See [Fig. 1](#) and [Table 1](#).

Appearance quality requirements are detailed under the "Quality Requirements for Appearance Attributes—Cab and Hood" heading.


Standards for appearance are detailed under the "Paint Surface Blemishes" heading.

Freightliner Service Bulletin

FLA COE
FLB COE
> FLD Conventional
Business Class
FLC 112 Conventional

> Century Class Conventional
> Argosy
> Cargo
> Columbia
> 122SD and Coronado

> Business Class M2
> Cascadia
> 108SD/114SD
> New Cascadia

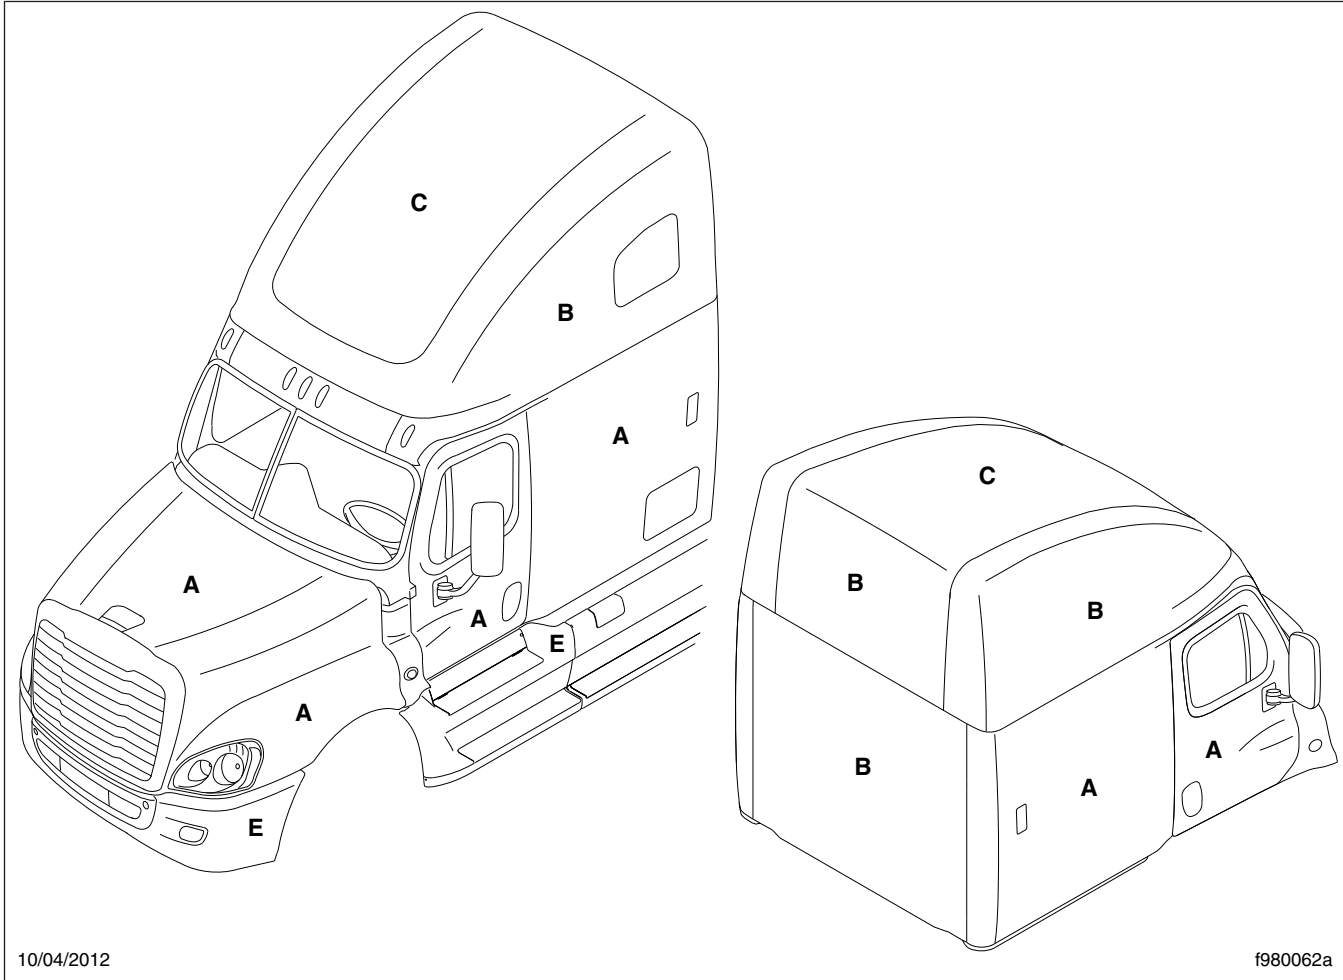

10/04/2012

f980062a

Fig. 1, Paint Appearance Zones (Typical)

Appearance Zones of a Cab and Hood	
Zone	Description
A	All Exterior Surfaces of the Cab, except the Back Panel and Roof Sections: Passenger, Baggage, and Access Doors (including exterior visible surfaces when door is closed), A-Pillar, Cab and Sleeper Side, B-Pillar, C-Pillar, Cowl Side, Lower Skirting, Cab Interior, Hood Top and Sides, Cowl Top, Fender, Upper and Lower Nose Skin, Center Nose Skin, Headlight Bucket, Sun Visor, non-textured Chassis Side Fairings and Bumpers, Forward Quarter-Fender, and Side Extenders (outboard side only)
B	Interior surfaces of Passenger, Baggage, and Access Doors, Back of Cab Panel, Raised Roof Side, Mid-Roof Side, Raised Roof Back Panel and Raised Roof below Skylight, M2 Access Panel, Side Extenders (inboard side only), and Trim Tabs
C	Flat Roof, Mid-Roof Top, Raised Roof Cap Above Skylight, "B" Side Surfaces (underside or inside) of Fairing Fuel Door, Sun Visor, and Roof Fairing
D	Chassis and Chassis Components

FLA COE
 FLB COE
 > FLD Conventional
 Business Class
 FLC 112 Conventional

> Century Class Conventional
 > Argosy
 > Cargo
 > Columbia
 > 122SD and Coronado

> Business Class M2
 > Cascadia
 > 108SD/114SD
 > New Cascadia

Appearance Zones of a Cab and Hood	
Zone	Description
E	Molded plastic proprietary textured surface parts such as some Chassis Side Fairing and Bumper options

Table 1, Appearance Zones of a Cab and Hood

NOTE: The interior surfaces of the hood and fender wells are to have a light coating (fog) of topcoat paint; however, there are no appearance or surface blemish standard requirements for these areas.

Quality Requirements for Appearance Attributes—Cab and Hood

Gloss

Condition: The term used to describe the relative amount of mirror-like reflection. This is measured in the percentage of light reflected from the surface.

Method of Inspection: Gloss is measured using a 20-degree gloss meter. Gloss measurements should be taken only on flat surfaces of the cab. Contoured surfaces, such as those on the hood, will give false readings. Do not take gloss measurements on the chassis, as the surface preparation of the frame rails is uneven.

Measurement Required: Measure three random points on each of the following surfaces:

- left-hand door
- left-hand sleeper side
- right-hand door
- right-hand sleeper side

Record the average of each set of the above measurements.

Appearance Zone Requirements: See [Table 2](#).

20-Degree Gloss		
Zone	Non-Metallic	Metallic
A	80	65
B	N/A	N/A
C	N/A	N/A
D	N/A	N/A
E*	80	65

* A 60-degree gloss meter is used for zone E. If a 60-degree meter is not available, a 20-degree meter may be used, however the resulting gloss measurement will show a 30 point difference of the value measured in zone A.

Table 2, 20-Degree Gloss

Orange Peel

Condition: An evenly textured surface appearance similar to the skin of an orange.

Method of Inspection: Instrumental evaluation with wave scan or visual evaluation and comparison with the standard ACT orange peel panels ranging from 1 (worst) to 10 (best). When evaluating orange peel, measure a minimum of three random points on each of the following surfaces:

- left-hand door

Freightliner Service Bulletin

FLA COE
 FLB COE
 > FLD Conventional Business Class
 FLC 112 Conventional

> Century Class Conventional
 > Argosy
 > Cargo
 > Columbia
 > 122SD and Coronado

> Business Class M2
 > Cascadia
 > 108SD/114SD
 > New Cascadia

- left-hand sleeper side
- right-hand door
- right-hand sleeper side

Record the average of each set of the above measurements.

Appearance Zone Requirements: See [Table 3](#).

Orange Peel	
Zone	Requirement
A	>=5
B	N/A
C	N/A
D	N/A
E	N/A

Table 3, Orange Peel

Uniformity

Uniformity refers to the consistency of the topcoat appearance over the entire vehicle. Gloss, orange peel, and color should not be visibly different within individual body panels or between adjacent panels in a zone. For example, the gloss of a zone A panel will match other zone A panels, and the gloss of a zone E panel will match other zone E panels.

Film Thickness

Film thickness refers to the layer depth of dry paint on the surface of the part after the baking process.

Method of Inspection: Film thickness can be evaluated instrumentally with a mil thickness gauge suitable for the substrate material. Film thickness measurements are taken as a combination of primer and topcoat for a total thickness.

When evaluating film thickness by instrumental means, measure a minimum of three random points on each of the following surfaces:

- left-hand door
- left-hand sleeper side
- right-hand door
- right-hand sleeper side

Record the average of each set of the above measurements.

Appearance Zone Requirements: See [Table 4](#).

Paint Film Thickness		
Zone	Single Stage	Base/Clear Coat
A	2.8 mils	3.4 mils
B	N/A	N/A
C	N/A	N/A
D	2.4 mils	N/A

FLA COE
 FLB COE
 > FLD Conventional
 Business Class
 FLC 112 Conventional

> Century Class Conventional
 > Argosy
 > Cargo
 > Columbia
 > 122SD and Coronado

> Business Class M2
 > Cascadia
 > 108SD/114SD
 > New Cascadia

Paint Film Thickness		
Zone	Single Stage	Base/Clear Coat
E	2.8 mils	3.4 mils

Table 4, Paint Film Thickness

Paint Surface Blemishes

When combinations of the following blemishes are present, apply the standards for the highest quality requirement.

Bubbles/Craters

Condition: Small, round depressions in the paint film that may or may not expose the underlying surface.

Method of Inspection: Visual inspection only.

Appearance Zone Requirements: See [Table 5](#).

Bubbles/Craters				
Zone	Quantity Per Panel Per Zone	Maximum Size (diameter)	Minimum Distance Apart	Description
A	5 maximum	2 mm	2 allowed within a 6-inch (150-mm) diameter circle	Primer not exposed
B	Unlimited	2 mm	10 allowed within a 6-inch (150-mm) diameter circle	Primer not exposed
C	Unlimited	3 mm	N/A	Primer not exposed
D	Unlimited	4 mm	N/A	Primer not exposed
E	5 maximum	2 mm	2 allowed within a 6-inch (150-mm) diameter circle	Primer not exposed

Table 5, Bubbles/Craters

Dirt

Condition: Foreign matter in, on, or under the paint film surface (e.g., lint, fibers, sanding dust, etc.).

Method of Inspection: Metric scale with visual evaluation and comparison to boundary samples.

Appearance Zone Requirements: See [Table 6](#).

Dirt in Paint			
Zone	Quantity Per Panel Per Zone	Maximum Size (diameter)	Minimum Distance Apart
A	5 maximum	2 mm	2 allowed within a 6-inch (150-mm) diameter circle
B	Unlimited	2 mm	10 allowed within a 6-inch (150-mm) diameter circle
C	Unlimited	3 mm	No requirement
D	N/A	N/A	N/A
E	5 maximum	2 mm	2 allowed within a 6-inch (150-mm) diameter circle

Table 6, Dirt in Paint

Freightliner Service Bulletin

FLA COE
FLB COE
> FLD Conventional
Business Class
FLC 112 Conventional

> Century Class Conventional
> Argosy
> Cargo
> Columbia
> 122SD and Coronado

> Business Class M2
> Cascadia
> 108SD/114SD
> New Cascadia

Ding/Dent

Condition: A ding/dent is a visible depression or protrusion in the metal surface or substrate.

Method of Inspection: Visual evaluation and comparison with appearance zone requirements.

Appearance Zone Requirements: See [Table 7](#).

Ding/Dent	
Zone	Quantity per Panel
A	0 maximum
B	0 maximum
C	No requirement
D	N/A
E	N/A

Table 7, Ding/Dent

Overspray

Condition: Overspray is a rough or gritty texture on a painted surface caused by small droplets of paint that fail to blend or melt into the surface.

Method of Inspection: Visual evaluation and comparison with appearance zone requirements; color difference is not acceptable.

Appearance Zone Requirements: See [Table 8](#).

Overspray	
Zone	Quantity per Panel
A	No visible or felt overspray
B	No visible or felt overspray
C	No visible overspray allowed
D	No overspray of a different color allowed
E	No visible or felt overspray

Table 8, Overspray

Solvent Pops

Condition: Small holes in a paint film usually caused by trapped solvent. Solvent boils are small, clustered, raised but unbroken bubbles in a paint film surface.

Method of Inspection: Visual evaluation and comparison with appearance zone requirements.

Appearance Zone Requirements: See [Table 9](#).

Solvent Pop			
Zone	Quantity per Panel	Maximum Size	Description
A	Unlimited	0.5 mm	3 areas allowed per panel No area larger than 6-inch (150-mm) diameter circle

FLA COE
 FLB COE
 > FLD Conventional
 Business Class
 FLC 112 Conventional

> Century Class Conventional
 > Argosy
 > Cargo
 > Columbia
 > 122SD and Coronado

> Business Class M2
 > Cascadia
 > 108SD/114SD
 > New Cascadia

Solvent Pop			
Zone	Quantity per Panel	Maximum Size	Description
B	Unlimited	0.5 mm	10 areas allowed per panel No area larger than 6-inch (150-mm) diameter circle
C	Unlimited	0.5 mm	N/A
D	Unlimited	0.5 mm	N/A
E	Unlimited	0.5 mm	3 areas allowed per panel No area larger than 6-inch (150-mm) diameter circle

Table 9, Solvent Pop

Polishing Marks

Condition: Marks left by polishing are identified as visible swirl or hazy marks.

Method of Inspection: Visual evaluation.

Requirements: See [Table 10](#).

Polishing Marks	
Zone	Quantity per Panel
A	None allowed
B	None allowed
C	N/A
D	N/A
E	None allowed

Table 10, Polishing Marks

Sags and Runs

Condition: Non-uniform downward flow of a wet paint film, typically found around rivets and along edges.

Method of Inspection: Visual evaluation and comparison to examples shown in [Table 11](#).

Appearance Zone Requirements: See [Table 11](#).

Sags and Runs		
Zone	Quantity per Panel	Maximum Size
A	3	4 mm vertical; no color change
B	10	4 mm vertical
C	Allowed	4 mm vertical
D	Allowed	Outside frame rail: 2 inches (50 mm) Inside frame rail: 6 inches (150 mm)
E	3	4 mm vertical; no color change

Table 11, Sags and Runs

Freightliner Service Bulletin

FLA COE
 FLB COE
 > FLD Conventional Business Class
 FLC 112 Conventional

> Century Class Conventional
 > Argosy
 > Cargo
 > Columbia
 > 122SD and Coronado

> Business Class M2
 > Cascadia
 > 108SD/114SD
 > New Cascadia

Scratches and Mars

Condition: Scratched or marred paint surface.

Method of Inspection: Visual evaluation and comparison with appearance zone requirements.

Appearance Zone Requirements: See [Table 12](#).

Scratches and Mars			
Zone	Allowed	Maximum Size (length)	Description
A	Yes	25 mm	Visible but not felt; easily polished out
B	Yes	25 mm	Visible and felt
C	Unlimited	No requirement	No bare substrate primer exposed
D	Unlimited	No requirement	No bare substrate primer exposed
E	Yes	25 mm	Visible and felt

Table 12, Scratches and Mars

File/Grind Marks

Condition: Cuts in the surface metal caused by poor file technique or incorrect repair (visible after paint).

Method of Inspection: Visual evaluation and comparison with appearance zone requirements.

Appearance Zone Requirements: See [Table 13](#).

File and Grind Marks	
Zone	Quantity per Panel
A	None allowed
B	None allowed
C	N/A
D	N/A
E	None allowed

Table 13, File and Grind Marks

Pinholes

Condition: Small holes in a paint film, usually in the area of a silicon bronze joint, plastic parts, or polyester body fill (i.e., porosity).

Method of Inspection: Visual evaluation and comparison with appearance zone requirements.

Appearance Zone Requirements: See [Table 14](#).

Pinholes			
Zone	Quantity Per Panel Per Zone	Maximum Size (diameter)	Description
A	5 maximum	2 mm	2 allowed within a 6-inch (150-mm) diameter circle
B	Unlimited	2 mm	10 allowed within a 6-inch (150-mm) diameter circle
C	Unlimited	3 mm	No requirement

FLA COE
 FLB COE
 > FLD Conventional
 Business Class
 FLC 112 Conventional

> Century Class Conventional
 > Argosy
 > Cargo
 > Columbia
 > 122SD and Coronado

> Business Class M2
 > Cascadia
 > 108SD/114SD
 > New Cascadia

Pinholes			
Zone	Quantity Per Panel Per Zone	Maximum Size (diameter)	Description
D	N/A	N/A	N/A
E	5 maximum	2 mm	2 allowed within a 6-inch (150-mm) diameter circle

Table 14, Pinholes

Paint Chips

Condition: The absence of a small portion of the paint film usually caused by scraping or impacting the painted surface. Rock chips are a common example.

Method of Inspection: Visual evaluation and comparison with appearance zone requirements.

Appearance Zone Requirements: See [Table 15](#).

Paint Chips	
Zone	Quantity per Panel
A	None allowed
B	None allowed
C	No bare substrate or primer exposed
D	No bare substrate or primer exposed
E	None allowed

Table 15, Paint Chips

Stripes and Paint Break Edges

Condition: The chipping or loss of adhesion of small portions of the paint film from the edge of the stripe or paint break.

Definition: A stripe is any color less than 8 inches (203 mm) wide. A paint break is wider than 8 inches (203 mm).

Method of Inspection: Visual evaluation and comparison with appearance zone requirements.

Appearance Zone Requirements: See [Table 16](#).

Stripes and Paint Breaks		
Zone	Allowed	Description
A	Yes	Very slight loss of edge (less than 2 mm)
B	Yes	5 mm horizontal: 1 mm vertical: Must be at least 11-3/4 inches (300 mm) away from next occurrence
C	Yes	5 mm horizontal: 1 mm vertical: Must be at least 11-3/4 inches (300 mm) away from next occurrence
D	N/A	N/A
E	Yes	Very slight loss of edge (less than 2 mm)

Table 16, Stripes and Paint Breaks

Freightliner Service Bulletin

FLA COE
FLB COE
> FLD Conventional
Business Class
FLC 112 Conventional

> Century Class Conventional
> Argosy
> Cargo
> Columbia
> 122SD and Coronado

> Business Class M2
> Cascadia
> 108SD/114SD
> New Cascadia

Chassis Paint Requirements

The chassis is inspected for runs and sags, overspray, grind marks, inadequate paint coverage, and loss of adhesion (primer and/or topcoat) at the time of manufacture.

NOTE: Chassis includes frame rails, crossmembers, axles, drivelines, battery boxes, fuel tanks, and wheels.

Chassis Marks

Cosmetic surface marks and scratches are usually present on the frame rails. These surface marks are acceptable, as long as they are properly covered with paint.

Sags and Runs

Outside: Sags or runs on the outside of the rail or in visible areas of brackets, axle, hubs, or wheels shall be allowed, if no longer than 2 inches (50 mm) in length and have only a single crest. All other runs are unacceptable.

Inside: Sags or runs inside the rail and in less visible areas are allowed, if no longer than 6 inches (150 mm) in length. All other runs are unacceptable, including runs on drivelines, crossmembers, etc.

Overspray

Overspray on visible areas of bumpers, steps, battery and tool boxes, brackets, axles, hubs, wheels, drivelines, or frame rails is unacceptable. Overspray inside the frame rail is allowed, if it is not an unacceptable color.

Inadequate Paint Coverage

Inadequate or incomplete primer/substrate paint coverage, visible or hidden, is unacceptable and requires touch-up.

IMPORTANT: Several vehicle components, such as aluminum wheel hubs, are not meant to be painted.

Loss of Adhesion

Loss of adhesion to primer and/or topcoat on any visible or hidden areas of the chassis is unacceptable.

Tape Test

In instances where it is difficult to determine an adhesion problem, a tape test should be performed using the following steps.

1. Photograph an area that **does not** already have paint damage.
2. Take a piece of regular masking tape and press it firmly to the area.
3. Pull (jerk) the tape off quickly.
4. Photograph any paint attached to the tape.
5. Photograph any paint missing from where the tape was applied.
6. Large parts will need to have multiple areas tested.

FLA COE
FLB COE
> FLD Conventional
Business Class
FLC 112 Conventional

> Century Class Conventional
> Argosy
> Cargo
> Columbia
> 122SD and Coronado

> Business Class M2
> Cascadia
> 108SD/114SD
> New Cascadia

**Freightliner
Service Bulletin**

IMPORTANT: A second option is the cross-hatch method where a small "X" is scribed with a razor blade through the paint and primer prior to performing the tape test. However, if no adhesion problem is found, fixing the scribe "X" damage will be the **responsibility of the person performing the tape test.**

Topcoat Requirement

The chassis topcoat thickness (plus primer) requirement is to be 2.4 ± 0.5 mils using Axalta's (formerly DuPont's) Imron 5000 or the Standard Black Urethane.

The chassis topcoat thickness (plus primer) requirement is to be 2.5 ± 0.5 mils using PPG Delfleet Evolution® or Delfleet One™.

The chassis topcoat dry film thickness (plus primer) requirement is to be 2.6 ± 0.5 mils using Sherwin-Williams® Genesis® Single Stage System.

NOTE: Chassis paint finish gloss cannot be measured with a meter, because of the uneven metal surface condition.

Warranty

This is an informational bulletin only; warranty does not apply.